

CELANEX® 2300 GV1/20 - PBT

Description

General purpose, 20% glass fiber reinforced PBT

Chemical abbreviation according to ISO 1043-1: PBT Moulding compound ISO 7792- PBT, MGHR, 08-070N, GF20 Polybutylene terephthalate, 20 % glass fibre reinforced. Flammability UL 94 HB minimum thickness 1.2 mm. Recognition by Underwriters Laboratories, USA (UL)

Physical properties	Value	Unit	Test Standard
Density	90.5	lb/ft ³	ISO 1183
Melt volume rate, MVR	14	cm ³ /10min	ISO 1133
MVR temperature	482	°F	ISO 1133
MVR load	4.76	lb	ISO 1133
Molding shrinkage, parallel (flow)	0.4 - 0.5	%	ISO 294-4, 2577
Molding shrinkage, transverse normal	1.0 - 1.2	%	ISO 294-4, 2577
Water absorption, 23°C-sat	0.4	%	Sim. to ISO 62
Humidity absorption, 23°C/50%RH	0.15	%	ISO 62

Mechanical properties	Value	Unit	Test Standard
Tensile modulus	1.07E6	psi	ISO 527-1, -2
Tensile stress at break, 5mm/min	18100	psi	ISO 527-1, -2
Tensile strain at break, 5mm/min	3	%	ISO 527-1, -2
Tensile creep modulus, 1h	899000	psi	ISO 899-1
Tensile creep modulus, 1000h	696000	psi	ISO 899-1
Flexural strength, 23°C	24700	psi	ISO 178
Charpy impact strength, 23°C	21.9	ft-lb/in ²	ISO 179/1eU
Charpy impact strength, -30°C	20.5	ft-lb/in ²	ISO 179/1eU
Charpy notched impact strength, 23°C	3.57	ft-lb/in ²	ISO 179/1eA
Charpy notched impact strength, -30°C	3.33	ft-lb/in ²	ISO 179/1eA
Ball indentation hardness, 30s	27600	psi	ISO 2039-1

Thermal properties	Value	Unit	Test Standard
Melting temperature, 10°C/min	437	°F	ISO 11357-1/-3
DTUL at 1.8 MPa	383	°F	ISO 75-1, -2
DTUL at 0.45 MPa	428	°F	ISO 75-1, -2
DTUL at 8.0 MPa	212	°F	ISO 75-1, -2
Vicat softening temperature, 50°C/h 50N	419	°F	ISO 306
Coeff. of linear therm expansion, parallel	0.194	E-4/°F	ISO 11359-2
Limiting oxygen index (LOI)	20	%	ISO 4589-1/-2
Flammability @1.6mm nom. thickn.	HB	class	UL 94
thickness tested (1.6)	0.1	in	UL 94
Flammability at thickness h	HB	class	UL 94
thickness tested (h)	0.0394	in	UL 94
UL recognition (h)	UL	-	UL 94

Electrical properties	Value	Unit	Test Standard
Dielectric constant (Dk), 100Hz	4.2	-	IEC 60250
Dielectric constant (Dk), 1MHz	4.1	-	IEC 60250
Dissipation factor, 100Hz	16	E-4	IEC 60250
Dissipation factor, 1MHz	190	E-4	IEC 60250
Volume resistivity, 23°C	>1E13	Ohm*m	IEC 62631-3-1
Surface resistivity, 23°C	>1E15	Ohm	IEC 62631-3-2
Electric strength, 23°C (AC)	787	kV/in	IEC 60243-1
Comparative tracking index	PLC 1	-	UL 746
CTI 50 drops	350	V	IEC 60112




CELANEX® 2300 GV1/20 - PBT

Rheological calculation properties


	Value	Unit	Test Standard
Density of melt	76.8	lb/ft ³	Internal
Thermal conductivity of melt	0.156	W/(m K)	Internal
Spec. heat capacity melt	1840	J/(kg K)	Internal
Ejection temperature	428	°F	Internal

Diagrams


Viscosity-shear rate

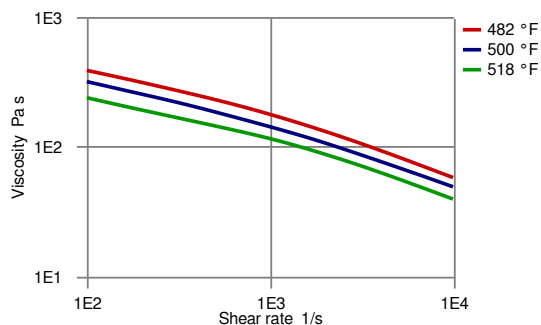


Shear stress-shear rate

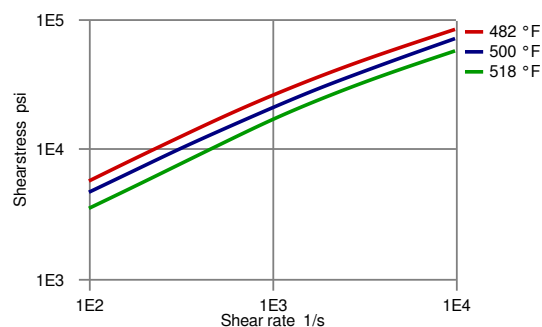


Dynamic Shear modulus-temperature

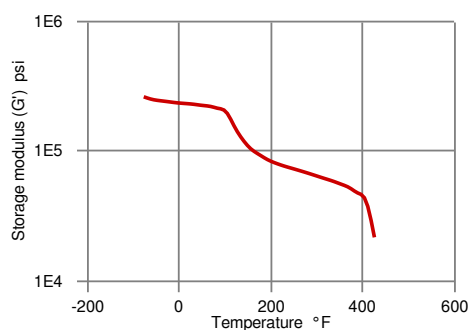


Stress-strain


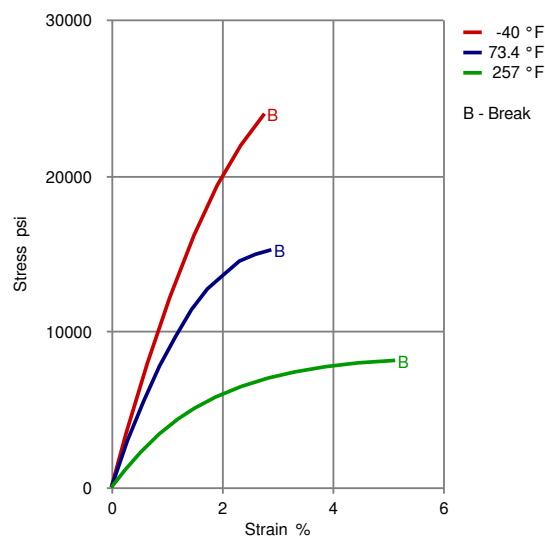


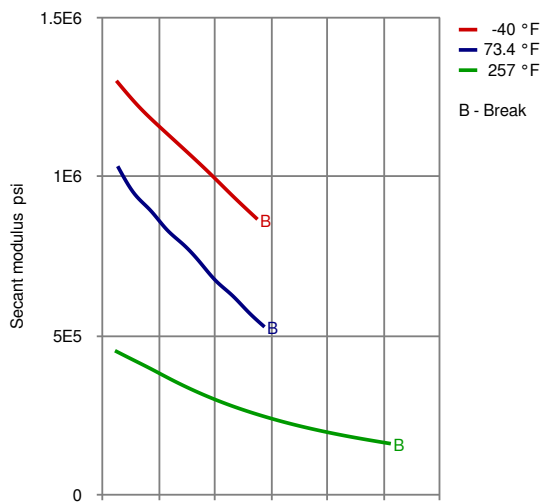

CAMPUS Stress-strain (isochronous) 73.4 °F

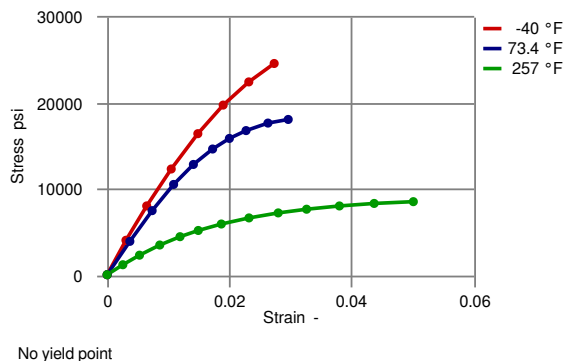

CAMPUS Creep modulus-time 73.4 °F

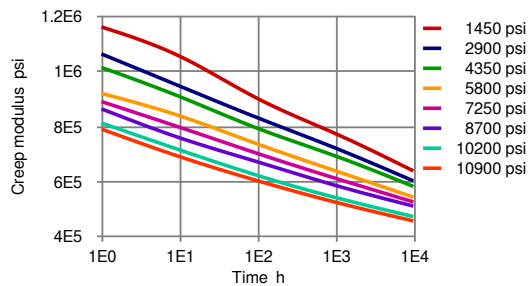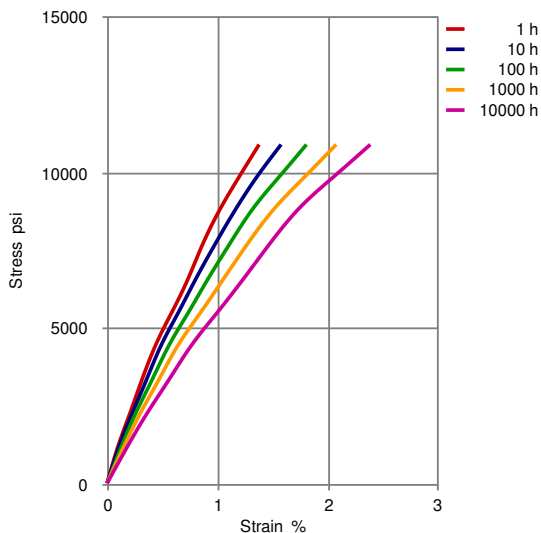

Typical injection moulding processing conditions

Pre Drying

Necessary low maximum residual moisture content	0.02	%
Drying time	2 - 4	h
Drying temperature	248 - 284	°F

Temperature

Hopper temperature	68 - 122	°F
Feeding zone temperature	374 - 392	°F
Zone1 temperature	482 - 500	°F
Zone2 temperature	482 - 500	°F
Zone3 temperature	491 - 509	°F
Zone4 temperature	491 - 509	°F
Nozzle temperature	500 - 518	°F

Value Unit

Value Unit



CELANEX® 2300 GV1/20 - PBT

Melt temperature	482 - 518	°F
Mold temperature	167 - 212	°F
Hot runner temperature	500 - 518	°F

Speed	Value
Injection speed	fast

Screw Speed	Value	Unit
Screw speed diameter, 25mm	90	RPM
Screw speed diameter, 40mm	75	RPM
Screw speed diameter, 55mm	60	RPM

Other text information

Pre-drying

CELANEX should in principle be predried. Because of the necessary low maximum residual moisture content the use of dry air dryers is recommended. The dew point should be $\leq -30^{\circ}\text{C}$. The time between drying and processing should be as short as possible.

Longer pre-drying times/storage

For subsequent storage of the material in the dryer until processed ($\leq 60\text{ h}$) it is necessary to lower the temperature to 100°C .

Injection molding

Melt Temperature 260-270 °C
Mold Temperature *) 75-85 °C
Maximum Barrel Residence Time **) 5-10 min
Injection Speed fast
Peripheral screw speed max. 0,3 m/sec
Back Pressure 10-30 bar
Injection Pressure 600-1000 bar
Holding Pressure 400-800 bar
Nozzle Design open design preferred

Injection speed, injection pressure and holding pressure have to be optimized to the individual article geometry. To avoid material degradation during processing low back pressure and minimum screw speed have to be used. Overheating of the material has to be avoided. For grades containing flame retardants, a maximum temperature of 265°C should not be exceeded.

Celanese recommends only externally heated hot runner systems.

*) For moulded parts with especially high requirements to the surface quality or dimensional stability, a mold temperature of up to 110°C can be advantageous.

**) If the cylinder temperatures are higher than the recommended maximum temperatures, the max. residence time in the barrel has to be reduced.

Injection Molding Preprocessing

To avoid hydrolytic degradation during processing, CELANEX resins have to be dried to a moisture level equal to or less than 0,02%. The drying should be done in a dry-air dryer (dew point $< -30^{\circ}\text{C}$) with a temperature of 120 to 140°C and a drying time of 2 to 4 hours. In case of longer residence times in the dry-air dryer, the temperature should be reduced to 100°C .

The time between drying and processing should be kept as short as possible. The processing machine feed hopper should be closed during the processing operation.

Characteristics

Special Characteristics	Auto spec approved, Heat resistant
Product Categories	Glass reinforced
Processing	Injection molding
Delivery Form	Pellets
Additives	Release agent



CELANEX® 2300 GV1/20 - PBT

Other Approvals

OEM	Specification	Additional Information
Bosch	N28 BN07-GF014	Natural & Black
Continental	SN 57908-7	
Li Auto	Q/LiA5310038	2021 (V2)
VW Group	VW50136	

