

CELANEX® 2402MT

unfilled easy flowing nucleated grade, for use in medical applications requiring high precision
 Celanex 2402MT is an unfilled and nucleated, easy flow PBT grade for injection molding processing.

Celanex 2402MT is a special grade developed for medical industry applications and complies with:

- CFR 21 (177.1660) of the Food and Drug Administration (FDA) and is listed in the Drug Master File (DMF 10047 (US) / 10033 (EU)) and the Device Master File (MAF 443 (US) / 1078 (EU))
- the corresponding EU and national registry regulatory requirements
- biocompatibility in tests corresponding to USP 23 Class VI/ISO 10993
- low residual monomers
- no animal products

Product information

Part Marking Code	> PBT <	ISO 11469
-------------------	---------	-----------

Rheological properties

Melt volume-flow rate	40 cm ³ /10min	ISO 1133
Temperature	250 °C	
Load	2.16 kg	
Moulding shrinkage range, parallel	1.8 - 2.2 %	ISO 294-4, 2577
Moulding shrinkage, normal	2.0 %	ISO 294-4, 2577
Moulding shrinkage range, normal	1.8 - 2.2 %	ISO 294-4, 2577

Typical mechanical properties

Tensile Modulus	2700 MPa	ISO 527-1/-2
Yield stress, 50mm/min	60 MPa	ISO 527-1/-2
Yield strain, 50mm/min	4 %	ISO 527-1/-2
Nominal strain at break	15 %	ISO 527-1/-2
Flexural Modulus	2550 MPa	ISO 178
Flexural Strength	80 MPa	ISO 178
Charpy impact strength, 23°C	135 kJ/m ²	ISO 179/1eU
Charpy impact strength, -30°C	130 kJ/m ²	ISO 179/1eU
Charpy notched impact strength, 23°C	5 kJ/m ²	ISO 179/1eA
Charpy notched impact strength, -30°C	4.5 kJ/m ²	ISO 179/1eA

Thermal properties

Melting temperature, 10°C/min	225 °C	ISO 11357-1/-3
Glass transition temperature, 10°C/min	60 °C	ISO 11357-1/-3
Temp. of deflection under load, 1.8 MPa	60 °C	ISO 75-1/-2
Temp. of deflection under load, 0.45 MPa	160 °C	ISO 75-1/-2
Vicat softening temperature, 50°C/h, 50N	190 °C	ISO 306
Coeff. of linear therm. expansion, parallel	110 E-6/K	ISO 11359-1/-2



CELANEX® 2402MT

Flammability

Burning Behav. at thickness h	HB class	UL 94
Thickness tested	0.80 mm	UL 94

Other properties

Humidity absorption, 2mm	0.2 %	Sim. to ISO 62
Water absorption, 2mm	0.45 %	Sim. to ISO 62
Density	1310 kg/m ³	ISO 1183

Injection

Drying Temperature	120 - 130 °C	
Drying Time, Dehumidified Dryer	4 h	
Processing Moisture Content	0.02 %	
Melt Temperature Optimum	250 °C	Internal
Max. mould temperature	70 - 90 °C	
Injection speed	medium-fast	

Characteristics

Additives	Release agent
Food contact	FDA 21 CFR

Additional information


Injection molding	Rear Temperature 450-470(230-240) deg F (deg C)
	Center Temperature 460-480(235-250) deg F (deg C)
	Front Temperature 470-500(240-260) deg F (deg C)
	Nozzle Temperature 480-500(250-260) deg F (deg C)
	Melt Temperature 460-500(235-260) deg F (deg C)
	Mold Temperature 150-200(65-93) deg F (deg C)
	Back Pressure 0-50 psi
	Screw Speed Medium
	Injection Speed Fast

Injection speed, injection pressure and holding pressure have to be optimized to the individual article geometry. To avoid material degradation during processing low back pressure and minimum screw speed have to be used. Overheating of the material has to be avoided, in particular for flame retardant grades. Up to 25% clean and dry regrind may be used.




CELANEX® 2402MT

Viscosity-shear rate

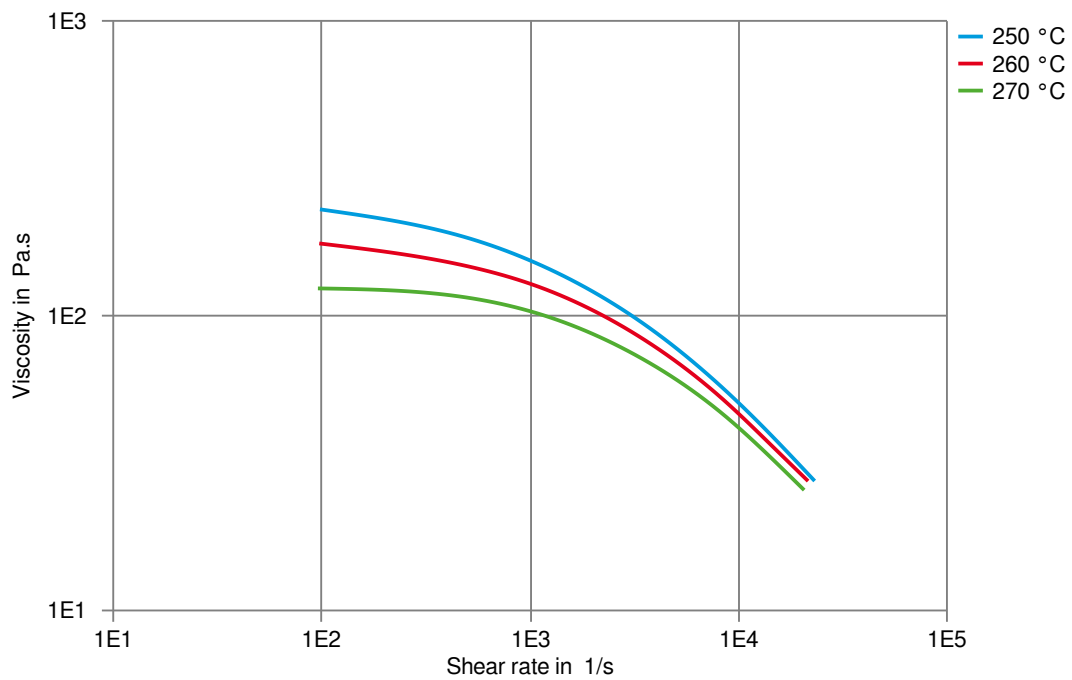


CELANEX® 2402MT

Shearstress-shear rate

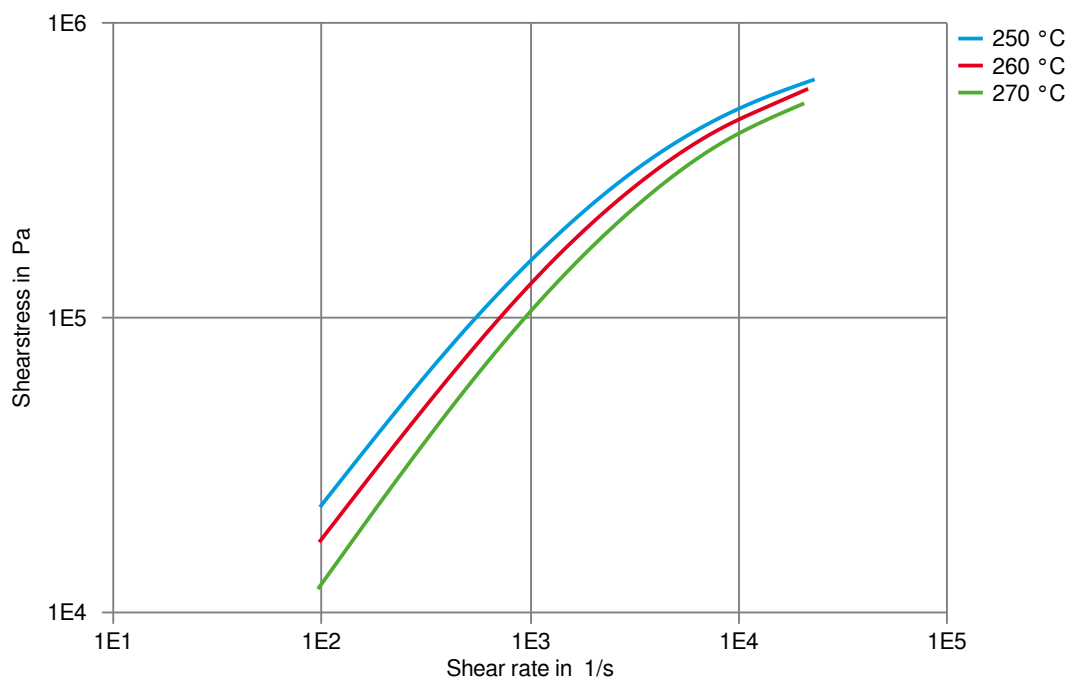


CELANEX® 2402MT

Stress-strain

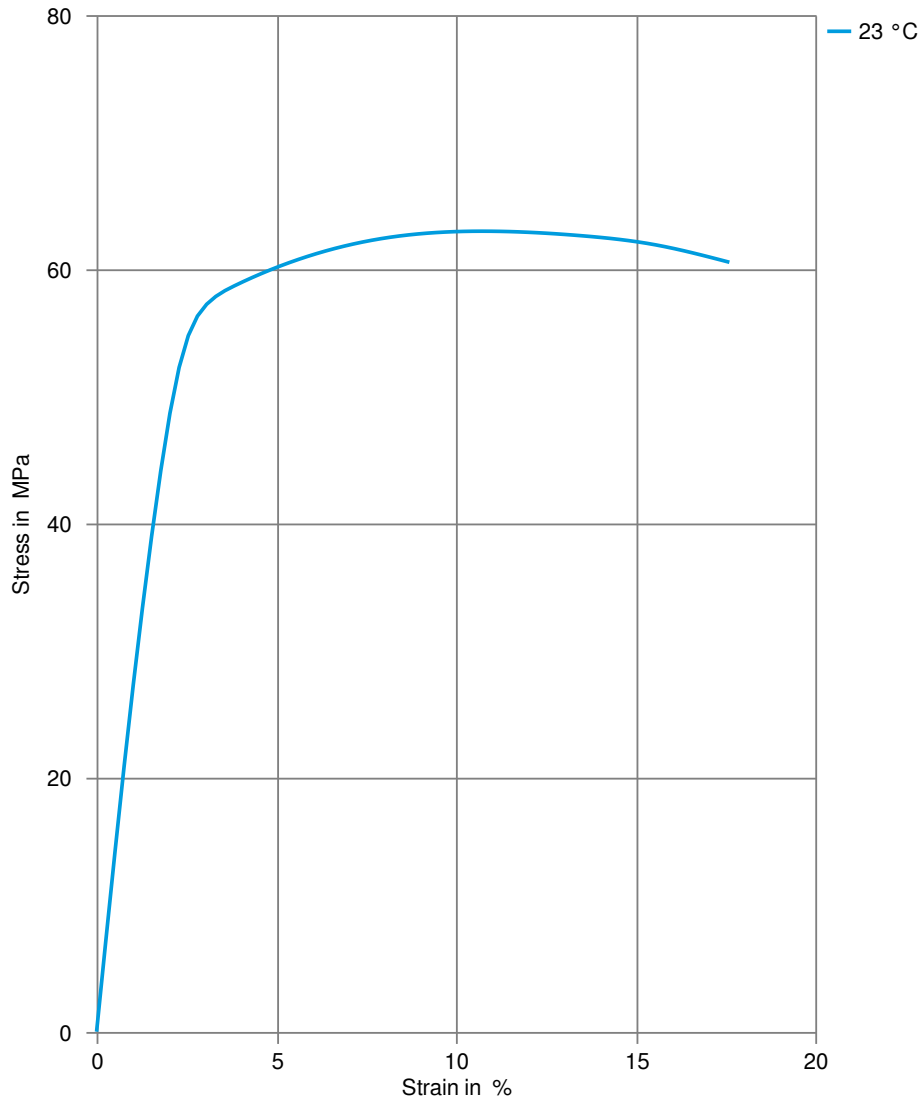


CELANEX® 2402MT

Secant modulus-strain

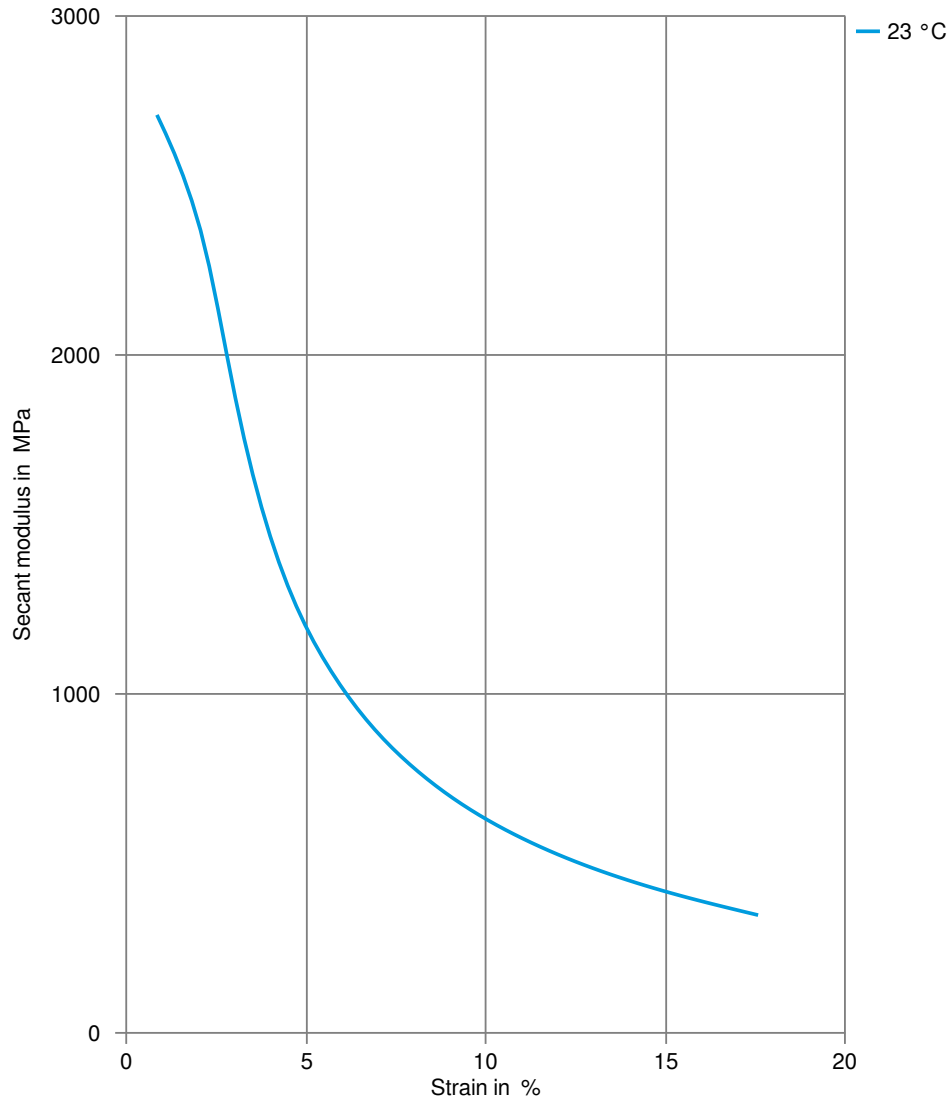

CELANEX® 2402MT

True stress-strain

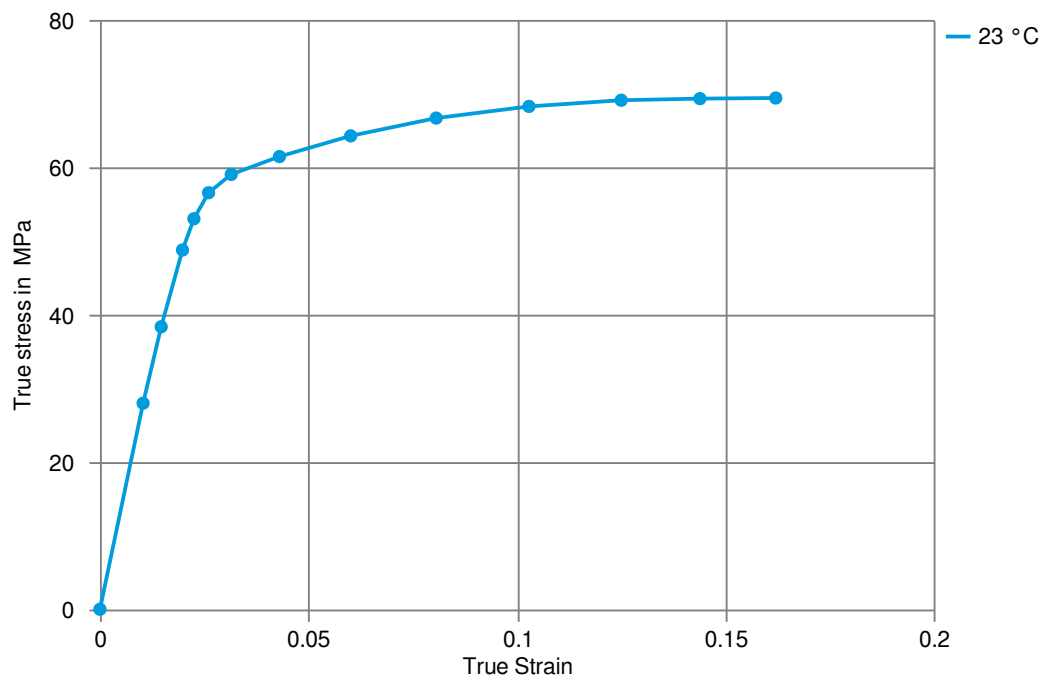

CELANEX® 2402MT

Processing Texts

Pre-drying

To avoid hydrolytic degradation during processing, CELANEX resins have to be dried to a moisture level equal to or less than 0.02%. Drying should be done in a dehumidifying hopper dryer capable of dewpoints <-40°F (-40°C) at 250°F (121°C) for 4 hours.

Longer pre-drying times/storage

For subsequent storage of the material in the dryer until processed (<= 60 h) it is necessary to lower the temperature to 100° C.

Injection molding

Rear Temperature 450-470(230-240) deg F (deg C)
Center Temperature 460-480(235-250) deg F (deg C)
Front Temperature 470-500(240-260) deg F (deg C)
Nozzle Temperature 480-500(250-260) deg F (deg C)
Melt Temperature 460-500(235-260) deg F (deg C)
Mold Temperature 150-200(65-93) deg F (deg C)
Back Pressure 0-50 psi
Screw Speed Medium
Injection Speed Fast

Injection speed, injection pressure and holding pressure have to be optimized to the individual article geometry. To avoid material degradation during processing low back pressure and minimum screw speed have to be used. Overheating of the material has to be avoided, in particular for flame retardant grades. Up to 25% clean and dry regrind may be used.

Injection molding Preprocessing

To avoid hydrolytic degradation during processing, CELANEX resins have to be dried to a moisture level equal to or less than 0.02%. Drying should be done in a dehumidifying hopper dryer capable of dewpoints <-30°F (-34°C) at 250°F (121°C) for 4 hours.

