

CELANEX® 3300-2 - PBT

Description

Celanex 3300-2 is a general purpose, 30% glass reinforced, polybutylene terephthalate that offers a superior combination of mechanical, electrical, and thermal properties. This grade provides outstanding processability and good chemical resistance. Celanex 3300-2 is a high flow material that contains an internal lubricant.

Physical properties	Value	Unit	Test Standard
Density	1530	kg/m ³	ISO 1183
Melt volume rate, MVR	17	cm ³ /10min	ISO 1133
MVR temperature	250	°C	ISO 1133
MVR load	2.16	kg	ISO 1133
Molding shrinkage, parallel	0.3 - 0.7	%	ISO 294-4, 2577
Molding shrinkage, normal	0.7 - 1.1	%	ISO 294-4, 2577
Water absorption, 23°C-sat	0.4	%	ISO 62
Humidity absorption, 23°C/50%RH	0.2	%	ISO 62

Mechanical properties	Value	Unit	Test Standard
Tensile modulus	9200	MPa	ISO 527-2/1A
Tensile stress at break, 5mm/min	130	MPa	ISO 527-2/1A
Tensile strain at break, 5mm/min	2.5	%	ISO 527-2/1A
Flexural modulus, 23°C	9700	MPa	ISO 178
Flexural strength, 23°C	210	MPa	ISO 178
Charpy impact strength, 23°C	46	kJ/m ²	ISO 179/1eU
Charpy impact strength, -30°C	45	kJ/m ²	ISO 179/1eU
Charpy notched impact strength, 23°C	8.5	kJ/m ²	ISO 179/1eA
Charpy notched impact strength, -30°C	8.5	kJ/m ²	ISO 179/1eA
Izod impact notched, 23°C	7.5	kJ/m ²	ISO 180/1A
Rockwell hardness (M-Scale)	90	M-Scale	ISO 2039-2

Thermal properties	Value	Unit	Test Standard
Melting temperature, 10°C/min	225	°C	ISO 11357-1/-3
Glass transition temperature, 10°C/min	60	°C	ISO 11357-1,-2,-3
DTUL at 1.8 MPa	205	°C	ISO 75-1, -2
DTUL at 0.45 MPa	225	°C	ISO 75-1, -2
DTUL at 8.0 MPa	150	°C	ISO 75-1, -2
Vicat softening temperature, 50°C/h 50N	220	°C	ISO 306
Coeff. of linear therm expansion, parallel	0.25	E-4/°C	ISO 11359-2
Coeff. of linear therm expansion, normal	1	E-4/°C	ISO 11359-2
Limiting oxygen index (LOI)	20	%	ISO 4589-1/-2
Flammability at thickness h	HB	class	UL 94
thickness tested (h)	0.71	mm	UL 94


Electrical properties	Value	Unit	Test Standard
Relative permittivity, 100Hz	4.5	-	IEC 60250
Relative permittivity, 1MHz	4.1	-	IEC 60250
Dissipation factor, 100Hz	22	E-4	IEC 60250
Dissipation factor, 1MHz	160	E-4	IEC 60250
Volume resistivity	>1E13	Ohm*m	IEC 60093
Surface resistivity	>1E15	Ohm	IEC 60093
Electric strength	31	kV/mm	IEC 60243-1
Comparative tracking index	425	-	IEC 60112




CELANEX® 3300-2 - PBT

Diagrams

True Stress-strain

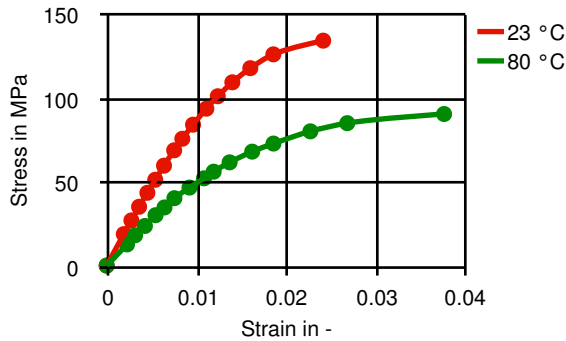

Moldflow Specific volume-temperature (pvT)

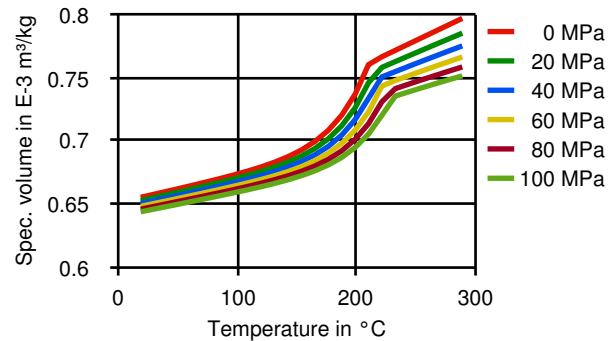

Typical injection moulding processing conditions

	Value	Unit	Test Standard
Pre Drying			
Necessary low maximum residual moisture content	0.02	%	-
Drying time	4	h	-
Drying temperature	120 - 130	°C	-
Temperature	Value	Unit	Test Standard
Hopper temperature	20 - 50	°C	-
Feeding zone temperature	20 - 50	°C	-
Zone1 temperature	230 - 240	°C	-
Zone2 temperature	235 - 250	°C	-
Zone3 temperature	235 - 250	°C	-
Zone4 temperature	240 - 260	°C	-
Nozzle temperature	250 - 260	°C	-
Melt temperature	235 - 290	°C	-
Mold temperature	65 - 93	°C	-
Hot runner temperature	250 - 260	°C	-
Speed	Value	Unit	Test Standard
Injection speed	medium-fast	-	-

Other text information

Pre-drying

To avoid hydrolytic degradation during processing, CELANEX resins have to be dried to a moisture level equal to or less than 0.02%. Drying should be done in a dehumidifying hopper dryer capable of dewpoints <-40 °F (-40 °C) at 250 °F (121 °C) for 4 hours.

Longer pre-drying times/storage

For subsequent storage of the material in the dryer until processed (<= 60 h) it is necessary to lower the temperature to 100 °C.

Injection molding

Rear Temperature 450-470(230-240) deg F (deg C)
Center Temperature 460-480(235-250) deg F (deg C)
Front Temperature 470-500(240-260) deg F (deg C)
Nozzle Temperature 480-500(250-260) deg F (deg C)
Melt Temperature 460-500(235-260) deg F (deg C)
Mold Temperature 150-200(65-93) deg F (deg C)
Back Pressure 0-50 psi
Screw Speed Medium
Injection Speed Fast

Injection speed, injection pressure and holding pressure have to be optimized to the individual article geometry. To avoid material degradation during processing low back pressure and minimum screw speed have to be used. Overheating of the material has to be avoided, in particular for flame retardant grades. Up to 25% clean and dry regrind may be used.



CELANEX® 3300-2 - PBT

Characteristics

Product Categories

Glass reinforced

Delivery Form

Pellets

Processing

Injection molding

Additives

Lubricants, Release agent

