

CELANEX® 4300

30% glass-fiber reinforced PBT grade; good impact strength
 Celanex 4300 is a toughened, 30% glass reinforced PBT.

Product information

Part Marking Code	PBT-GF30	ISO 11469
-------------------	----------	-----------

Rheological properties

Melt mass-flow rate	8 g/10min	ISO 1133
Melt mass-flow rate, Temperature	250 °C	
Melt mass-flow rate, Load	2.16 kg	
Moulding shrinkage range, parallel	0.3 - 0.5 %	ISO 294-4, 2577
Moulding shrinkage range, normal	0.8 %	ISO 294-4, 2577

Typical mechanical properties

Tensile Modulus	9300 MPa	ISO 527-1/-2
Stress at break, 5mm/min	130 MPa	ISO 527-1/-2
Strain at break, 5mm/min	3 %	ISO 527-1/-2
Flexural Modulus	9000 MPa	ISO 178
Flexural Strength	205 MPa	ISO 178
Charpy impact strength, 23°C	40 kJ/m ²	ISO 179/1eU
Charpy impact strength, -30°C	51 kJ/m ²	ISO 179/1eU
Charpy notched impact strength, 23°C	10 kJ/m ²	ISO 179/1eA
Charpy notched impact strength, -30°C	8.5 kJ/m ²	ISO 179/1eA
Izod notched impact strength, 23°C	12 kJ/m ²	ISO 180/1A
Hardness, Rockwell, M-scale	91	ISO 2039-2
Shore D hardness, 15s	83	ISO 48-4 / ISO 868

Thermal properties

Melting temperature, 10°C/min	225 °C	ISO 11357-1/-3
Glass transition temperature, 10°C/min	41 °C	ISO 11357-1/-3
Temp. of deflection under load, 1.8 MPa	200 °C	ISO 75-1/-2
Temp. of deflection under load, 0.45 MPa	220 °C	ISO 75-1/-2
Coeff. of linear therm. expansion, parallel	24 E-6/K	ISO 11359-1/-2
Coeff. of linear therm. expansion, normal	80 E-6/K	ISO 11359-1/-2

Flammability

Burning Behav. at thickness h	HB class	UL 94
Thickness tested	0.71 mm	UL 94



CELANEX® 4300

Electrical properties

Relative permittivity, 100Hz	2.8	IEC 62631-2-1
Relative permittivity, 1MHz	3.9	IEC 62631-2-1
Dissipation factor, 1MHz	220 E-4	IEC 62631-2-1
Volume resistivity	1E13 Ohm.m	IEC 62631-3-1
Surface resistivity	1E15 Ohm	IEC 62631-3-2
Electric strength	20 kV/mm	IEC 60243-1
Comparative tracking index	PLC 1 PLC	UL 746A

Other properties

Humidity absorption, 2mm	0.14 %	Sim. to ISO 62
Density	1530 kg/m³	ISO 1183

Injection

Drying Temperature	120 - 130 °C
Drying Time, Dehumidified Dryer	4 h
Processing Moisture Content	0.02 %
Max. mould temperature	65 - 93 °C
Injection speed	medium-fast

Additional information


Injection molding	Rear Temperature 450-470(230-240) deg F (deg C)
	Center Temperature 460-480(235-250) deg F (deg C)
	Front Temperature 470-500(240-260) deg F (deg C)
	Nozzle Temperature 480-500(250-260) deg F (deg C)
	Melt Temperature 460-500(235-260) deg F (deg C)
	Mold Temperature 150-200(65-93) deg F (deg C)
	Back Pressure 0-50 psi
	Screw Speed Medium
	Injection Speed Fast

Injection speed, injection pressure and holding pressure have to be optimized to the individual article geometry. To avoid material degradation during processing low back pressure and minimum screw speed have to be used. Overheating of the material has to be avoided, in particular for flame retardant grades. Up to 25% clean and dry regrind may be used.




CELANEX® 4300

Stress-strain

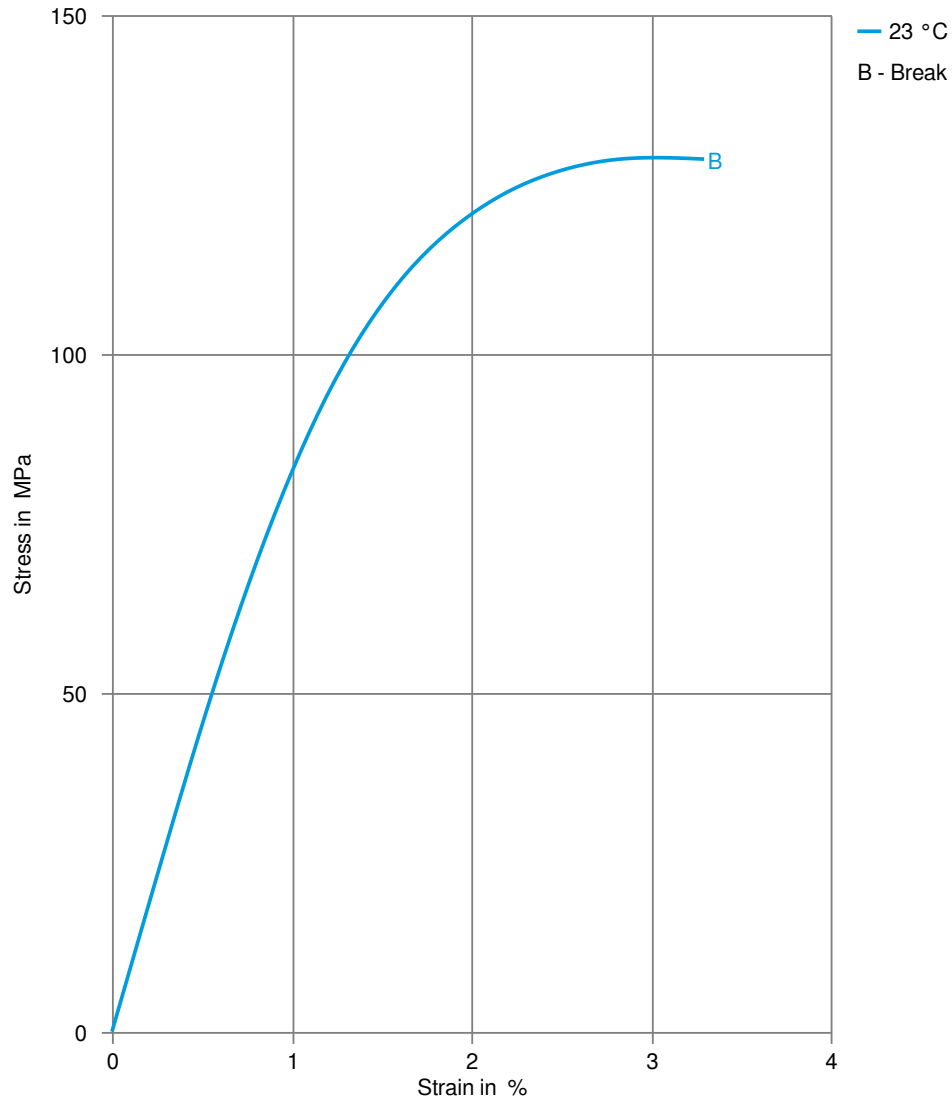


CELANEX® 4300

Secant modulus-strain

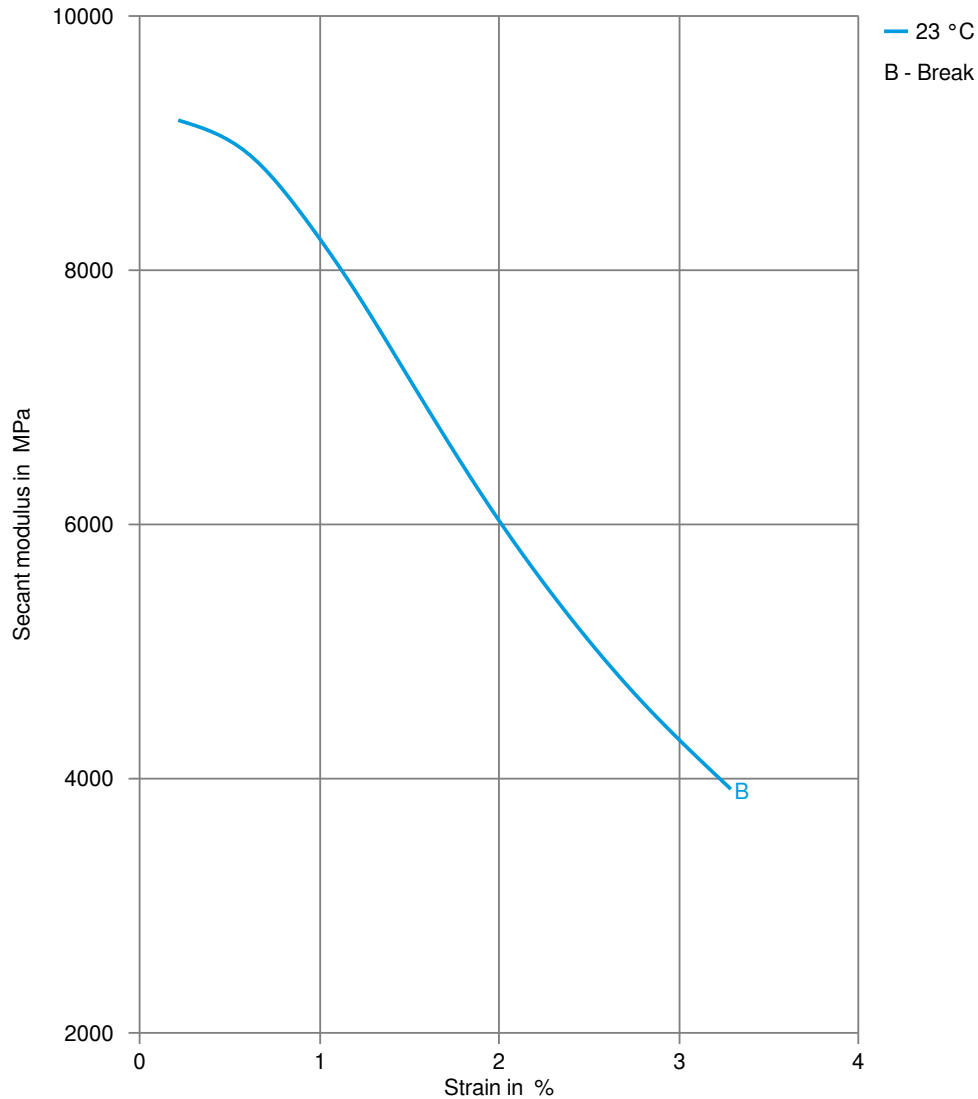

CELANEX® 4300

True stress-strain

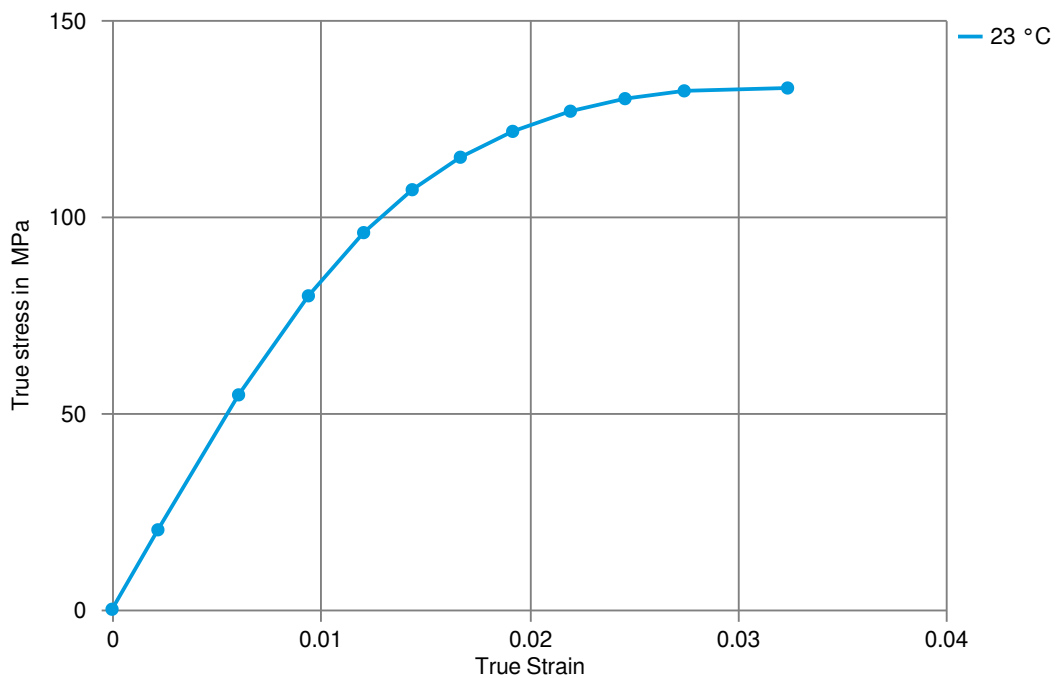

CELANEX® 4300

Processing Texts

Pre-drying

To avoid hydrolytic degradation during processing, CELANEX resins have to be dried to a moisture level equal to or less than 0.02%. Drying should be done in a dehumidifying hopper dryer capable of dewpoints <-40°F (-40°C) at 250°F (121°C) for 4 hours.

Longer pre-drying times/storage

For subsequent storage of the material in the dryer until processed (<= 60 h) it is necessary to lower the temperature to 100° C.

Injection molding

Rear Temperature 450-470(230-240) deg F (deg C)
 Center Temperature 460-480(235-250) deg F (deg C)
 Front Temperature 470-500(240-260) deg F (deg C)
 Nozzle Temperature 480-500(250-260) deg F (deg C)
 Melt Temperature 460-500(235-260) deg F (deg C)
 Mold Temperature 150-200(65-93) deg F (deg C)
 Back Pressure 0-50 psi
 Screw Speed Medium
 Injection Speed Fast

Injection speed, injection pressure and holding pressure have to be optimized to the individual article geometry. To avoid material degradation during processing low back pressure and minimum screw speed have to be used. Overheating of the material has to be avoided, in particular for flame retardant grades. Up to 25% clean and dry regrind may be used.

Injection molding Preprocessing

To avoid hydrolytic degradation during processing, CELANEX resins have to be dried to a moisture level equal to or less than 0.02%. Drying should be done in a dehumidifying hopper dryer capable of dewpoints <-30°F (-34°C) at 250°F (121°C) for 4 hours.

Other Approvals

Other Approvals

OEM	Specification	Additional Information
Stellantis - Chrysler	CPN 3199	CANOD

