

IMPET® 2700 GV1/30

30% glass-fiber reinforced grade

30% glass filled Polyethylene terephthalate (PET) with high flowability, excellent gloss, high modulus, and high heat deflection temperature.

Rheological properties

| | | |
|------------------------------|-----------------------|---------------------|
| Viscosity number | 70 cm ³ /g | ISO 307, 1157, 1628 |
| Moulding shrinkage, parallel | 0.2 - 0.4 % | ISO 294-4, 2577 |
| Moulding shrinkage, normal | 0.7 - 0.9 % | ISO 294-4, 2577 |

Typical mechanical properties

| | | |
|---------------------------------------|-----------------------|--------------|
| Tensile Modulus | 11500 MPa | ISO 527-1/-2 |
| Stress at break, 5mm/min | 175 MPa | ISO 527-1/-2 |
| Strain at break, 5mm/min | 2.2 % | ISO 527-1/-2 |
| Flexural Modulus | 11100 MPa | ISO 178 |
| Flexural Strength | 225 MPa | ISO 178 |
| Charpy impact strength, 23°C | 28 kJ/m ² | ISO 179/1eU |
| Charpy impact strength, -30°C | 28 kJ/m ² | ISO 179/1eU |
| Charpy notched impact strength, 23°C | 8.8 kJ/m ² | ISO 179/1eA |
| Charpy notched impact strength, -30°C | 8.8 kJ/m ² | ISO 179/1eA |
| Izod notched impact strength, 23°C | 7.5 kJ/m ² | ISO 180/1A |
| Hardness, Rockwell, M-scale | 123 | ISO 2039-2 |
| Ball indentation hardness, H 358/30 | 260 MPa | ISO 2039-1 |

Thermal properties

| | | |
|--|--------|----------------|
| Melting temperature, 10°C/min | 252 °C | ISO 11357-1/-3 |
| Glass transition temperature, 10°C/min | 80 °C | ISO 11357-1/-3 |
| Temp. of deflection under load, 1.8 MPa | 225 °C | ISO 75-1/-2 |
| Temp. of deflection under load, 0.45 MPa | 252 °C | ISO 75-1/-2 |
| Temp. of deflection under load, 8 MPa | 135 °C | ISO 75-1/-2 |
| Vicat softening temperature, 50°C/h, 50N | 255 °C | ISO 306 |

Flammability

| | | |
|--------------------------------------|----------|---------------|
| Burning Behav. at 1.5mm nom. thickn. | HB class | UL 94 |
| Thickness tested | 1.6 mm | UL 94 |
| Burning Behav. at thickness h | HB class | UL 94 |
| Thickness tested | 0.80 mm | UL 94 |
| Oxygen index | 25 % | ISO 4589-1/-2 |

Electrical properties

| | | |
|------------------------------|---------|---------------|
| Relative permittivity, 100Hz | 4.8 | IEC 62631-2-1 |
| Relative permittivity, 1MHz | 4.2 | IEC 62631-2-1 |
| Dissipation factor, 100Hz | 130 E-4 | IEC 62631-2-1 |
| Dissipation factor, 1MHz | 180 E-4 | IEC 62631-2-1 |



IMPET® 2700 GV1/30

| | | |
|----------------------------|------------|---------------|
| Volume resistivity | 2E14 Ohm.m | IEC 62631-3-1 |
| Surface resistivity | 3E15 Ohm | IEC 62631-3-2 |
| Electric strength | 33 kV/mm | IEC 60243-1 |
| Comparative tracking index | PLC 4 PLC | UL 746A |
| Arc Resistance | 39 s | Internal |

Other properties

| | | |
|--------------------------|------------|----------------|
| Humidity absorption, 2mm | 0.15 % | Sim. to ISO 62 |
| Water absorption, 2mm | 0.4 % | Sim. to ISO 62 |
| Density | 1600 kg/m³ | ISO 1183 |

Injection

| | |
|---------------------------------|----------------|
| Drying Temperature | 120 - 140 °C |
| Drying Time, Dehumidified Dryer | 2 - 4 h |
| Processing Moisture Content | 0.01 % |
| Screw tangential speed | 0.1 - 0.14 m/s |
| Max. mould temperature | 135 - 145 °C |
| Injection speed | fast |

Characteristics

| | |
|-----------|---------------|
| Additives | Release agent |
|-----------|---------------|

Additional information

| | |
|-------------------|---|
| Injection molding | Melt Temperature 270-290 °C |
| | Mold Temperature 135-145 °C |
| | Maximum Barrel Residence Time *) 5-10 min |
| | Injection Speed fast |
| | Peripheral screw speed max.0,3 m/sec |
| | Back Pressure 10-20 bar |
| | Injection Pressure 600-900 bar |
| | Holding Pressure 300-500 bar |
| | Nozzle Design open design preferred |

Injection speed, injection pressure and holding pressure have to be optimized to the individual article geometry. To avoid material degradation during processing low back pressure and minimum screw speed have to be used. Overheating of the material has to be avoided.


Ticona recommends only externally heated hot runner systems.

*) If the cylinder temperatures are higher than the recommended maximum temperatures, the max. residence time in the barrel has to be reduced.




IMPET® 2700 GV1/30

Stress-strain

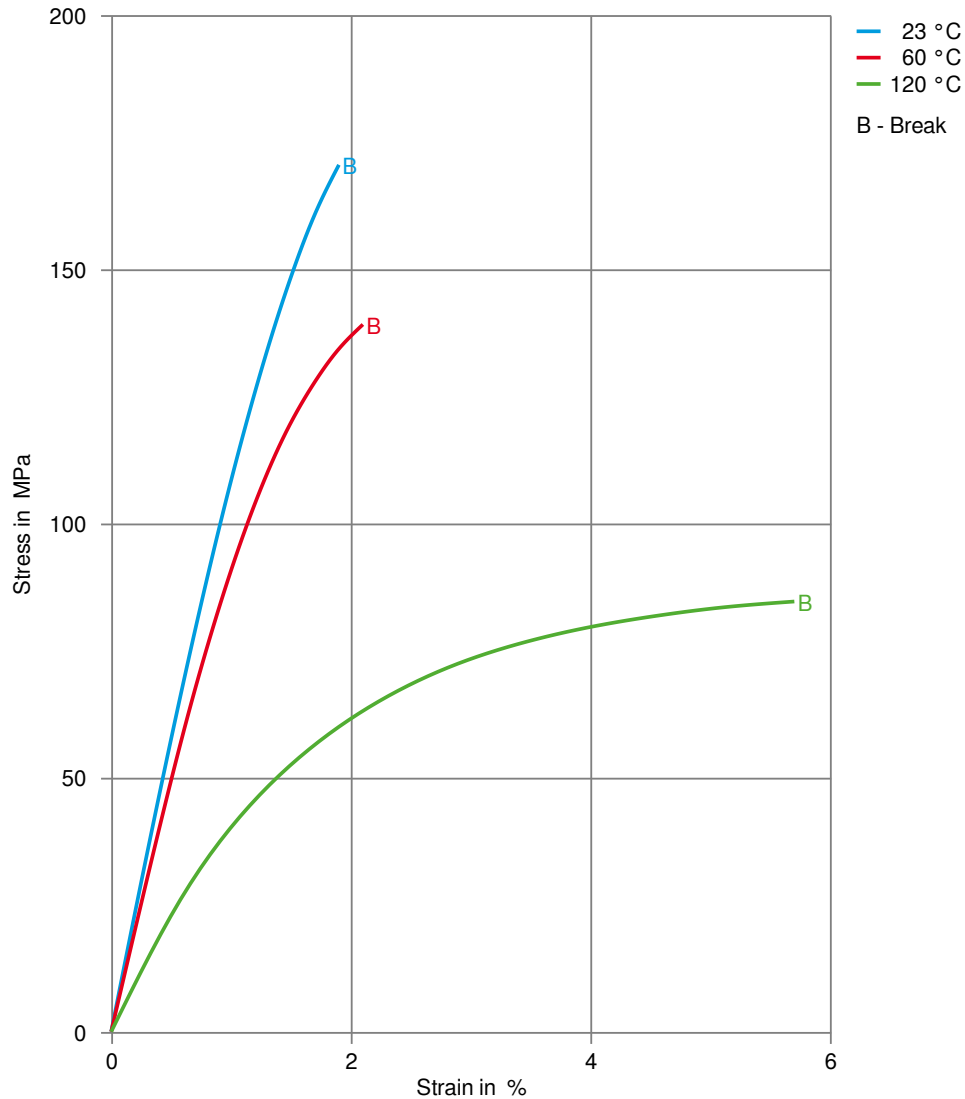

IMPET® 2700 GV1/30

Secant modulus-strain

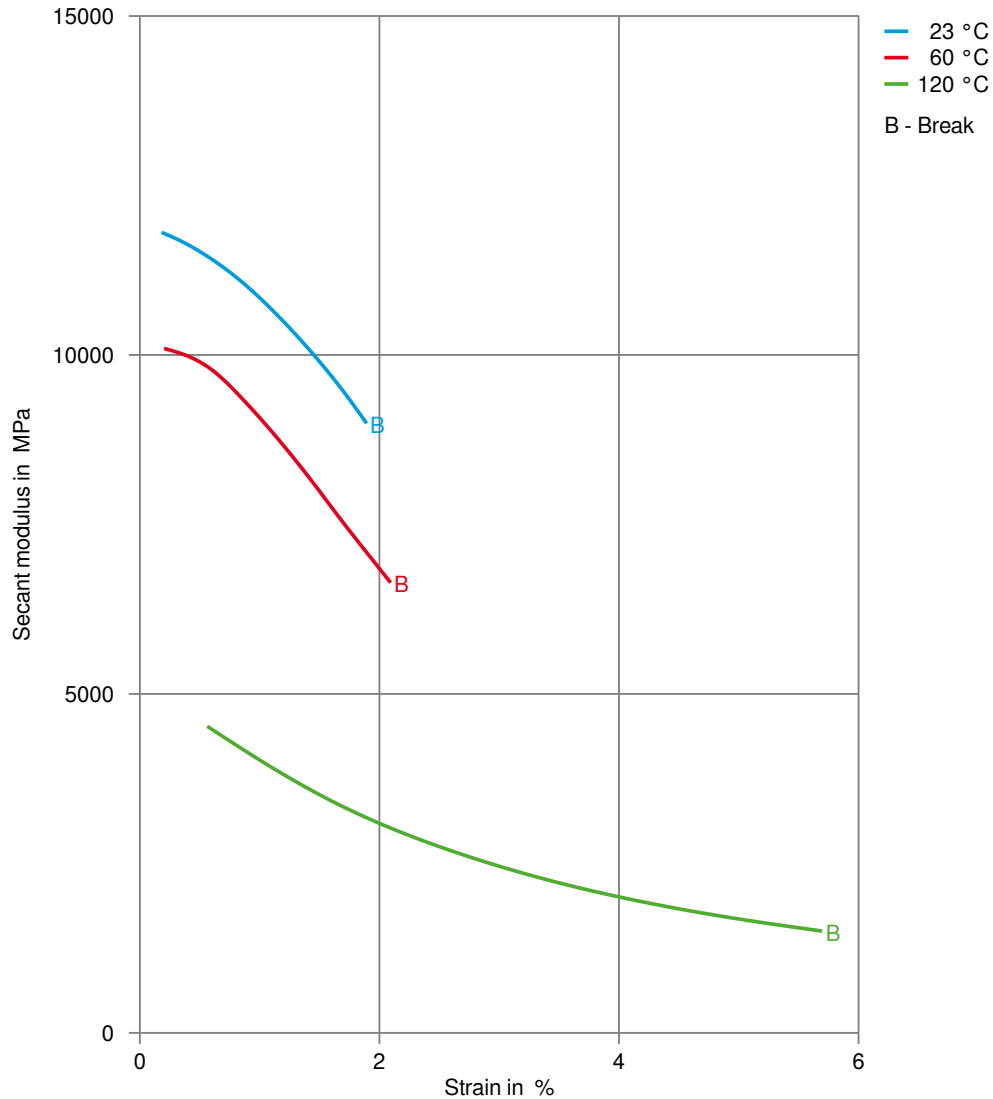

IMPET® 2700 GV1/30

Processing Texts

Pre-drying

IMPET should in principle be predried. Because of the necessary low maximum residual moisture content the use of dry air dryers is recommended. The dew point should be $\leq -30^{\circ}\text{C}$. The time between drying and processing should be as short as possible.

Longer pre-drying times/storage

For subsequent storage of the material in the dryer until processed (≤ 60 h) it is necessary to lower the temperature to 100°C .

Injection molding

Melt Temperature $270-290^{\circ}\text{C}$
 Mold Temperature $135-145^{\circ}\text{C}$
 Maximum Barrel Residence Time *) $5-10$ min
 Injection Speed fast
 Peripheral screw speed max. $0,3$ m/sec
 Back Pressure $10-20$ bar
 Injection Pressure $600-900$ bar
 Holding Pressure $300-500$ bar
 Nozzle Design open design preferred

Injection speed, injection pressure and holding pressure have to be optimized to the individual article geometry. To avoid material degradation during processing low back pressure and minimum screw speed have to be used. Overheating of the material has to be avoided.

Ticona recommends only externally heated hot runner systems.

*) If the cylinder temperatures are higher than the recommended maximum temperatures, the max. residence time in the barrel has to be reduced.

Injection molding Preprocessing

To avoid hydrolytic degradation during processing, IMPET resins have to be dried to a moisture level equal to or less than $0,01\%$. The drying should be done in a dry-air dryer (dew point $< -30^{\circ}\text{C}$) with a temperature of 120 to 140°C and a drying time of 2 to 4 hours. In case of longer residence times in the dry-air dryer, the temperature should be reduced to 100°C .

The time between drying and processing should be kept as short as possible. The processing machine feed hopper should be closed during the processing operation.

Other Approvals

Other Approvals

| OEM | Specification | Additional Information |
|----------------------------------|---------------|------------------------|
| Mercedes-Benz Group (Daimler) | | Lighting |



IMPET® 2700 GV1/30

| | | |
|-------|--------------|------|
| Geely | Q/JL J124006 | 2010 |
|-------|--------------|------|

