

HOSTAFORM® C 9021 G

Injection molding type like C 9021, with (R) GUR (PE-UHMW) modified

Chemical abbreviation according to ISO 1043-1: POM Molding compound ISO 29988- POM-K, M-GNS, 02-002 POM copolymer Injection molding type with (R) GUR (PE-UHMW) modified; good chemical resistance to solvents, fuel and strong alkalis as well as good hydrolysis resistance; high resistance to thermal and oxidative degradation. Burning rate ISO 3795 and FMVSS 302 < 100 mm/min for a thickness more than 1 mm. Ranges of applications: for parts under abrasion stress. FMVSS = Federal Motor Vehicle Safety Standard (USA)

Rheological properties

Melt volume-flow rate	5.5 cm ³ /10min	ISO 1133
Temperature	190 °C	
Load	2.16 kg	
Moulding shrinkage range, parallel	2.3 %	ISO 294-4, 2577
Moulding shrinkage range, normal	1.8 %	ISO 294-4, 2577

Typical mechanical properties

Tensile Modulus	2300 MPa	ISO 527-1/-2
Yield stress, 50mm/min	45 MPa	ISO 527-1/-2
Yield strain, 50mm/min	9 %	ISO 527-1/-2
Nominal strain at break	10 %	ISO 527-1/-2
Flexural Modulus	2100 MPa	ISO 178
Tensile creep modulus, 1h	2000 MPa	ISO 899-1
Tensile creep modulus, 1000h	1300 MPa	ISO 899-1
Charpy impact strength, 23°C	30 kJ/m ²	ISO 179/1eU
Charpy impact strength, -30°C	30 kJ/m ²	ISO 179/1eU
Charpy notched impact strength, 23°C	3.5 kJ/m ²	ISO 179/1eA
Charpy notched impact strength, -30°C	3 kJ/m ²	ISO 179/1eA
Ball indentation hardness, H 358/30	113 MPa	ISO 2039-1

Thermal properties

Melting temperature, 10°C/min	166 °C	ISO 11357-1/-3
Temp. of deflection under load, 1.8 MPa	88 °C	ISO 75-1/-2
Vicat softening temperature, 50°C/h, 50N	140 °C	ISO 306
Coeff. of linear therm. expansion, parallel	120 E-6/K	ISO 11359-1/-2

Electrical properties

Relative permittivity, 100Hz	3.8	IEC 62631-2-1
Relative permittivity, 1MHz	3.8	IEC 62631-2-1
Dissipation factor, 100Hz	25 E-4	IEC 62631-2-1
Dissipation factor, 1MHz	70 E-4	IEC 62631-2-1
Volume resistivity	1E12 Ohm.m	IEC 62631-3-1
Surface resistivity	1E14 Ohm	IEC 62631-3-2
Electric strength	35 kV/mm	IEC 60243-1
Comparative tracking index	PLC 0 PLC	UL 746A

Printed: 2023-09-15



HOSTAFORM® C 9021 G

Other properties

Humidity absorption, 2mm	0.2 %	Sim. to ISO 62
Water absorption, 2mm	0.8 %	Sim. to ISO 62
Density	1340 kg/m ³	ISO 1183

Injection

Drying Temperature	100 - 120 °C
Drying Time, Dehumidified Dryer	3 - 4 h
Processing Moisture Content	0.15 %
Screw tangential speed	0.2 - 0.21 m/s
Max. mould temperature	80 - 120 °C
Back pressure	2 MPa
Injection speed	slow

Characteristics

Additives	Release agent
-----------	---------------


Additional information

Injection molding	Standard injection moulding machines with three phase (15 to 25 D) plasticating screws will fit.
-------------------	--




HOSTAFORM® C 9021 G

Viscosity-shear rate

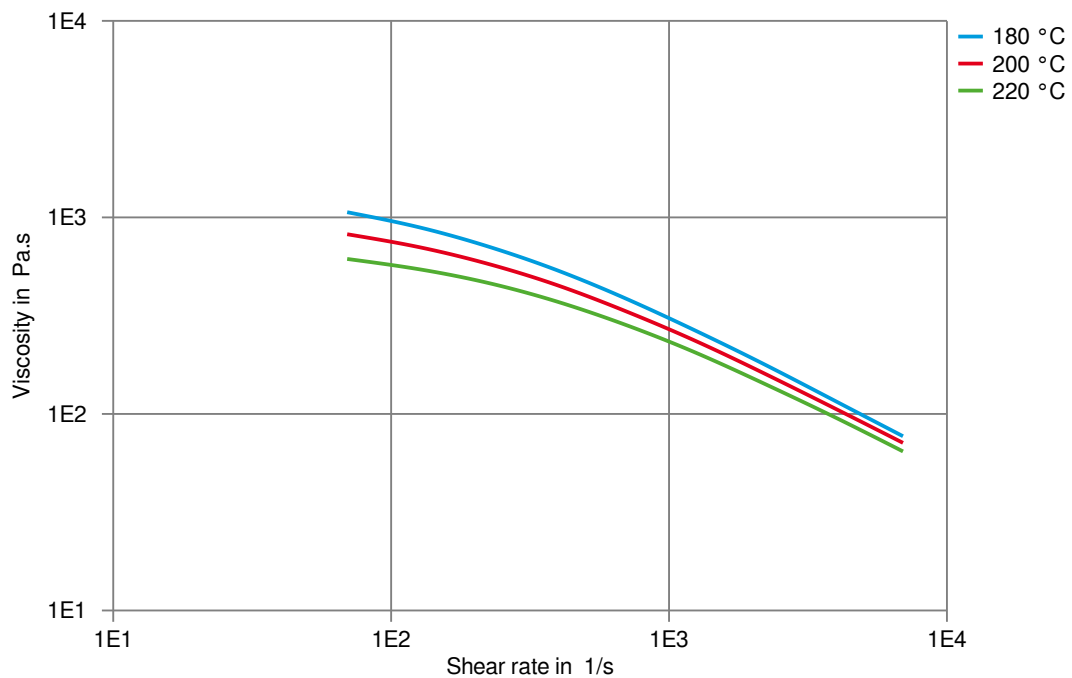

HOSTAFORM® C 9021 G

Shearstress-shear rate

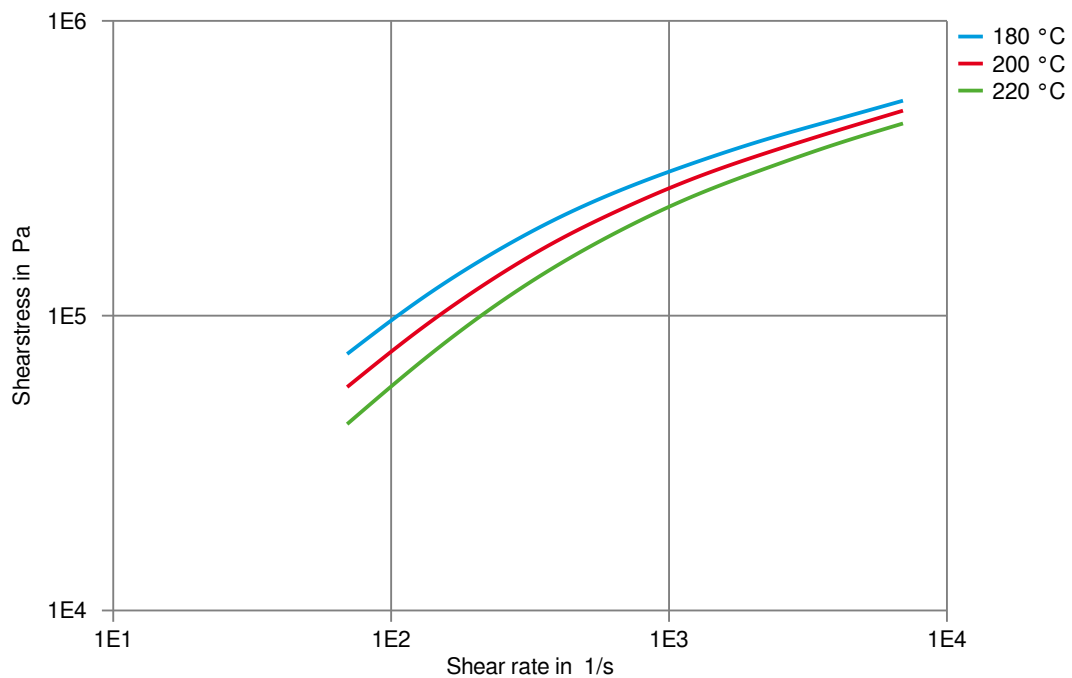


Printed: 2023-09-15



HOSTAFORM® C 9021 G

Stress-strain

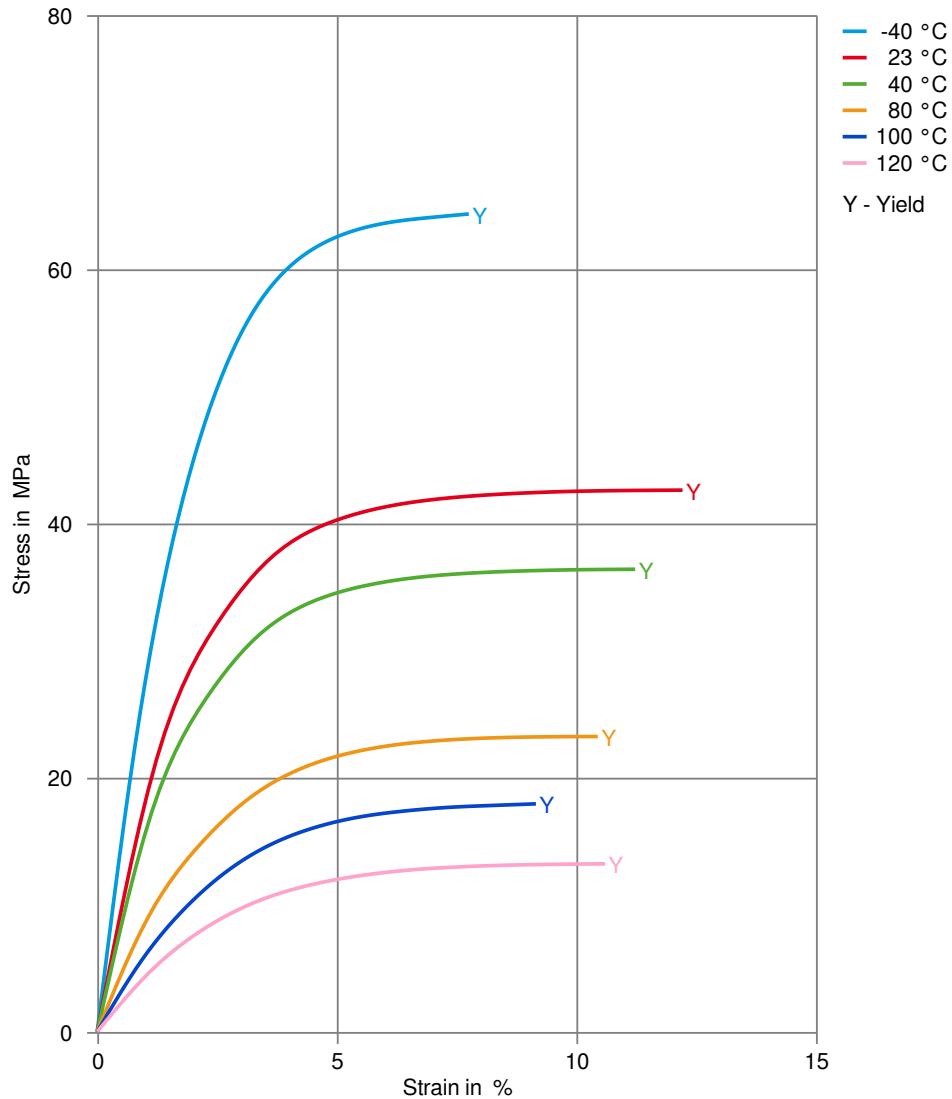


Printed: 2023-09-15



HOSTAFORM® C 9021 G

Secant modulus-strain

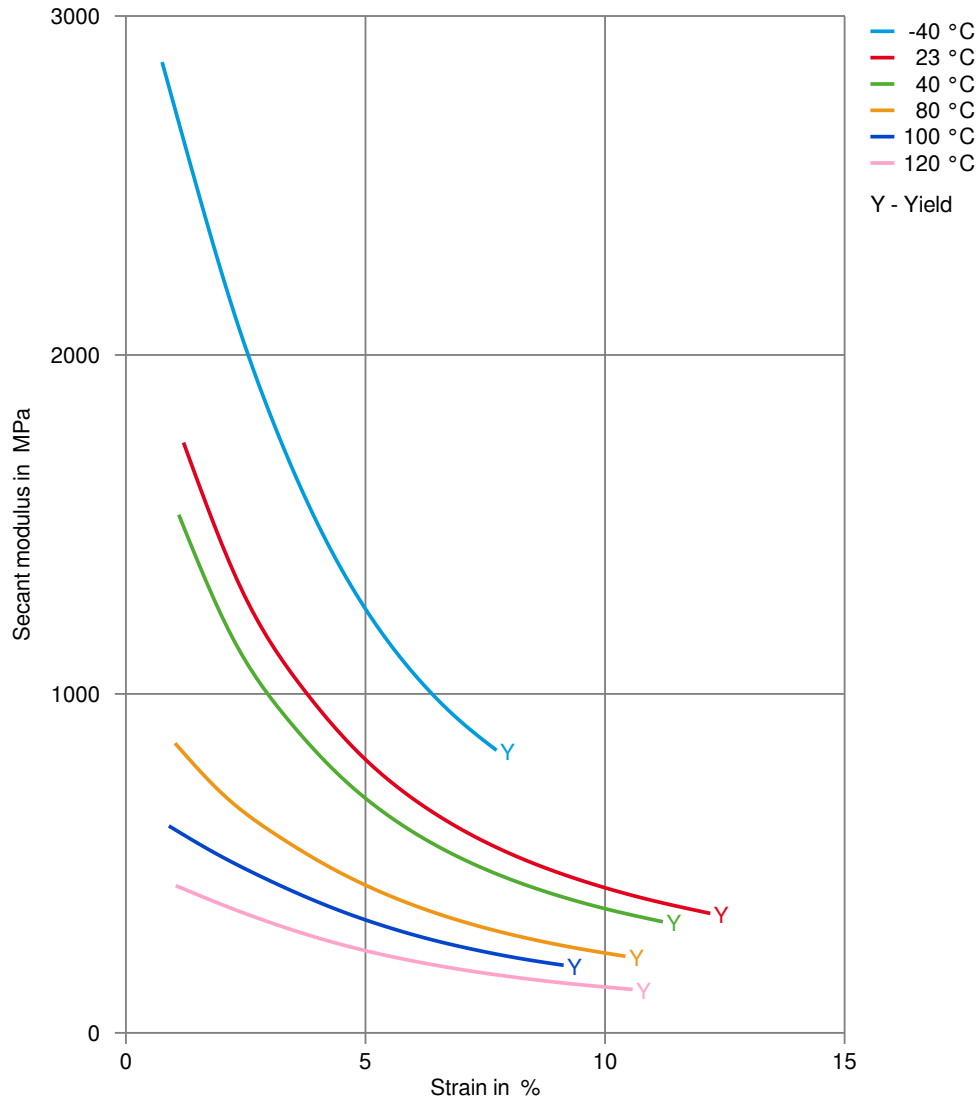

Printed: 2023-09-15



HOSTAFORM® C 9021 G

Processing Texts

Pre-drying	Drying is not normally required. If material has come in contact with moisture through improper storage or handling or through regrind use, drying may be necessary to prevent splay and odor problems.
Longer pre-drying times/storage	The product can then be stored in standard conditions until processed.
Injection molding	Standard injection moulding machines with three phase (15 to 25 D) plasticating screws will fit.
Injection molding Preprocessing	General drying is not necessary due to low moisture absorption of the resin. In case of bad storage conditions (water contact or condensed water) the use of a recirculating air dryer (100 to 120 °C / max. 40 mm layer / 3 to 6 hours) is recommended. Max. Water content 0,2 %
Injection molding Postprocessing	Conditioning e.g. moisturizing is not necessary.

Other Approvals

Other Approvals	OEM	Specification	Additional Information
	Bosch	N28 BN22-X013	Natural

Printed: 2023-09-15

