

FORTRON® 1120L4 - PPS


Description

Fortron 1120L4 is a 20% glass fiber reinforced injection molding grade.

Fortron 1120L4 is a 20% glass fiber reinforced injection molding grade exhibiting excellent heat and chemical resistance, inherent flame retardancy, high hardness and stiffness at elevated temperatures.

Physical properties	Value	Unit	Test Standard
Density	92.4	lb/ft ³	ISO 1183
Molding shrinkage, parallel (flow)	0.3	%	ISO 294-4, 2577
Molding shrinkage, transverse normal	0.7	%	ISO 294-4, 2577
Water absorption, 23°C-sat	0.02	%	Sim. to ISO 62
Mechanical properties	Value	Unit	Test Standard
Tensile stress at break, 5mm/min	17400	psi	ISO 527-1, -2
Tensile strain at break, 5mm/min	1.8	%	ISO 527-1, -2
Flexural modulus, 23°C	1.16E6	psi	ISO 178
Flexural strength, 23°C	24700	psi	ISO 178
Izod impact notched, 23°C	3.33	ft-lb/in ²	ISO 180/1A
Izod impact unnotched, 23°C	16.6	ft-lb/in ²	ISO 180/1U
Rockwell hardness (M-Scale)	100	M-Scale	ISO 2039-2
Thermal properties	Value	Unit	Test Standard
DTUL at 1.8 MPa	491	°F	ISO 75-1, -2
Coeff. of linear therm expansion, parallel	0.144	E-4/°F	ISO 11359-2
Coeff. of linear therm expansion, normal	0.294	E-4/°F	ISO 11359-2
Flammability @1.6mm nom. thickn.	V-0	class	UL 94
Electrical properties	Value	Unit	
Comparative tracking index	PLC 4		UL 746
Diagrams			



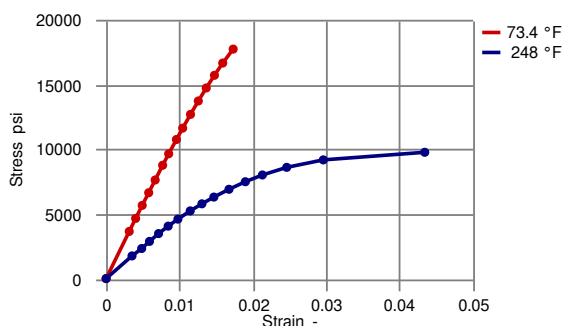

Typical injection moulding processing conditions

Pre Drying	Value	Unit
Necessary low maximum residual moisture content	0.02	%
Drying time	3 - 4	h
Drying temperature	266 - 284	°F
Temperature	Value	Unit
Hopper temperature	68 - 86	°F
Feeding zone temperature	140 - 176	°F
Zone1 temperature	554 - 572	°F
Zone2 temperature	590 - 608	°F
Zone3 temperature	626 - 644	°F
Zone4 temperature	626 - 644	°F
Nozzle temperature	590 - 626	°F
Melt temperature	626 - 644	°F
Mold temperature	284 - 320	°F
Hot runner temperature	626 - 644	°F
Pressure	Value	Unit
Back pressure max.	30	bar
Speed	Value	
Injection speed	fast	
Screw Speed	Value	Unit
Screw speed diameter, 25mm	120	RPM
Screw speed diameter, 40mm	75	RPM
Screw speed diameter, 55mm	50	RPM

Other text information

Pre-drying

FORTRON should in principle be predried. Because of the necessary low maximum residual moisture content the use of dry air dryers is recommended. The dew point should be $\leq -30^{\circ}\text{C}$. The time between drying and processing should be as short as possible.



FORTRON® 1120L4 - PPS

Longer pre-drying times/storage

For subsequent storage the material should be stored dry in the dryer until processed (≤ 60 h).

Injection molding

On injection molding machines with 15-25 D long three-section screws, as are usual in the trade, the FORTRON is processable. A shut-off nozzle is preferred to a free-flow nozzle.

Melt temperature 320-340 degC
Mold wall temperature at least 140 degC

A medium injection rate is normally preferred. All mold cavities must be effectively vented.

Injection Molding Preprocessing

Predrying in a dehumidified air dryer at 130 - 140 degC/3-4 hours is recommended.

Injection Molding Postprocessing

Tool temperature of at least 135 degC is recommended for parts to achieve maximum crystallizable potential.

Characteristics

Special Characteristics	Auto spec approved, Chemical resistant, Flame retardant, Heat resistant
Product Categories	Glass reinforced
Processing	Injection molding

