

KYNAR FLEX®

2800-20

Kynar Flex® resins are fluorinated thermoplastic copolymers.

Outstanding characteristics: chemical resistance, imperviousness to UV, high barrier properties, high purity, good mechanical and thermo-mechanical properties. This product is **NSF/ANSI/CAN 61** certified.

Kynar Flex® resin is a standard grade of granules, compared to the homopolymer grades, which exhibits a lower modulus, a better resistance to stress cracking in alkaline and oxidizing media, and a lower melting point.

For cable coating, extrusion of tube and plaque, injection molding.

Additional characteristics:

- Easily processed using conventional equipment
- Excellent thermal stability
- Retains properties after aging
- Pigmentable
- UL RTI temperature rating 125°C

PROPERTIES	VALUE	UNIT	TEST STANDARD
RHEOLOGICAL PROPERTIES			
Melt Volume-Flow Rate	4.5	cm ³ /10min	ISO 1133
Temperature	230	°C	-
	446	°F	-
Load	5	kg	-
	11	lb	-
Melt Flow Rate	1 - 8	g/10min	ASTM D1238
Temperature	230	°C	-
Load	5	kg	-
Melt Viscosity, 230°C, 100 s ⁻¹	12 - 20	kPoise	ASTM D3835
MECHANICAL PROPERTIES			
Tensile Modulus	700	MPa	ISO 527-1/-2
	102000	psi	
Tensile Modulus, 73 °F	552 - 896	MPa	ASTM D638
	80000 - 130000	psi	
Yield stress	27	MPa	ISO 527-1/-2
	3920	psi	
Tensile Strength at Yield, 73 °F	20 - 34.5	MPa	ASTM D638
	2900 - 5000	psi	
Yield strain	15	%	ISO 527-1/-2
Nominal Strain at Break	>50	%	ISO 527-1/-2
Tensile Strength at Break, 73 °F	17.2 - 34.5	MPa	ASTM D638
	2500 - 5000	psi	

KYNAR FLEX®

2800-20

Elongation at Break, 73 °F	100 - 300	%	ASTM D638
Taber Abrasion, CS 17 1000g:pad	16 - 19	mg/1000 cycles	ASTM-G195-13A
Hardness, Shore D, 73 °F	60 - 70	-	ASTM D2240
Flexural Modulus, 73 °F	483 - 758	MPa	ASTM D790
	70000 - 110000	psi	
Compressive Strength, 73 °F	31 - 41.4	MPa	ASTM D695
	4500 - 6000	psi	
Charpy Impact Strength, +23°C	177	kJ/m²	ISO 179/1eU
	84.2	ftlb/in²	
Charpy Impact Strength, -30°C	235	kJ/m²	ISO 179/1eU
	112	ftlb/in²	
Charpy Notched Impact Strength, +23°C	60	kJ/m²	ISO 179/1eA
	28.5	ftlb/in²	
Charpy Notched Impact Strength, -30°C	5	kJ/m²	ISO 179/1eA
	2.38	ftlb/in²	
Unnotched Impact Strength, 73 °F	No Break	kJ/m	ASTM D256
Notched Impact Strength, 73 °F	0.534 - 1.07	kJ/m	ASTM D256
	10 - 20	ftlb/in	
Coefficient of Friction, Static vs. Steel, 73 °F	0.33	-	ASTM D1894
Coefficient of Friction, Dynamic vs. Steel, 73 °F	0.33	-	ASTM D1894
THERMAL PROPERTIES			
Melting Temperature, 10°C/min	143	°C	ISO 11357-1/-3
Melting Point, 73 °F	140 - 145	°C	ASTM D3418
Glass Transition Temperature, 10°C/min	-40	°C	ISO 11357-1/-2
Glass Transition Temperature (Tg)	-41.1 - -39.4	°C	ASTM D7028
	-42 - -39	°F	
Temperature Rating	130	°C	UL RTI
	266	°F	
Temp. of Deflection Under Load, 1.80 MPa	48	°C	ISO 75-1/-2
	118	°F	
Heat Deflection Temperature, 264 Psi, 248 °F/hr	40 - 55	°C	ASTM D648
	104 - 131	°F	
Temp. of Deflection Under Load, 0.45 MPa	68	°C	ISO 75-1/-2
	154	°F	

KYNAR FLEX[®]

2800-20

Heat Deflection Temperature, 66 Psi, 248 °F/hr	60 - 75	°C	ASTM D648
	140 - 167	°F	
Vicat Softening Temperature, 50°C/h 50N	76	°C	ISO 306
	169	°F	
Coeff. of Linear Thermal Expansion, parallel	160	E-6/K	ISO 11359-1/-2
Coefficient of Thermal Expansion, 73 °F	12.6 - 18.5	10E-5/°C	ASTM D696
	7 - 10.3	10E-5/°F	
Burning Behav. at 1.5 mm Nominal Thickness	V-0	class	IEC 60695-11-10
Thickness Tested	1.6	mm	-
	0.0630	in	
Burning Behav. at Thickness h	V-0	class	IEC 60695-11-10
Thickness Tested	0.8	mm	-
	0.0315	in	
Oxygen Index	42	%	ISO 4589-1/-2
Limiting Oxygen Index, 73 °F	42	%	ASTM D2863
Thermal Conductivity	0.144 - 0.18	W/(m K)	ASTM D433
	1 - 1.25	BTU in /(hr ft ² F)	
Specific Heat	745 - 958	J/(kg K)	DSC
	0.28 - 0.36	BTU/(lb·°F)	
Thermal Decomposition TGA, in air	375	°C	1% wt. loss
	707	°F	
Thermal Decomposition TGA, in nitrogen	410	°C	1% wt. loss
	770	°F	
Relative Thermal Index, Mechanical	130	°C	UL 746B
	266	°F	
Relative Thermal Index, Electrical	130	°C	UL 746B
	266	°F	
ELECTRICAL PROPERTIES			
Relative Permittivity, 100Hz	11	-	IEC 60250
Relative Permittivity, 1MHz	6	-	IEC 60250
Dielectric Constant, 1 kHz	3.5 - 10.6	-	ASTM D150
Dissipation Factor, 100Hz	570	E-4	IEC 60250
Dissipation Factor, 1MHz	2340	E-4	IEC 60250
Dissipation Factor, 100 kHz	0.02 - 0.21	-	ASTM D150

KYNAR FLEX[®]

2800-20


Volume Resistivity	2E12	Ohm*m	IEC 60093
Volume Resistivity, DC 68 °F, 65% R.H.	2E14	Ohm*cm	ASTM D257
Dielectric (Electric) Strength, 73°F	1.3 - 1.5	kV/mil	ASTM D149
OTHER PROPERTIES			
Water Absorption	0.03	%	Sim. to ISO 62
Density	1780	kg/m ³	ISO 1183
	1.78	g/cm ³	
Specific Gravity, 73 °F	1.77 - 1.8	-	ASTM D792
OPTICAL PROPERTIES			
Refractive Index @ sodium D line	1.41	-	ASTM D542

MAIN APPLICATIONS:


- flexible tubing
- corrosion protection in the chemical industry
- coating (painting, co-extrusion)
- off shore
- wire and cable jacketing with and without cross-linking

DIAGRAMS

VISCOSITY-SHEAR RATE

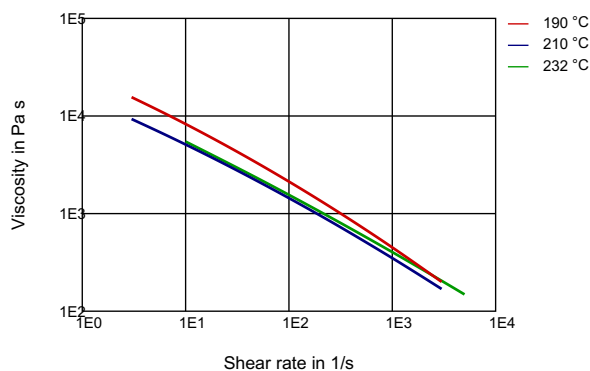


SHEARSTRESS-SHEAR RATE

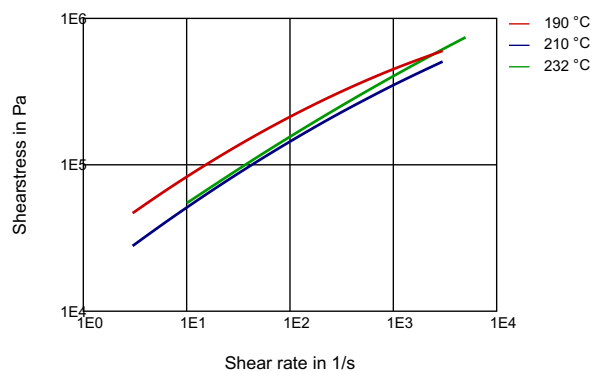


KYNAR FLEX[®]

2800-20

STRESS-STRAIN

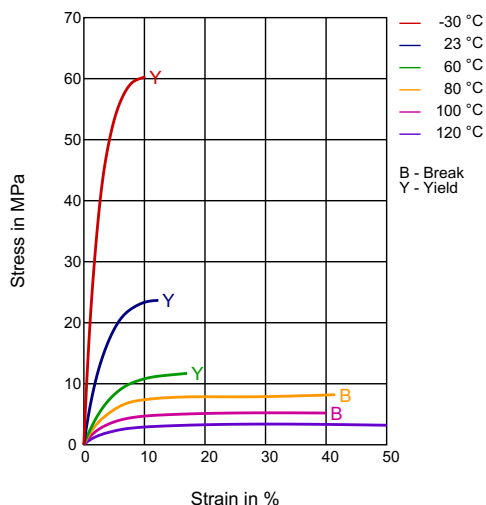

SECANT MODULUS-STRAIN

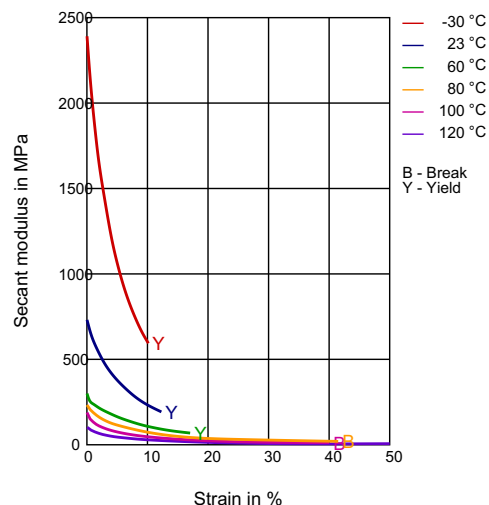

PROCESSING

Injection Molding, Film Extrusion, Profile Extrusion, Sheet Extrusion, Other Extrusion

DELIVERY FORM

Pellets

SPECIAL CHARACTERISTICS

Heat Stabilized, Light Stabilized

REGIONAL AVAILABILITY

North America, Europe, Asia Pacific, South and Central America, Near East/Africa