

AKROMID®

B3 GF 10 1 black (3658)

PA6 GF10

AKROMID® B3 GF 10 1 black (3658) is a 10% glass fibre reinforced, heat stabilised polyamide 6 with medium stiffness and strength.

Features

heat stabilised 130

Properties

Modulus

4.800 MPa

Strength

105 MPa

Impact

47 kJ/m²

Mechanical Properties

Tensile modulus

ISO 527-2

1 mm/min | d.a.m.

4800 MPa

1 mm/min | conditioned

2700 MPa

Tensile stress at break

ISO 527-2

5 mm/min | d.a.m.

105 MPa

5 mm/min | conditioned

55 MPa

Tensile strain at break

ISO 527-2

5 mm/min | d.a.m.

3 %

5 mm/min | conditioned

17 %

Flexural modulus

ISO 178

2 mm/min | d.a.m.

3500 MPa

Flexural strength

ISO 178

2 mm/min | d.a.m.

150 MPa

Charpy impact strength

ISO 179-1/1eU

23°C | d.a.m.

47 kJ/m²

23°C | conditioned

115 kJ/m²

-30°C | d.a.m.

41 kJ/m²

Charpy notched impact strength

ISO 179-1/1eA

23°C | d.a.m.

5 kJ/m²

23°C | conditioned

8 kJ/m²

-30°C | d.a.m.

5 kJ/m²

Thermal Properties

Temperature of deflection under load HDT/A ISO 75	1,8 MPa	200 °C
Temperature of deflection under load HDT/B ISO 75	0,45 MPa	220 °C
Melting temperature ISO 11357-3	DSC, 10K/min	220 °C

Flammability


Flammability UL 94	0,8 mm Wall thickness	HB Class
Burning rate (<100 mm/min) FMVSS 302	> 1 mm Thickness	+

General Properties

Density ISO 1183	23°C	1,2 g/cm ³
Humidity absorption ISO 1110	70°C, 62% r.H.	2,6 - 3,4 %
Water absorption ISO 62	23°C, saturated	8,5 - 9,0 %
Molding shrinkage ISO 294-4	flow transverse	0,4 % 0,7 %

Processing

The values mentioned are recommendations. We only recommend desiccant / dry air dryers or vacuum dryers. Too long a drying time and the resulting residual moisture content below the lower limit can lead to filling problems and surface defects. The specified drying time refers to closed and undamaged bagged material. When processing from previously opened bags or from octabins with polyolefin inliners, a longer drying time may be necessary. It is recommended to check the residual moisture content after the drying process.

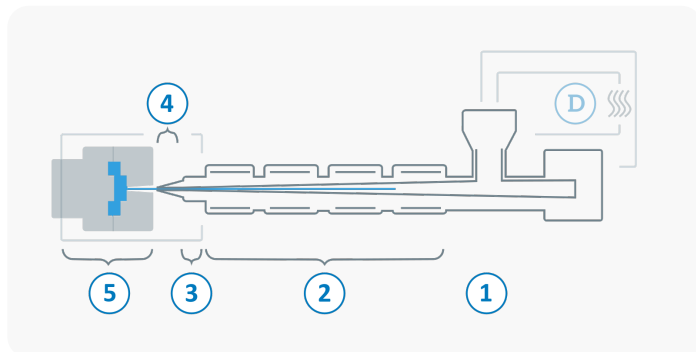

D	Drying time	0 - 4 h
	Drying temperature ($\tau \leq -30^{\circ}\text{C}$)	80 °C
	Processing moisture	0,02 - 0,1 %
1	Feed section	60 - 80 °C
2	Temperature Zone 1 - Zone 4	240 - 290 °C
3	Nozzle temperature	260 - 300 °C
4	Melt temperature	270 - 290 °C
5	Mold temperature	80 - 100 °C
→	Holding pressure, spec.	300 - 800 bar
←	Back pressure, spec.	50 - 150 bar
	Injection speed	medium to high
	Screw speed	8 - 15 m/min