

AKROMID®

B3 GF 35 1 black (2486)

PA6 GF35

AKROMID® B3 GF 35 1 black (2486) is a 35% glass fibre reinforced, heat stabilised Polyamid 6 with high stiffness and strength.

Features

heat stabilised 130

Properties

Modulus

11.500 MPa

Strength

195 MPa

Impact

100 kJ/m²

Mechanical Properties

Tensile modulus

ISO 527-2

1 mm/min | d.a.m.

11500 MPa

1 mm/min | conditioned

7300 MPa

Tensile stress at break

ISO 527-2

5 mm/min | d.a.m.

195 MPa

5 mm/min | conditioned

120 MPa

Tensile strain at break

ISO 527-2

5 mm/min | d.a.m.

3 %

5 mm/min | conditioned

5 %

Flexural modulus

ISO 178

2 mm/min | d.a.m.

10000 MPa

2 mm/min | conditioned

7200 MPa

Flexural strength

ISO 178

2 mm/min | d.a.m.

285 MPa

2 mm/min | conditioned

195 MPa

Charpy impact strength

ISO 179-1/1eU

23°C | d.a.m.

100 kJ/m²

23°C | conditioned

110 kJ/m²

-30°C | d.a.m.

90 kJ/m²

Charpy notched impact strength

ISO 179-1/1eA

23°C | d.a.m.

15 kJ/m²

23°C | conditioned

21 kJ/m²

-30°C | d.a.m.

13 kJ/m²

Izod impact strength ISO 180/1A	23°C d.a.m.	85 kJ/m²
Izod notched impact strength ISO 180/1A	23°C d.a.m.	20 kJ/m²
Ball indentation hardness ISO 2039-1	961N/30s d.a.m.	240 MPa

Thermal Properties

Temperature of deflection under load HDT/A ISO 75	1,8 MPa	215 °C
Temperature of deflection under load HDT/B ISO 75	0,45 MPa	220 °C
Temperature of deflection under load HDT/C ISO 75	8 MPa	165 °C
Melting temperature ISO 11357-3	DSC, 10K/min	220 °C
Temperature index for 50% loss of tensile strength IEC 60216	5.000 h 20.000 h	160 - 175 °C 130 - 150 °C

Flammability

Flammability UL 94	0,8 mm Wall thickness	HB Class
GWFI IEC 60695-2-12	1,6 mm Wall thickness	650 °C
Burning rate (<100 mm/min) FMVSS 302	> 1 mm Thickness	+

General Properties

Density ISO 1183	23°C	1,41 g/cm³
Humidity absorption ISO 1110	70°C, 62% r.H.	1,8 - 2,1 %

Water absorption	23°C, saturated	5,9 - 6,5 %
ISO 62		

Molding shrinkage	flow	0,1 - 0,3 %
ISO 294-4	transverse	0,5 - 0,7 %

Electrical Properties


Volume resistivity	d.a.m.	$10^{13} \Omega \times \text{cm}$
IEC 62631-3-1	conditioned	$10^{10} \Omega \times \text{cm}$

Surface resistivity	d.a.m.	$10^{12} \Omega$
IEC 62631-3-2	conditioned	$10^{10} \Omega$

Comparative tracking index	Test liquid A	600 V
IEC 60112		

Processing

The values mentioned are recommendations. We only recommend desiccant / dry air dryers or vacuum dryers. Too long a drying time and the resulting residual moisture content below the lower limit can lead to filling problems and surface defects. The specified drying time refers to closed and undamaged bagged material. When processing from previously opened bags or from octabins with polyolefin inliners, a longer drying time may be necessary. It is recommended to check the residual moisture content after the drying process.

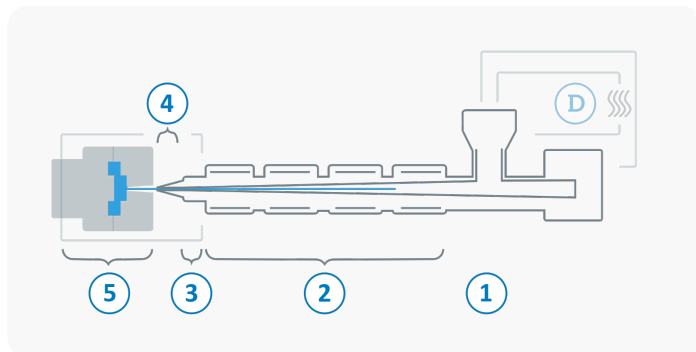

(D) Drying time	0 - 4 h
Drying temperature ($\tau \leq -30^{\circ}\text{C}$)	80 °C
Processing moisture	0,02 - 0,1 %
(1) Feed section	60 - 80 °C
(2) Temperature Zone 1 - Zone 4	240 - 290 °C
(3) Nozzle temperature	260 - 300 °C
(4) Melt temperature	270 - 290 °C
(5) Mold temperature	80 - 100 °C
(→) Holding pressure, spec.	300 - 800 bar
(←) Back pressure, spec.	50 - 150 bar
Injection speed	medium to high
Screw speed	8 - 15 m/min