

# AKROMID®

## B3 GK 30 black (1827)

PA6 GB30

AKROMID® B3 GK 30 black (1827) is a PA 6 filled with 30% glass beads. It is characterized by a high surface quality and low tendency to warp, which makes it suitable for use in technically demanding components in mechanical engineering and in the automotive industry.

### Features

low warpage

### Properties

Modulus	Strength	Impact
4.500 MPa	75 MPa	20 kJ/m <sup>2</sup>

## Sustainability

Recycled content 30 %

## Mechanical Properties

<b>Tensile modulus</b>	1 mm/min   d.a.m.	4500 MPa
ISO 527-2	1 mm/min   conditioned	2000 MPa
<b>Tensile stress at break</b>	5 mm/min   d.a.m.	75 MPa
ISO 527-2	5 mm/min   conditioned	40 MPa
<b>Tensile strain at break</b>	5 mm/min   d.a.m.	> 3,5 %
ISO 527-2	5 mm/min   conditioned	> 25 %
<b>Flexural modulus</b>	2 mm/min   d.a.m.	3300 MPa
ISO 178		
<b>Flexural strength</b>	2 mm/min   d.a.m.	110 MPa
ISO 178		
<b>Charpy impact strength</b>	23°C   d.a.m.	20 kJ/m <sup>2</sup>
ISO 179-1/1eU	23°C   conditioned	40 kJ/m <sup>2</sup>

<b>Charpy notched impact strength</b>	23°C   d.a.m.	<b>3 kJ/m<sup>2</sup></b>
ISO 179-1/1eA	23°C   conditioned	<b>5 kJ/m<sup>2</sup></b>

<b>Ball indentation hardness</b>	358N/30s   conditioned	<b>90 MPa</b>
ISO 2039-1	961N/30s   d.a.m.	<b>180 MPa</b>

## Thermal Properties

<b>Temperature of deflection under load HDT/A</b>	1,8 MPa	<b>70 °C</b>
ISO 75		

<b>Temperature of deflection under load HDT/B</b>	0,45 MPa	<b>185 °C</b>
ISO 75		

<b>Melting temperature</b>	DSC, 10K/min	<b>220 °C</b>
ISO 11357-3		

<b>Temperature index for 50% loss of tensile strength</b>	5.000 h	<b>100 °C</b>
IEC 60216	20.000 h	<b>90 °C</b>

<b>Vicat softening temperature B50</b>	50°C/50N	<b>205 °C</b>
ISO 306		

## Flammability

<b>Flammability</b>	1,6 mm Wall thickness	<b>HB Class</b>
UL 94		

<b>GWIT</b>	1,6 mm Wall thickness	<b>675 °C</b>
IEC 60695-2-13		

<b>Burning rate (&lt;100 mm/min)</b>	> 1 mm Thickness	<b>+</b>
FMVSS 302		

## General Properties

<b>Density</b>	23°C	<b>1,34 g/cm<sup>3</sup></b>
ISO 1183		

<b>Humidity absorption</b>	70°C, 62% r.H.	<b>2,0 - 2,2 %</b>
ISO 1110		

<b>Water absorption</b>	23°C, saturated	<b>6,5 %</b>
ISO 62		

---

<b>Molding shrinkage</b>	flow	<b>0,8 - 1,0 %</b>
ISO 294-4	transverse	<b>0,9 - 1,1 %</b>

---

## Rheological Properties


---

<b>Flowability</b>	1 mm Thickness	<b>120 mm</b>
AKRO	2 mm Thickness	<b>360 mm</b>

---

## Processing

The values mentioned are recommendations. We only recommend desiccant / dry air dryers or vacuum dryers. Too long a drying time and the resulting residual moisture content below the lower limit can lead to filling problems and surface defects. The specified drying time refers to closed and undamaged bagged material. When processing from previously opened bags or from octabins with polyolefin inliners, a longer drying time may be necessary. It is recommended to check the residual moisture content after the drying process.

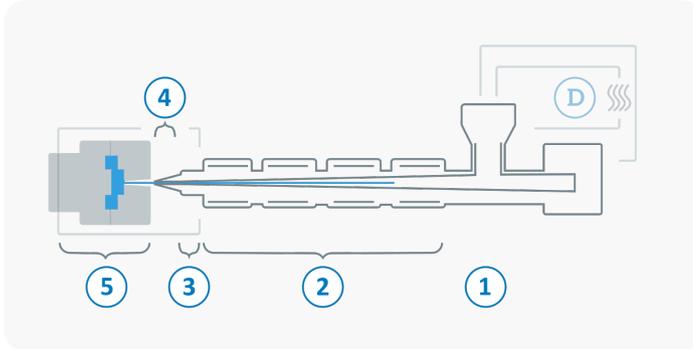

<b>D</b>	Drying time	0 - 4 h
	Drying temperature ( $\tau \leq -30^{\circ}\text{C}$ )	80 °C
	Processing moisture	0,02 - 0,1 %
<b>1</b>	Feed section	60 - 80 °C
<b>2</b>	Temperature Zone 1 - Zone 4	240 - 290 °C
<b>3</b>	Nozzle temperature	260 - 300 °C
<b>4</b>	Melt temperature	270 - 290 °C
<b>5</b>	Mold temperature	80 - 100 °C
<b>→</b>	Holding pressure, spec.	300 - 800 bar
<b>←</b>	Back pressure, spec.	50 - 150 bar
	Injection speed	medium to high
	Screw speed	8 - 15 m/min

## Diagrams

