

AKROMID®

B3 GK 50 black (2311)

PA6 GB50

AKROMID® B3 GK 50 black (2311) is a PA 6 filled with 50% glass beads. It is characterized by a high surface quality and low tendency to warp, which makes it suitable for use in technically demanding components in mechanical engineering and in the automotive industry.

Features

low warpage

Properties

| | | |
|-----------|----------|----------------------|
| Modulus | Strength | Impact |
| 5.700 MPa | 75 MPa | 42 kJ/m ² |

Sustainability

Recycled content 50 %

Mechanical Properties

| | | |
|---|------------------------|------------------|
| Tensile modulus ISO 527-2 | 1 mm/min d.a.m. | 5700 MPa |
| | 1 mm/min conditioned | 2000 MPa |
| Tensile stress at break ISO 527-2 | 5 mm/min d.a.m. | 75 MPa |
| | 5 mm/min conditioned | 45 MPa |
| Tensile strain at break ISO 527-2 | 5 mm/min d.a.m. | 4 % |
| | 5 mm/min conditioned | > 10 % |
| Flexural modulus ISO 178 | 2 mm/min d.a.m. | 5200 MPa |
| Flexural strength ISO 178 | 2 mm/min d.a.m. | 135 MPa |

| | | |
|-------------------------------|----------------|----------------------|
| Charpy impact strength | 23°C d.a.m. | 42 kJ/m ² |
| ISO 179-1/1eU | -30°C d.a.m. | 32 kJ/m ² |

| | | |
|---------------------------------------|--------------------|---------------------|
| Charpy notched impact strength | 23°C d.a.m. | 3 kJ/m ² |
| ISO 179-1/1eA | 23°C conditioned | 7 kJ/m ² |
| | -30°C d.a.m. | 1 kJ/m ² |

Thermal Properties

| | | |
|---|---------|-------|
| Temperature of deflection under load HDT/A | 1,8 MPa | 75 °C |
| ISO 75 | | |

| | | |
|---|----------|--------|
| Temperature of deflection under load HDT/B | 0,45 MPa | 188 °C |
| ISO 75 | | |

| | | |
|----------------------------|--------------|--------|
| Melting temperature | DSC, 10K/min | 225 °C |
| ISO 11357-3 | | |

Flammability

| | | |
|---------------------|-----------------------|----------|
| Flammability | 1,6 mm Wall thickness | HB Class |
| UL 94 | | |

| | | |
|----------------|-----------------------|--------|
| GWFI | 1,6 mm Wall thickness | 650 °C |
| IEC 60695-2-12 | | |

| | | |
|----------------|-----------------------|--------|
| GWIT | 1,6 mm Wall thickness | 675 °C |
| IEC 60695-2-13 | | |

| | | |
|--------------------------------------|------------------|---|
| Burning rate (<100 mm/min) | > 1 mm Thickness | + |
| FMVSS 302 | | |

General Properties

| | | |
|----------------|------|------------------------|
| Density | 23°C | 1,54 g/cm ³ |
| ISO 1183 | | |

| | | |
|----------------------------|----------------|-------|
| Humidity absorption | 70°C, 62% r.H. | 1,5 % |
| ISO 1110 | | |

| | | |
|-------------------------|-----------------|-------|
| Water absorption | 23°C, saturated | 4,7 % |
| ISO 62 | | |

| | | |
|--------------------------|------------|--------------------|
| Molding shrinkage | flow | 0,6 - 0,8 % |
| ISO 294-4 | transverse | 0,7 - 0,9 % |

Electrical Properties


| | | |
|---------------------------|--------|-------------------------------|
| Volume resistivity | d.a.m. | 10¹⁵ Ω x cm |
| IEC 62631-3-1 | | |

| | | |
|----------------------------|--------|--------------------------|
| Surface resistivity | d.a.m. | 10¹³ Ω |
| IEC 62631-3-2 | | |

| | | |
|-----------------------------------|---------------|--------------|
| Comparative tracking index | Test liquid A | 500 V |
| IEC 60112 | | |

Processing

The values mentioned are recommendations. We only recommend desiccant / dry air dryers or vacuum dryers. Too long a drying time and the resulting residual moisture content below the lower limit can lead to filling problems and surface defects. The specified drying time refers to closed and undamaged bagged material. When processing from previously opened bags or from octabins with polyolefin inliners, a longer drying time may be necessary. It is recommended to check the residual moisture content after the drying process.

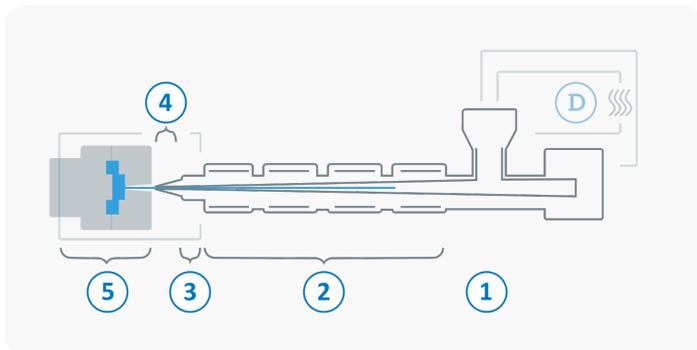

| | | |
|----------|--|----------------|
| D | Drying time | 0 - 4 h |
| | Drying temperature ($\tau \leq -30^{\circ}\text{C}$) | 80 °C |
| | Processing moisture | 0,02 - 0,1 % |
| 1 | Feed section | 60 - 80 °C |
| 2 | Temperature Zone 1 - Zone 4 | 240 - 290 °C |
| 3 | Nozzle temperature | 260 - 300 °C |
| 4 | Melt temperature | 270 - 290 °C |
| 5 | Mold temperature | 80 - 100 °C |
| → | Holding pressure, spec. | 300 - 800 bar |
| ← | Back pressure, spec. | 50 - 150 bar |
| | Injection speed | medium to high |
| | Screw speed | 8 - 15 m/min |