

AKROMID®

B3 ICF 15 black (5026)

PA6 CF15

AKROMID® B3 ICF 15 black (5026) is a high performance Polyamide 6 with 15% carbon fiber reinforcement, offering medium stiffness and flexural strength. Compared to glass fiber-reinforced PA 6, it provides an optimized strength-to-weight ratio. Thanks to its low density and high mechanical durability, this material is ideal for load-bearing components in the automotive industry, such as lightweight structural parts, as well as for sports and leisure applications, including high-stress sports equipment and technical components. Furthermore, the material can be processed with either gas injection (GIT) or water injection technology (WIT).

Features

recycled content reduced density antistatic/conductive tribological modified Sports & leisure lightweight construction

Properties



Sustainability

Recycled content 15 %

Mechanical Properties

Tensile modulus ISO 527-2	1 mm/min d.a.m.	11000 MPa
	1 mm/min conditioned	5000 MPa
Tensile stress at break ISO 527-2	5 mm/min d.a.m.	140 MPa
	5 mm/min conditioned	80 MPa
Tensile strain at break ISO 527-2	5 mm/min d.a.m.	3 %
	5 mm/min conditioned	7 %
Flexural modulus ISO 178	2 mm/min d.a.m.	9000 MPa
	2 mm/min conditioned	7000 MPa

Flexural strength	2 mm/min d.a.m.	200 MPa
ISO 178	2 mm/min conditioned	150 MPa
Flexural strain at break	2 mm/min d.a.m.	3,5 %
ISO 178	2 mm/min conditioned	6 %
Charpy impact strength	23°C d.a.m.	55 kJ/m²
ISO 179-1/1eU	23°C conditioned	80 kJ/m²
	-30°C d.a.m.	45 kJ/m²
Charpy notched impact strength	23°C d.a.m.	6 kJ/m²
ISO 179-1/1eA	23°C conditioned	10 kJ/m²
	-30°C d.a.m.	4 kJ/m²

Thermal Properties

Temperature of deflection under load HDT/A	1,8 MPa	200 °C
ISO 75		
Melting temperature	DSC, 10K/min	220 °C
ISO 11357-3		
Coefficient of linear thermal expansion	23°C to 80°C parallel	0,17 10⁻⁴/K
ISO 11359-1/2	23°C to 80°C transverse	0,66 10⁻⁴/K
Thermal conductivity		0,31 W/mK
DIN 52612		

Flammability

Flammability	1,6 mm Wall thickness	HB Class
UL 94		

General Properties

Density	23°C	1,19 g/cm³
ISO 1183		
Humidity absorption	70°C, 62% r.H.	2,7 %
ISO 1110		
Molding shrinkage	flow	0,3 %
ISO 294-4	transverse	0,7 %

Electrical Properties


Surface resistivity	d.a.m.	10⁵ Ω
IEC 62631-3-2	conditioned	10⁵ Ω

Rheological Properties

Flowability	2 mm Thickness	360 mm
AKRO		

Processing

The values mentioned are recommendations. We only recommend desiccant / dry air dryers or vacuum dryers. Too long a drying time and the resulting residual moisture content below the lower limit can lead to filling problems and surface defects. The specified drying time refers to closed and undamaged bagged material. When processing from previously opened bags or from octabins with polyolefin inliners, a longer drying time may be necessary. It is recommended to check the residual moisture content after the drying process.

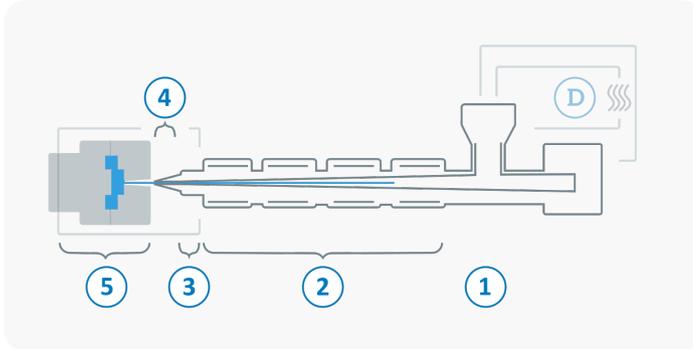

D	Drying time	0 - 4 h
	Drying temperature ($\tau \leq -30^\circ\text{C}$)	80 °C
	Processing moisture	0,02 - 0,1 %
1	Feed section	60 - 80 °C
2	Temperature Zone 1 - Zone 4	240 - 300 °C
3	Nozzle temperature	270 - 300 °C
4	Melt temperature	270 - 300 °C
5	Mold temperature	80 - 130 °C
→	Holding pressure, spec.	300 - 800 bar
←	Back pressure, spec.	50 - 150 bar
	Injection speed	medium to high
	Screw speed	8 - 15 m/min