

AKROMID®

B3 ICF 30 black (5119)

PA6 CF30

AKROMID® B3 ICF 30 black (5119) is a high performance Polyamide 6 with 30% carbon fiber reinforcement, offering medium stiffness and flexural strength. Compared to glass fiber-reinforced PA 6, it provides an optimized strength-to-weight ratio. Thanks to its low density and high mechanical durability, this material is ideal for load-bearing components in the automotive industry, such as lightweight structural parts, as well as for sports and leisure applications, including high-stress sports equipment and technical components.

Features

recycled content reduced density antistatic/conductive tribological modified Sports & leisure lightweight construction

Properties

Modulus

23.000 MPa

Strength

200 MPa

Impact

55 kJ/m²

Mechanical Properties

Tensile modulus

ISO 527-2

1 mm/min | d.a.m.

23000 MPa

1 mm/min | conditioned

11000 MPa

Tensile stress at break

ISO 527-2

5 mm/min | d.a.m.

200 MPa

5 mm/min | conditioned

125 MPa

Tensile strain at break

ISO 527-2

5 mm/min | d.a.m.

2 %

5 mm/min | conditioned

4 %

Flexural modulus

ISO 178

2 mm/min | d.a.m.

18000 MPa

2 mm/min | conditioned

11300 MPa

Flexural strength

ISO 178

2 mm/min | d.a.m.

290 MPa

2 mm/min | conditioned

200 MPa

Flexural strain at break

ISO 178

2 mm/min | d.a.m.

2 %

2 mm/min | conditioned

3,5 %

Charpy impact strength

ISO 179-1/1eU

23°C | d.a.m.

55 kJ/m²

23°C | conditioned

70 kJ/m²

-30°C | d.a.m.

50 kJ/m²

Charpy notched impact strength

ISO 179-1/1eA

23°C | d.a.m.

10 kJ/m²

23°C | conditioned

15 kJ/m²

-30°C | d.a.m.

7 kJ/m²

Thermal Properties

Temperature of deflection under load HDT/A

ISO 75

1,8 MPa

210 °C

Melting temperature

ISO 11357-3

DSC, 10K/min

220 °C

Coefficient of linear thermal expansion

ISO 11359-1/2

23°C to 80°C | parallel

0,06 10⁻⁴/K

23°C to 80°C | transverse

0,93 10⁻⁴/K

Flammability

Flammability

UL 94

1,6 mm Wall thickness

HB Class

Burning rate (<100 mm/min)

FMVSS 302

> 1 mm Thickness

+

General Properties

Density

ISO 1183

23°C

1,28 g/cm³

Humidity absorption

ISO 1110

70°C, 62% r.H.

2,0 - 2,2 %

Molding shrinkage

ISO 294-4

flow

0,1 - 0,3 %

transverse


0,4 - 0,6 %

Electrical Properties

Surface resistivity	d.a.m.	10³ Ω
IEC 62631-3-2	conditioned	10³ Ω

Processing

The values mentioned are recommendations. We only recommend desiccant / dry air dryers or vacuum dryers. Too long a drying time and the resulting residual moisture content below the lower limit can lead to filling problems and surface defects. The specified drying time refers to closed and undamaged bagged material. When processing from previously opened bags or from octabins with polyolefin inliners, a longer drying time may be necessary. It is recommended to check the residual moisture content after the drying process.

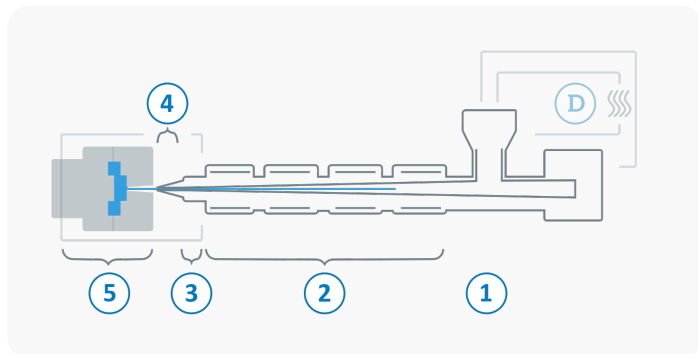

D	Drying time	0 - 4 h
	Drying temperature ($\tau \leq -30^{\circ}\text{C}$)	80 °C
	Processing moisture	0,02 - 0,1 %
1	Feed section	60 - 80 °C
2	Temperature Zone 1 - Zone 4	240 - 300 °C
3	Nozzle temperature	270 - 300 °C
4	Melt temperature	270 - 300 °C
5	Mold temperature	80 - 130 °C
→	Holding pressure, spec.	300 - 800 bar
←	Back pressure, spec.	50 - 150 bar
	Injection speed	medium to high
	Screw speed	8 - 15 m/min