

AKROMID®

A28 GF 40 1 natural (4919)

PA66 GF40

AKROMID® A3 GF 40 1 natural (2393) is a 40% glass fiber reinforced, easy flowing polyamide 6.6. It is characterised by a very high stiffness and strength. Furthermore, the material is heat stabilised and therefore perfectly suitable for technical parts and housings in industrial engineering and in the automotive industry. The material has a light inherent color.

Features

heat stabilised 130 easy flow

Properties

Modulus

13.000 MPa

Strength

245 MPa

Impact

95 kJ/m²

Mechanical Properties

Tensile modulus

ISO 527-2

1 mm/min | d.a.m.

13000 MPa

1 mm/min | conditioned

9800 MPa

Tensile stress at break

ISO 527-2

5 mm/min | d.a.m.

245 MPa

5 mm/min | conditioned

175 MPa

Tensile strain at break

ISO 527-2

5 mm/min | d.a.m.

3,0 %

5 mm/min | conditioned

4,0 %

Charpy impact strength

ISO 179-1/1eU

23°C | d.a.m.

95 kJ/m²

-30°C | d.a.m.

80 kJ/m²

Charpy notched impact strength

ISO 179-1/1eA

23°C | d.a.m.

17 kJ/m²

-30°C | d.a.m.

15 kJ/m²

Thermal Properties

Temperature of deflection under load HDT/A

ISO 75

1,8 MPa

260 °C

Temperature of deflection under load HDT/B ISO 75	0,45 MPa	260 °C
Temperature of deflection under load HDT/C ISO 75	8 MPa	225 °C
Melting temperature ISO 11357-3	DSC, 10K/min	262 °C

Flammability

Flammability UL 94	1,6 mm Wall thickness	HB Class
Burning rate (<100 mm/min) FMVSS 302	> 1 mm Thickness	+

General Properties


Density ISO 1183	23°C	1,46 g/cm³
Molding shrinkage ISO 294-4	flow transverse	0,4 % 0,8 %

Electrical Properties

Volume resistivity IEC 62631-3-1	d.a.m. conditioned	10¹³ Ω x cm 10¹⁰ Ω x cm
Surface resistivity IEC 62631-3-2	d.a.m. conditioned	10¹² Ω 10¹⁰ Ω
Comparative tracking index IEC 60112	Test liquid A	600 V

Processing

The values mentioned are recommendations. We only recommend desiccant / dry air dryers or vacuum dryers. Too long a drying time and the resulting residual moisture content below the lower limit can lead to filling problems and surface defects. The specified drying time refers to closed and undamaged bagged material. When processing from previously opened bags or from octabins with polyolefin inliners, a longer drying time may be necessary. It is recommended to check the residual moisture content after the drying process.

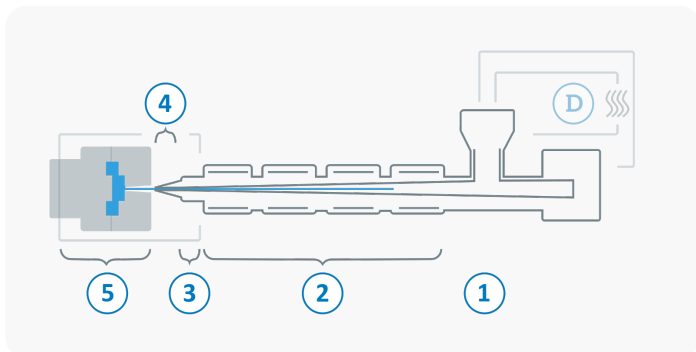

D	Drying time	0 - 4 h
	Drying temperature ($\tau \leq -30^{\circ}\text{C}$)	80 °C
	Processing moisture	0,02 - 0,1 %
1	Feed section	60 - 80 °C
2	Temperature Zone 1 - Zone 4	260 - 300 °C
3	Nozzle temperature	270 - 310 °C
4	Melt temperature	280 - 300 °C
5	Mold temperature	80 - 100 °C
→	Holding pressure, spec.	300 - 800 bar
←	Back pressure, spec.	50 - 150 bar
	Injection speed	medium to high
	Screw speed	8 - 15 m/min

Diagrams

