

AKROMID® A3 GF 20 1 natural (1261)


PA66 GF20

AKROMID® A3 GF 20 1 natural (1261) is a 20% glass fibre reinforced and heat stabilised polyamide 6.6 with medium stiffness and strength and light inherent color..

Features

heat stabilised 130

Properties

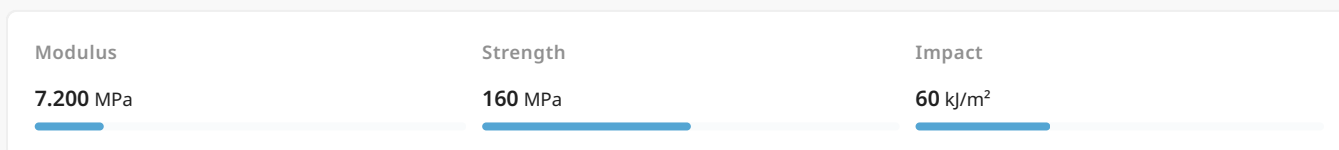

Mechanical Properties

Tensile modulus ISO 527-2	1 mm/min d.a.m.	7200 MPa
	1 mm/min conditioned	4600 MPa
Tensile stress at break ISO 527-2	5 mm/min d.a.m.	160 MPa
	5 mm/min conditioned	100 MPa
Tensile strain at break ISO 527-2	5 mm/min d.a.m.	3,5 %
	5 mm/min conditioned	8 %
Flexural modulus ISO 178	2 mm/min d.a.m.	7000 MPa
	2 mm/min conditioned	5000 MPa
Flexural strength ISO 178	2 mm/min d.a.m.	235 MPa
	2 mm/min conditioned	165 MPa
Charpy impact strength ISO 179-1/1eU	23°C d.a.m.	60 kJ/m²
	23°C conditioned	86 kJ/m²
	-30°C d.a.m.	48 kJ/m²
Charpy notched impact strength ISO 179-1/1eA	23°C d.a.m.	9 kJ/m²
	-30°C d.a.m.	8 kJ/m²

Ball indentation hardness	961N/30s d.a.m.	210 MPa
ISO 2039-1		

Thermal Properties

Temperature of deflection under load HDT/A	1,8 MPa	250 °C
ISO 75		

Temperature of deflection under load HDT/B	0,45 MPa	260 °C
ISO 75		

Melting temperature	DSC, 10K/min	262 °C
ISO 11357-3		

Temperature index for 50% loss of tensile strength	5.000 h	160 - 175 °C
IEC 60216	20.000 h	130 -150 °C

Flammability

Flammability	0,8 mm Wall thickness	HB Class
UL 94		

GWFI	1,6 mm Wall thickness	650 °C
IEC 60695-2-12		

Burning rate (<100 mm/min)	> 1 mm Thickness	+
FMVSS 302		

General Properties

Density	23°C	1,28 g/cm ³
ISO 1183		

Humidity absorption	70°C, 62% r.H.	2,3 - 2,5 %
ISO 1110		

Water absorption	23°C, saturated	6,7 - 7,2 %
ISO 62		


Molding shrinkage	flow	0,3 %
ISO 294-4	transverse	1,3 %

Electrical Properties

Volume resistivity IEC 62631-3-1	d.a.m.	$10^{13} \Omega \times \text{cm}$
Surface resistivity IEC 62631-3-2	d.a.m.	$10^{12} \Omega$
Comparative tracking index IEC 60112	Test liquid A	600 V

Processing

The values mentioned are recommendations. We only recommend desiccant / dry air dryers or vacuum dryers. Too long a drying time and the resulting residual moisture content below the lower limit can lead to filling problems and surface defects. The specified drying time refers to closed and undamaged bagged material. When processing from previously opened bags or from octabins with polyolefin inliners, a longer drying time may be necessary. It is recommended to check the residual moisture content after the drying process.

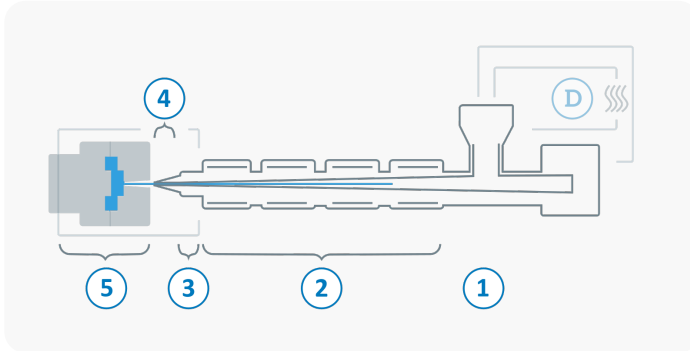

Ⓓ	Drying time	0 - 4 h
	Drying temperature ($\tau \leq -30^{\circ}\text{C}$)	80 °C
	Processing moisture	0,02 - 0,1 %
①	Feed section	60 - 80 °C
②	Temperature Zone 1 - Zone 4	260 - 300 °C
③	Nozzle temperature	270 - 310 °C
④	Melt temperature	280 - 300 °C
⑤	Mold temperature	80 - 100 °C
→	Holding pressure, spec.	300 - 800 bar
←	Back pressure, spec.	50 - 150 bar
	Injection speed	medium to high
	Screw speed	8 - 15 m/min