

AKROMID®

A3 GF 50 1 EN black (5737)

PA66 GF50

AKROMID® A3 GF 50 1 EN black (5737) is a 50% glass fiber reinforced, electrically neutral polyamide 6.6. It is characterised by a very high stiffness and strength. Furthermore, the material is heat stabilised and therefore perfectly suitable for technical parts in industrial engineering and in the automotive industry, e.g. gearbox components.

Features

heat stabilised 130

electrically neutral

Properties

Modulus

16.700 MPa

Strength

250 MPa

Impact

105 kJ/m²

Mechanical Properties

Tensile modulus

ISO 527-2

1 mm/min | d.a.m.

16700 MPa

1 mm/min | conditioned

12600 MPa

Tensile stress at break

ISO 527-2

5 mm/min | d.a.m.

250 MPa

5 mm/min | conditioned

180 MPa

Tensile strain at break

ISO 527-2

5 mm/min | d.a.m.

2,5 %

5 mm/min | conditioned

3,5 %

Flexural modulus

ISO 178

2 mm/min | d.a.m.

15200 MPa

2 mm/min | conditioned

13600 MPa

Flexural strength

ISO 178

2 mm/min | d.a.m.

380 MPa

2 mm/min | conditioned

310 MPa

Charpy impact strength

ISO 179-1/1eU

23°C | d.a.m.

105 kJ/m²

23°C | conditioned

110 kJ/m²

-30°C | d.a.m.

105 kJ/m²

Charpy notched impact strength

ISO 179-1/1eA

23°C | d.a.m.

19 kJ/m²

23°C | conditioned

23 kJ/m²

-30°C | d.a.m.

16 kJ/m²

Ball indentation hardness	961N/30s d.a.m.	290 MPa
ISO 2039-1		

Thermal Properties

Temperature of deflection under load HDT/A	1,8 MPa	260 °C
ISO 75		

Temperature of deflection under load HDT/B	0,45 MPa	260 °C
ISO 75		

Temperature of deflection under load HDT/C	8 MPa	235 °C
ISO 75		

Melting temperature	DSC, 10K/min	262 °C
ISO 11357-3		

Coefficient of linear thermal expansion	23°C to 80°C parallel	0,17 10⁻⁴/K
ISO 11359-1/2	23°C to 80°C transverse	0,88 10⁻⁴/K

Temperature index for 50% loss of tensile strength	5.000 h	160 - 175 °C
IEC 60216	20.000 h	130 - 150 °C

Flammability

Flammability	1,6 mm Wall thickness	HB Class
UL 94		

GWFI	1,6 mm Wall thickness	650 °C
IEC 60695-2-12		

General Properties

Density	23°C	1,57 g/cm³
ISO 1183		

Humidity absorption	70°C, 62% r.H.	1,3 - 1,5 %
ISO 1110		

Water absorption	23°C, saturated	3,7 - 4,3 %
ISO 62		


Molding shrinkage	flow	0,1 - 0,3 %
ISO 294-4	transverse	0,3 - 0,5 %

Electrical Properties

Volume resistivity IEC 62631-3-1	d.a.m. conditioned	$10^{13} \Omega \times \text{cm}$ $10^{10} \Omega \times \text{cm}$
Surface resistivity IEC 62631-3-2	d.a.m. conditioned	$10^{12} \Omega$ $10^{10} \Omega$
Comparative tracking index IEC 60112	Test liquid A	600 V

Processing

The values mentioned are recommendations. We only recommend desiccant / dry air dryers or vacuum dryers. Too long a drying time and the resulting residual moisture content below the lower limit can lead to filling problems and surface defects. The specified drying time refers to closed and undamaged bagged material. When processing from previously opened bags or from octabins with polyolefin inliners, a longer drying time may be necessary. It is recommended to check the residual moisture content after the drying process.

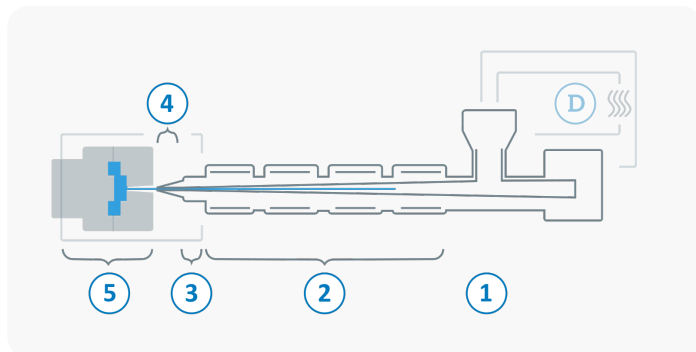

D	Drying time	0 - 4 h
	Drying temperature ($\tau \leq -30^{\circ}\text{C}$)	80 °C
	Processing moisture	0,02 - 0,1 %
1	Feed section	60 - 80 °C
2	Temperature Zone 1 - Zone 4	260 - 300 °C
3	Nozzle temperature	270 - 310 °C
4	Melt temperature	280 - 300 °C
5	Mold temperature	80 - 100 °C
→	Holding pressure, spec.	300 - 800 bar
←	Back pressure, spec.	50 - 150 bar
	Injection speed	medium to high
	Screw speed	8 - 15 m/min

Diagrams

