

AKROMID®

C3 GF 30 1 black (4363)

PA66+PA6 GF30

AKROMID® C3 GF 30 1 black (4363) is a 30% glass fiber reinforced, heat stabilised polyamide 6.6/6 blend. It is characterised by high stiffness and strength as well as by higher temperature resistance compared to standard PA6.6/6-blends. It is therefore perfectly suitable for parts in industrial engineering and in the automotive industry, which are used at elevated temperatures.

Features

heat stabilised 130

Properties

Modulus

9.300 MPa

Strength

185 MPa

Impact

75 kJ/m²

Mechanical Properties

Tensile modulus

ISO 527-2

1 mm/min | d.a.m.

9300 MPa

1 mm/min | conditioned

6500 MPa

Tensile stress at break

ISO 527-2

5 mm/min | d.a.m.

185 MPa

5 mm/min | conditioned

120 MPa

Tensile strain at break

ISO 527-2

5 mm/min | d.a.m.

3 %

5 mm/min | conditioned

5,5 %

Flexural modulus

ISO 178

2 mm/min | d.a.m.

9200 MPa

Flexural strength

ISO 178

2 mm/min | d.a.m.

275 MPa

Charpy impact strength

ISO 179-1/1eU

23°C | d.a.m.

75 kJ/m²

23°C | conditioned

90 kJ/m²

-30°C | d.a.m.

60 kJ/m²

Charpy notched impact strength	23°C d.a.m.	11 kJ/m²
ISO 179-1/1eA	23°C conditioned	14 kJ/m²
	-30°C d.a.m.	10 kJ/m²

Thermal Properties

Temperature of deflection under load HDT/A	1,8 MPa	247 °C
ISO 75		
Temperature of deflection under load HDT/B	0,45 MPa	257 °C
ISO 75		
Temperature of deflection under load HDT/C	8 MPa	204 °C
ISO 75		
Melting temperature	DSC, 10K/min	260 °C
ISO 11357-3		
Coefficient of linear thermal expansion	23°C to 80°C parallel	0,19 10⁻⁴/K
ISO 11359-1/2	23°C to 80°C transverse	1,04 10⁻⁴/K
Temperature index for 50% loss of tensile strength	5.000 h	160 - 175 °C
IEC 60216	20.000 h	130 - 150 °C

Flammability

Flammability	0,8 mm Wall thickness	HB Class
UL 94		
Burning rate (<100 mm/min)	> 1 mm Thickness	+
FMVSS 302		

General Properties

Density	23°C	1,36 g/cm³
ISO 1183		
Humidity absorption	70°C, 62% r.H.	1,8 - 2,0 %
ISO 1110		
Molding shrinkage	flow	0,1 - 0,3 %
ISO 294-4	transverse	0,6 - 0,8 %

Electrical Properties


Volume resistivity	d.a.m.	$10^{13} \Omega \times \text{cm}$
IEC 62631-3-1	conditioned	$10^{10} \Omega \times \text{cm}$
Surface resistivity	d.a.m.	$10^{12} \Omega$
IEC 62631-3-2	conditioned	$10^{10} \Omega$
Comparative tracking index	Test liquid A	600 V
IEC 60112		

Rheological Properties

MVR	275°C/5kg	$45 \text{ cm}^3/10 \text{ min}$
ISO 1133		

Processing

The values mentioned are recommendations. We only recommend desiccant / dry air dryers or vacuum dryers. Too long a drying time and the resulting residual moisture content below the lower limit can lead to filling problems and surface defects. The specified drying time refers to closed and undamaged bagged material. When processing from previously opened bags or from octabins with polyolefin inliners, a longer drying time may be necessary. It is recommended to check the residual moisture content after the drying process.

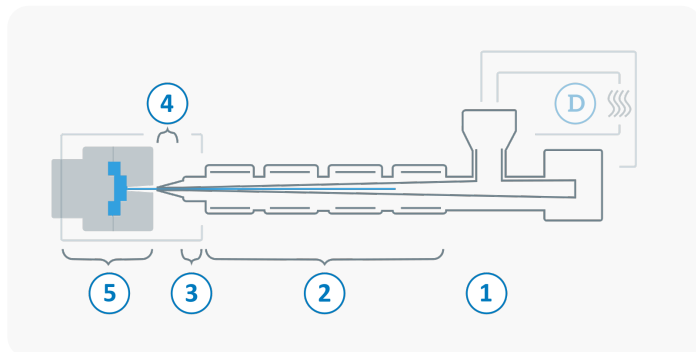

D	Drying time	0 - 4 h
	Drying temperature ($\tau \leq -30^{\circ}\text{C}$)	80 °C
	Processing moisture	0,02 - 0,1 %
1	Feed section	60 - 80 °C
2	Temperature Zone 1 - Zone 4	260 - 300 °C
3	Nozzle temperature	270 - 300 °C
4	Melt temperature	270 - 300 °C
5	Mold temperature	80 - 100 °C
→	Holding pressure, spec.	300 - 800 bar
←	Back pressure, spec.	50 - 150 bar
	Injection speed	medium to high
	Screw speed	8 - 15 m/min