

AKROMID®

NEXT C3 GF 25 1 FR black (7246BMBCI)

PA66+PA6 GF25 FR(40)

AKROMID® C3 GF 25 1 FR black (7246BMBCI) is a 25 % glass fiber reinforced, flame retardant and heat stabilised PA6/6.6 blend, colored in black. The flame retardant system is free of halogens, red phosphorus, PFAS and melamine. Due to its good flowability, an improved surface quality is achieved. This grade is also suitable for applications with high strength requirements in the automotive and E&E markets. The material is certified according to ISCC PLUS. 93 % of the fossil raw materials required for manufacturing this product were replaced by sustainable biomass-balanced PA and FR (Allocation factor).

Features

biomass balanced heat stabilised 130 flame retardant
surface modified easy flow E&E

Regulatory



Properties

Modulus

9.100 MPa

Strength

137 MPa

Impact

66 kJ/m²

Sustainability

Allocation factor

only valid for ISCC PLUS/REDcert² certified products

93 %

Mechanical Properties

Tensile modulus

ISO 527-2

1 mm/min | d.a.m.

9100 MPa

1 mm/min | conditioned

6300 MPa

Tensile stress at break

ISO 527-2

5 mm/min | d.a.m.

137 MPa

5 mm/min | conditioned

95 MPa

Tensile strain at break

ISO 527-2

5 mm/min | d.a.m.

3,0 %

5 mm/min | conditioned

5,5 %

Flexural modulus	2 mm/min d.a.m.	8800 MPa
ISO 178	2 mm/min conditioned	6000 MPa
Flexural strength	2 mm/min d.a.m.	225 MPa
ISO 178	2 mm/min conditioned	160 MPa
Flexural strain at break	2 mm/min d.a.m.	3,5 %
ISO 178	2 mm/min conditioned	5 %
Charpy impact strength	23°C d.a.m.	66 kJ/m²
ISO 179-1/1eU	23°C conditioned	75 kJ/m²
Charpy notched impact strength	23°C d.a.m.	11 kJ/m²
ISO 179-1/1eA	23°C conditioned	15 kJ/m²

Thermal Properties

RTI electrical	0,4mm Wall thickness	140 °C
UL 746B	0,8mm Wall thickness	150 °C
	1,6mm Wall thickness	150 °C
	3,2mm Wall thickness	120 °C
RTI impact	0,4mm Wall thickness	125 °C
UL 746B	0,8mm Wall thickness	125 °C
	1,6mm Wall thickness	125 °C
	3,2mm Wall thickness	125 °C
RTI strength	0,4mm Wall thickness	135 °C
UL 746B	0,8mm Wall thickness	140 °C
	1,6mm Wall thickness	140 °C
	3,2mm Wall thickness	140 °C
Temperature of deflection under load HDT/A	1,8 MPa	225 °C
ISO 75		
Temperature of deflection under load HDT/B	0,45 MPa	251 °C
ISO 75		
Temperature of deflection under load HDT/C	8 MPa	168 °C
ISO 75		
Melting temperature	DSC, 10K/min	262 °C
ISO 11357-3		
Ball pressure test		> 210 °C
IEC 60695-10-2		

Temperature index for 50% loss of tensile strength	5.000 h	155 °C
IEC 60216	20.000 h	130 °C

Flammability

Flammability	0,4 mm Wall thickness	V-0 Class
UL 94	0,8 mm Wall thickness	V-0 Class
	1,6 mm Wall thickness	V-0 Class
	3,2 mm Wall thickness	V-0 Class

Burning rate 5V	1,6 mm Wall thickness	5VA Class
UL 94	3,2 mm Wall thickness	5VA Class

GWFI	0,4 mm Wall thickness	960 °C
IEC 60695-2-12	0,8 mm Wall thickness	960 °C
	1,6 mm Wall thickness	960 °C
	3,2 mm Wall thickness	960 °C

GWIT	0,4 mm Wall thickness	750 °C
IEC 60695-2-13	0,8 mm Wall thickness	750 °C
	1,6 mm Wall thickness	750 °C
	3,2 mm Wall thickness	750 °C

HWI	0,4 mm Wall thickness	0 PLC
UL 746A	0,8 mm Wall thickness	0 PLC
	1,6 mm Wall thickness	0 PLC
	3,2 mm Wall thickness	0 PLC

HAI	0,4 mm Wall thickness	0 PLC
UL 746A	0,8 mm Wall thickness	0 PLC
	1,6 mm Wall thickness	0 PLC
	3,2 mm Wall thickness	0 PLC

Burning rate (<100 mm/min)	> 1 mm Thickness	+
FMVSS 302		

General Properties

Density	23°C	1,37 g/cm³
ISO 1183		

Humidity absorption	70°C, 62% r.H.	1,8 - 2,0 %
ISO 1110		

Molding shrinkage	flow	0,1 - 0,3 %
ISO 294-4	transverse	0,5 - 0,7 %

Electrical Properties

Comparative tracking index	Test liquid A	600 V
IEC 60112		

Comparative tracking index		0 PLC
ASTM D3638		

Dielectric strength	3 mm	121 kV/mm
IEC 60243		

Inclined-Plane Tracking, IPT		1 kV
ASTM D2303-13		

High voltage arc tracking rate (HVTR)		1 PLC
UL 746A		


High Volt, Low Current Arc Resistance		6 PLC
ASTM D495		

Rheological Properties

Flowability	2 mm Thickness	480 mm
AKRO		

Processing

The values mentioned are recommendations. We only recommend desiccant / dry air dryers or vacuum dryers. Too long a drying time and the resulting residual moisture content below the lower limit can lead to filling problems and surface defects. The specified drying time refers to closed and undamaged bagged material. When processing from previously opened bags or from octabins with polyolefin inliners, a longer drying time may be necessary. It is recommended to check the residual moisture content after the drying process.

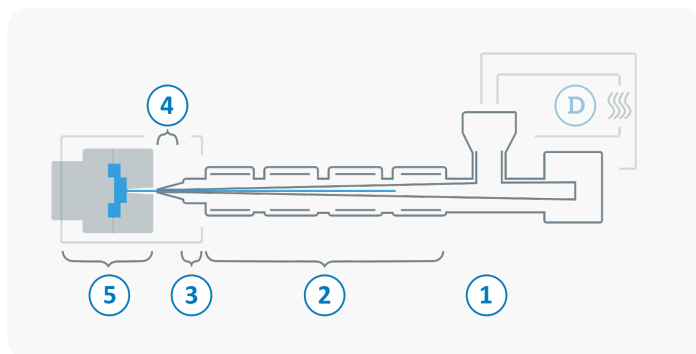

D	Drying time	2 - 4 h
	Drying temperature ($\tau \leq -30^{\circ}\text{C}$)	80 °C
	Processing moisture	0,02 - 0,08 %
1	Feed section	60 - 80 °C
2	Temperature Zone 1 - Zone 4	260 - 290 °C
3	Nozzle temperature	260 - 300 °C
4	Melt temperature	270 - 290 °C
5	Mold temperature	60 - 100 °C
→	Holding pressure, spec.	300 - 800 bar
←	Back pressure, spec.	30 - 100 bar
	Injection speed	medium
	Screw speed	5 - 10 m/min