

AKROMID®

NEXT C3 GF 30 1 FR orange (7855BMBCI)

PA66+PA6 GF30 FR(40)

AKROMID® C3 GF 30 1 FR orange (7855BMBCI) is a 30 % glass fiber reinforced, flame retardant and heat stabilised PA6/6.6 blend, colored in orange similar to RAL 2003. The flame retardant system is free of halogens, red phosphorus, PFAS and melamine. Due to its good flowability, an improved surface quality is achieved. This grade is also suitable E&E applications (e.g. control cabinets) as well as for railroad applications and meets the requirements for public transportation (EN 45545-2 R22/23/24/26 HL3). The material is certified according to ISCC PLUS. XX % of the fossil raw materials required for manufacturing this product were replaced by sustainable biomass-balanced PA (Allocation factor).

Features

biomass balanced heat stabilised 130 electrically neutral

flame retardant easy flow E&E public transportation

Sports & leisure E-Mobility

Regulatory

EN45545-2



Properties

Modulus

10.600 MPa

Strength

135 MPa

Impact

65 kJ/m²

Mechanical Properties

Tensile modulus

ISO 527-2

1 mm/min | d.a.m.

10600 MPa

Tensile stress at break

ISO 527-2

5 mm/min | d.a.m.

135 MPa

Tensile strain at break

ISO 527-2

5 mm/min | d.a.m.

2,5 %

Charpy impact strength

ISO 179-1/1eU

23°C | d.a.m.

65 kJ/m²

Charpy notched impact strength

ISO 179-1/1eA

23°C | d.a.m.

10 kJ/m²

Thermal Properties

RTI electrical UL 746B	0,4mm Wall thickness	140 °C
	0,8mm Wall thickness	150 °C
	1,6mm Wall thickness	150 °C
	3,2mm Wall thickness	125 °C
RTI impact UL 746B	0,4mm Wall thickness	120 °C
	0,8mm Wall thickness	125 °C
	1,6mm Wall thickness	125 °C
	3,2mm Wall thickness	125 °C
RTI strength UL 746B	0,4mm Wall thickness	135 °C
	0,8mm Wall thickness	140 °C
	1,6mm Wall thickness	140 °C
	3,2mm Wall thickness	140 °C
Melting temperature ISO 11357-3	DSC, 10K/min	262 °C

Flammability

Flammability UL 94	0,4 mm Wall thickness	V-0 Class
	0,8 mm Wall thickness	V-0 Class
	1,6 mm Wall thickness	V-0 Class
	3,2 mm Wall thickness	V-0 Class
GWFI IEC 60695-2-12	0,4 mm Wall thickness	960 °C
	0,8 mm Wall thickness	960 °C
	1,6 mm Wall thickness	960 °C
	3,2 mm Wall thickness	960 °C
GWIT IEC 60695-2-13	0,4 mm Wall thickness	725 °C
	0,8 mm Wall thickness	725 °C
	1,6 mm Wall thickness	725 °C
	3,2 mm Wall thickness	775 °C
HWI UL 746A	0,4 mm Wall thickness	0 PLC
	0,8 mm Wall thickness	0 PLC
	1,6 mm Wall thickness	0 PLC
	3,2 mm Wall thickness	0 PLC
HAI UL 746A	0,8 mm Wall thickness	0 PLC
	1,6 mm Wall thickness	0 PLC
	3,2 mm Wall thickness	0 PLC

Protection Train

EN 45545-2

R22/R23/R24/R26 HL3

General Properties

Density

ISO 1183

23°C

1,43 g/cm³

Electrical Properties

Comparative tracking index

IEC 60112

Test liquid A

600 V

Dielectric strength

IEC 60243

1 mm

24,6 kV/mm

Inclined-Plane Tracking, IPT

ASTM D2303-13

1 kV

High voltage arc tracking rate (HVTR)

UL 746A

1 PLC


High Volt, Low Current Arc Resistance

ASTM D495

6 PLC

Processing

The values mentioned are recommendations. We only recommend desiccant / dry air dryers or vacuum dryers. Too long a drying time and the resulting residual moisture content below the lower limit can lead to filling problems and surface defects. The specified drying time refers to closed and undamaged bagged material. When processing from previously opened bags or from octabins with polyolefin inliners, a longer drying time may be necessary. It is recommended to check the residual moisture content after the drying process.

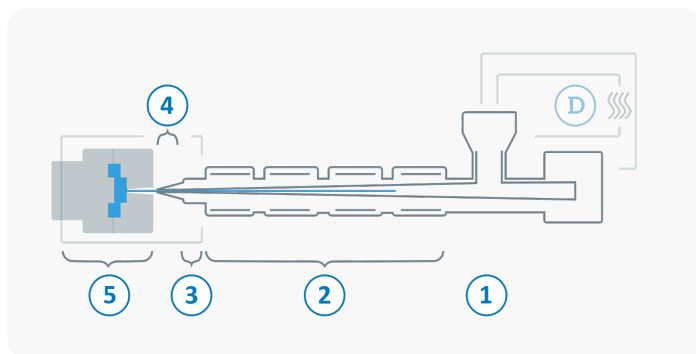

D	Drying time	2 - 4 h
	Drying temperature ($\tau \leq -30^{\circ}\text{C}$)	80 °C
	Processing moisture	0,02 - 0,08 %
1	Feed section	60 - 80 °C
2	Temperature Zone 1 - Zone 4	260 - 290 °C
3	Nozzle temperature	260 - 300 °C
4	Melt temperature	270 - 290 °C
5	Mold temperature	60 - 100 °C
→	Holding pressure, spec.	300 - 800 bar
←	Back pressure, spec.	30 - 100 bar
	Injection speed	medium
	Screw speed	5 - 10 m/min