

AKROTEK® PRELIMINARY

PK-VM GF 15 black (8686)

PK GF15

AKROTEK® PK-VM GF 15 black (8686) is a 15% glass fibre reinforced Polyketone with average stiffness and strength. Due to its very good media resistance, the material is suitable for use in applications that carry cooling water. This type was developed as the successor to PK-VM GF 15 schwarz (5091) in order to meet the requirements for a larger processing window during processing.

Features

hydrolysis / chemically stabilised

Properties

Modulus

4.500 MPa

Strength

90 MPa

Impact

50 kJ/m²

Mechanical Properties

Tensile modulus

ISO 527-2

1 mm/min | d.a.m.

4500 MPa

Tensile stress at break

ISO 527-2

5 mm/min | d.a.m.

90 MPa

Tensile strain at break

ISO 527-2

5 mm/min | d.a.m.

4 %

Charpy impact strength

ISO 179-1/1eU

23°C | d.a.m.

50 kJ/m²

Charpy notched impact strength

ISO 179-1/1eA

23°C | d.a.m.

10 kJ/m²

Thermal Properties

Temperature of deflection under load HDT/A

ISO 75

1,8 MPa

210 °C

Temperature of deflection under load HDT/B	0,45 MPa	220 °C
ISO 75		

Melting temperature	DSC, 10K/min	220 °C
ISO 11357-3		

Flammability

Flammability	1,6 mm Wall thickness	HB Class
UL 94		

Burning rate (<100 mm/min)	> 1 mm Thickness	+
FMVSS 302		

General Properties


Density	23°C	1,35 g/cm³
ISO 1183		

Humidity absorption	70°C, 62% r.H.	0,7 - 0,8 %
ISO 1110		

Molding shrinkage	flow	0,5 - 0,7 %
ISO 294-4	transverse	1,1 - 1,3 %

Processing

The values mentioned are recommendations. We only recommend desiccant / dry air dryers or vacuum dryers. Too long a drying time and the resulting residual moisture content below the lower limit can lead to filling problems and surface defects. The specified drying time refers to closed and undamaged bagged material. When processing from previously opened bags or from octabins with polyolefin inliners, a longer drying time may be necessary. It is recommended to check the residual moisture content after the drying process.

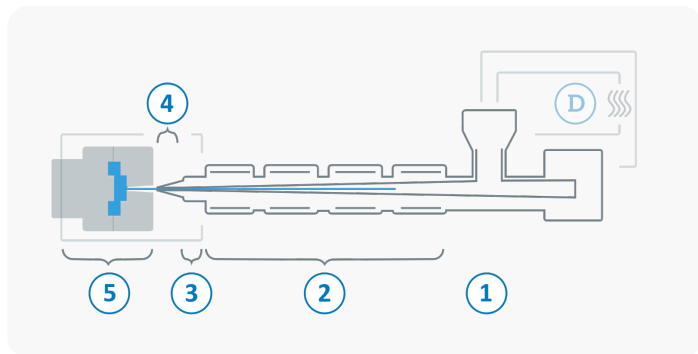

D	Drying time	0 - 4 h
	Drying temperature ($\tau \leq -30^{\circ}\text{C}$)	80 °C
	Processing moisture	0,02 - 0,1 %
1	Feed section	60 - 80 °C
2	Temperature Zone 1 - Zone 4	220 - 260 °C
3	Nozzle temperature	230 - 260 °C
4	Melt temperature	230 - 260 °C
5	Mold temperature	60 - 120 °C
→	Holding pressure, spec.	300 - 800 bar
←	Back pressure, spec.	30 - 70 bar
	Injection speed	medium to high
	Screw speed	8 - 15 m/min