

AKROTEK® PRELIMINARY

PK-VM GF 5 8 black (7322)

PK GF5

AKROTEK® PK-VM GF 5 8 black (7322) is a 5% glass fibre reinforced polyketone with high stiffness and strength. PK is characterized by its outstanding media resistance, which qualifies it to be used for components that are in contact with chemicals. The material corresponds to the European food guideline EU 10/2011 and to the American FDA 21 CFR. This grade is suitable for parts of kitchen and household appliances.

Features

hydrolysis / chemically stabilised household appliances

Properties

Modulus

2.300 MPa

Strength

65 MPa

Impact

55 kJ/m²

Mechanical Properties

Tensile modulus

ISO 527-2

1 mm/min | d.a.m.

2300 MPa

1 mm/min | conditioned

2300 MPa

Tensile stress at break

ISO 527-2

5 mm/min | d.a.m.

65 MPa

5 mm/min | conditioned

60 MPa

Tensile strain at break

ISO 527-2

5 mm/min | d.a.m.

> 10 %

5 mm/min | conditioned

> 10 %

Charpy impact strength

ISO 179-1/1eU

23°C | d.a.m.

55 kJ/m²

23°C | conditioned

55 kJ/m²

Charpy notched impact strength

ISO 179-1/1eA

23°C | d.a.m.

10 kJ/m²

23°C | conditioned

10 kJ/m²

Thermal Properties

Melting temperature

ISO 11357-3

DSC, 10K/min

220 °C

Flammability

Burning rate 5V

UL 94

1,6 mm Wall thickness

HB Class

Burning rate (<100 mm/min)

FMVSS 302

> 1 mm Thickness

+

General Properties

Density

ISO 1183

23°C

1,28 g/cm³

Humidity absorption

ISO 1110

70°C, 62% r.H.

0,8 - 0,9 %

Molding shrinkage

ISO 294-4

flow


1,2 - 1,4 %

transverse

1,6 - 1,8 %

Processing

The values mentioned are recommendations. We only recommend desiccant / dry air dryers or vacuum dryers. Too long a drying time and the resulting residual moisture content below the lower limit can lead to filling problems and surface defects. The specified drying time refers to closed and undamaged bagged material. When processing from previously opened bags or from octabins with polyolefin inliners, a longer drying time may be necessary. It is recommended to check the residual moisture content after the drying process.

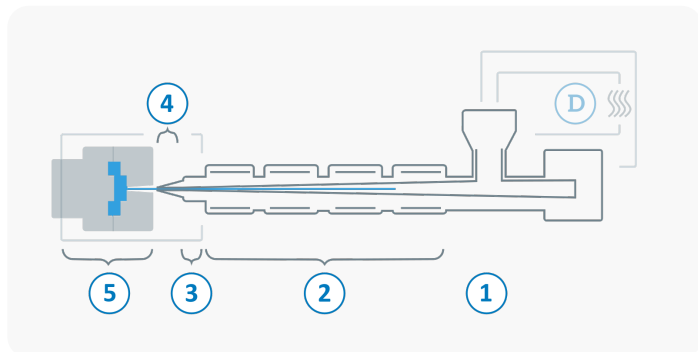

D	Drying time	0 - 4 h
	Drying temperature ($\tau \leq -30^{\circ}\text{C}$)	80 °C
	Processing moisture	0,02 - 0,1 %
1	Feed section	60 - 80 °C
2	Temperature Zone 1 - Zone 4	220 - 260 °C
3	Nozzle temperature	230 - 260 °C
4	Melt temperature	230 - 260 °C
5	Mold temperature	60 - 120 °C
→	Holding pressure, spec.	300 - 800 bar
←	Back pressure, spec.	30 - 70 bar
	Injection speed	medium to high
	Screw speed	8 - 15 m/min