

AKROMID®

T5 GF 40 8 black (7963)

PPA GF40

AKROMID® T5 GF 40 8 black (7963) is a 40% glass fibre reinforced polyphthalamide with very high rigidity and strength, as well as high temperature and chemical resistance. This aromatic PPA keeps mechanical performance even at elevated temperatures as well as moisture pick-up. The material corresponds to the European food guideline EU 10/2011 and to the American FDA 21 CFR except alcoholic beverages containing more than 8 percent alcohol. This grade is suitable for parts of kitchen and household appliances.

Regulatory



Properties

Modulus

15.000 MPa

Strength

235 MPa

Impact

80 kJ/m²

Mechanical Properties

Tensile modulus

ISO 527-2

1 mm/min | d.a.m.

15000 MPa

1 mm/min | conditioned

15000 MPa

Tensile stress at break

ISO 527-2

5 mm/min | d.a.m.

235 MPa

5 mm/min | conditioned

230 MPa

Tensile strain at break

ISO 527-2

5 mm/min | d.a.m.

2,4 %

5 mm/min | conditioned

2,4 %

Flexural modulus

ISO 178

2 mm/min | d.a.m.

15600 MPa

2 mm/min | conditioned

15000 MPa

Charpy impact strength

ISO 179-1/1eU

23°C | d.a.m.

80 kJ/m²

23°C | conditioned

80 kJ/m²

Charpy notched impact strength

ISO 179-1/1eA

23°C | d.a.m.

11 kJ/m²

23°C | conditioned

11 kJ/m²

Thermal Properties

Temperature of deflection under load HDT/A ISO 75	1,8 MPa	280 °C
Melting temperature ISO 11357-3	DSC, 10K/min	325 °C

Flammability

Flammability UL 94	1,6 mm Wall thickness	HB Class
------------------------------	-----------------------	-----------------

General Properties


Density ISO 1183	23°C	1,5 g/cm³
Molding shrinkage ISO 294-4	flow transverse	0,1 - 0,3 % 0,5 - 0,7 %

Rheological Properties

Flowability AKRO	1 mm Thickness 2 mm Thickness	120 mm 300 mm
----------------------------	----------------------------------	--------------------------

Processing

The values mentioned are recommendations. We only recommend desiccant / dry air dryers or vacuum dryers. Too long a drying time and the resulting residual moisture content below the lower limit can lead to filling problems and surface defects. The specified drying time refers to closed and undamaged bagged material. When processing from previously opened bags or from octabins with polyolefin inliners, a longer drying time may be necessary. It is recommended to check the residual moisture content after the drying process.

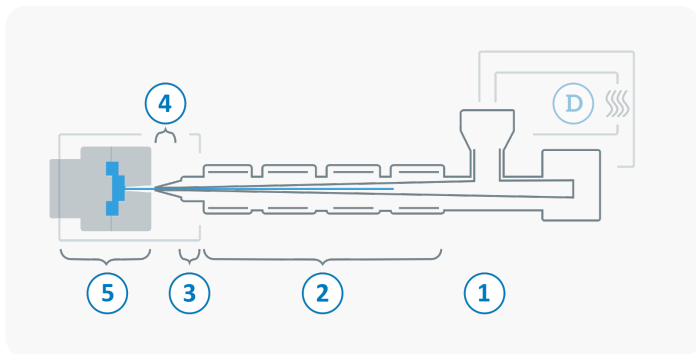

D	Drying time	0 - 4 h
	Drying temperature ($\tau \leq -30^{\circ}\text{C}$)	120 °C
	Processing moisture	0,02 - 0,1 %
1	Feed section	60 - 90 °C
2	Temperature Zone 1 - Zone 4	320 - 350 °C
3	Nozzle temperature	330 - 350 °C
4	Melt temperature	330 - 350 °C
5	Mold temperature	120 - 160 °C
→	Holding pressure, spec.	300 - 800 bar
←	Back pressure, spec.	50 - 150 bar
	Injection speed	medium to high
	Screw speed	8 - 15 m/min