

AKROMID®

T5 GF 40 black (6486)

PPA GF40

AKROMID® T5 GF 40 black (6486) is a 40% glass fibre reinforced polyphthalamide. It is characterised by its high stiffness and strength, even at elevated temperatures up to 120°C. Due to its low moisture absorption, the mechanical properties remain nearly unchanged even in conditioned state. Not only the good creep resistance, but also the hydrolysis and chemical resistance complement the property profile and make it the material of your choice for under the hood applications and connectors with special strength requirements.

Features

heat stabilised 160 hydrolysis / chemically stabilised reduced moisture metal substitution

Properties

Modulus

14.500 MPa

Strength

245 MPa

Impact

80 kJ/m²

Mechanical Properties

Tensile modulus

ISO 527-2

1 mm/min | d.a.m.

14500 MPa

1 mm/min | conditioned

14500 MPa

Tensile stress at break

ISO 527-2

5 mm/min | d.a.m.

245 MPa

5 mm/min | conditioned

230 MPa

Tensile strain at break

ISO 527-2

5 mm/min | d.a.m.

2,4 %

5 mm/min | conditioned

2,4 %

Flexural modulus

ISO 178

2 mm/min | d.a.m.

15600 MPa

2 mm/min | conditioned

15000 MPa

Flexural strength

ISO 178

2 mm/min | d.a.m.

380 MPa

2 mm/min | conditioned

350 MPa

Flexural strain at break

ISO 178

2 mm/min | d.a.m.

2,8 %

2 mm/min | conditioned

2,8 %

Charpy impact strength

ISO 179-1/1eU

23°C | d.a.m.

80 kJ/m²

23°C | conditioned

80 kJ/m²

-30°C | d.a.m.

73 kJ/m²

-30°C | conditioned

73 kJ/m²

Charpy notched impact strength

ISO 179-1/1eA

23°C | d.a.m.

11 kJ/m²

23°C | conditioned

11 kJ/m²

-30°C | d.a.m.

10 kJ/m²

-30°C | conditioned

10 kJ/m²

Thermal Properties

Temperature of deflection under load HDT/A

ISO 75

1,8 MPa

280 °C

Temperature of deflection under load HDT/C

ISO 75

8 MPa

220 °C

Glass transition temperature

ISO 11357-2

DSC, 2nd heating

135 °C

Melting temperature

ISO 11357-3

DSC, 10K/min

325 °C

Temperature index for 50% loss of tensile strength

IEC 60216

20.000 h

155 °C

Flammability

Flammability

UL 94

1,6 mm Wall thickness

HB Class

Burning rate (<100 mm/min)

FMVSS 302

> 1 mm Thickness

+

General Properties

Density

ISO 1183

23°C

1,5 g/cm³

Molding shrinkage

ISO 294-4

flow

0,2 %

transverse

0,6 %

Electrical Properties


Comparative tracking index	Test liquid A	600 V
IEC 60112		

Rheological Properties

Flowability	1 mm Thickness	120 mm
AKRO	2 mm Thickness	300 mm

Processing

The values mentioned are recommendations. We only recommend desiccant / dry air dryers or vacuum dryers. Too long a drying time and the resulting residual moisture content below the lower limit can lead to filling problems and surface defects. The specified drying time refers to closed and undamaged bagged material. When processing from previously opened bags or from octabins with polyolefin inliners, a longer drying time may be necessary. It is recommended to check the residual moisture content after the drying process.

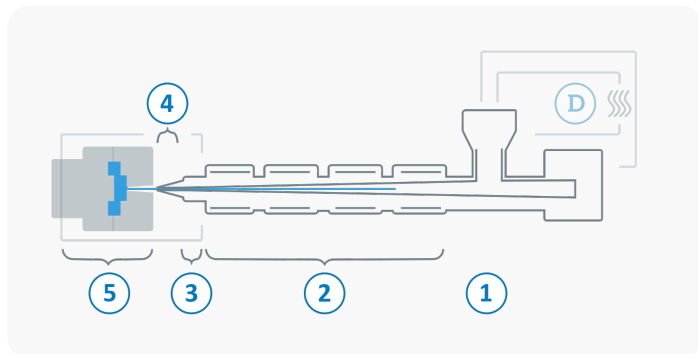

(D) Drying time	0 - 4 h
Drying temperature ($\tau \leq -30^{\circ}\text{C}$)	120 °C
Processing moisture	0,02 - 0,1 %
(1) Feed section	60 - 90 °C
(2) Temperature Zone 1 - Zone 4	320 - 350 °C
(3) Nozzle temperature	330 - 350 °C
(4) Melt temperature	330 - 350 °C
(5) Mold temperature	120 - 160 °C
(→) Holding pressure, spec.	300 - 800 bar
(←) Back pressure, spec.	50 - 150 bar
Injection speed	medium to high
Screw speed	8 - 15 m/min

Diagrams

