

Durethan® AKV30XTS3 901510
PA66-GF30

Envalior

Injection Molding, 30% Glass Reinforced, Heat Stabilized

ISO 1043 PA66-GF30

Rheological properties	dry / cond	Unit	Test Standard
ISO Data			
Molding shrinkage, parallel	0.3 / *	%	ISO 294-4, 2577
Molding shrinkage, normal	1.0 / *	%	ISO 294-4, 2577
Mechanical Properties	dry / cond	Unit	Test Standard
ISO Data			
Tensile Modulus	10000 / 6000	MPa	ISO 527
Stress at Break	175 / 110	MPa	ISO 527
Strain at Break	3 / 5	%	ISO 527
Impact Strength (Charpy), +23°C	65 / 80	kJ/m ²	ISO 179/1eU
Impact Strength (Charpy), -30°C	55 / 50	kJ/m ²	ISO 179/1eU
Notched Impact Strength (Charpy), +23°C	10 / 15	kJ/m ²	ISO 179/1eA
Notched Impact Strength (Charpy), -30°C	- / 10	kJ/m ²	ISO 179/1eA
Thermal Properties	dry / cond	Unit	Test Standard
ISO Data			
Melting Temperature (10°C/min)	262 / *	°C	ISO 11357-1/-3
Temp. of deflection under load (1.80 MPa)	235 / *	°C	ISO 75-1/-2
Coeff. of Linear Therm. Expansion, parallel	25 / *	E-6/K	ISO 11359-1/-2
Coeff. of Linear Therm. Expansion, normal	95 / *	E-6/K	ISO 11359-1/-2
Electrical Properties	dry / cond	Unit	Test Standard
ISO Data			
Volume Resistivity	>1E13 / -	Ohm*m	IEC 62631-3-1
Electric Strength	34 / -	kV/mm	IEC 60243-1
Comparative tracking index	525 / -	-	IEC 60112
Other Properties	dry / cond	Unit	Test Standard
ISO Data			
Water Absorption	5.5 / *	%	Sim. to ISO 62
Humidity absorption	2 / *	%	Sim. to ISO 62
Density	1360 / -	kg/m ³	ISO 1183
Test specimen production	Value	Unit	Test Standard
ISO Data			
Injection Molding, melt temperature	290	°C	ISO 294
Injection Molding, mold temperature	80	°C	ISO 294
Processing Recommendation Injection Molding	Value	Unit	Test Standard
Pre-drying - Temperature	80	°C	-
Pre-drying - Time	2 - 6	h	-
Processing humidity	≤0.12	%	-
Melt temperature	270 - 290	°C	-
Mold temperature	80 - 120	°C	-


Durethan® AKV30XTS3 901510

PA66-GF30


Envalior

Diagrams


Stress-strain

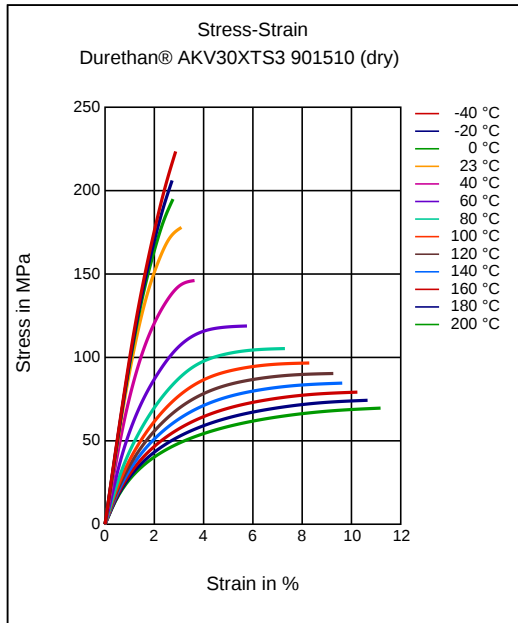


Stress-strain

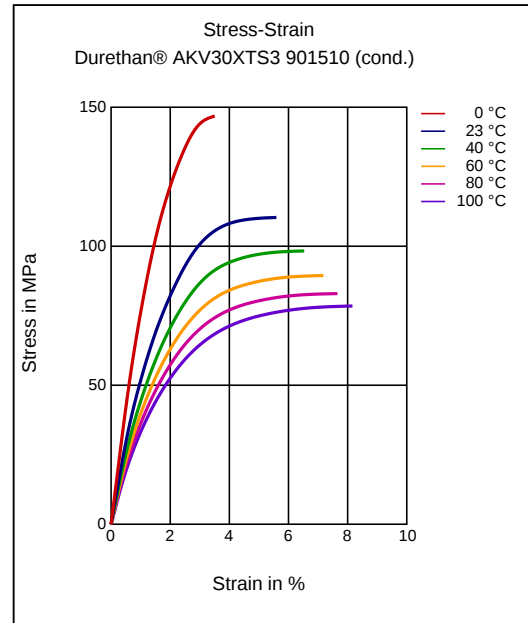

Secant modulus-strain

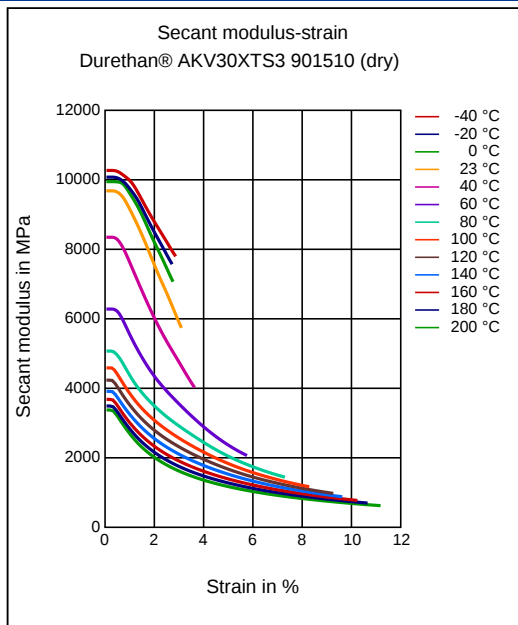

Secant modulus-strain

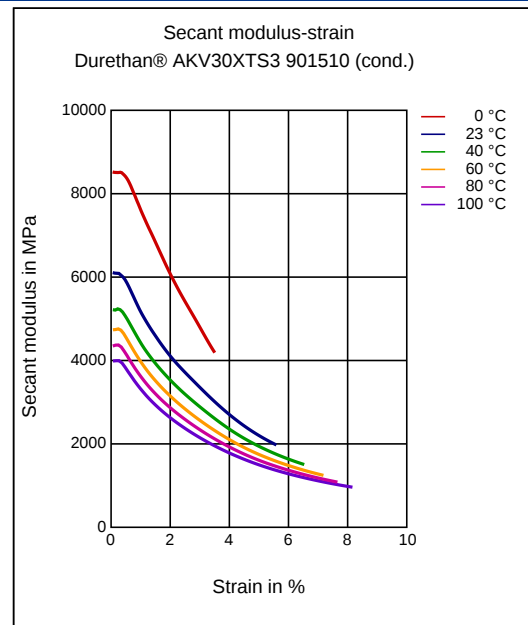

Characteristics

Processing

Injection Molding

Delivery form

Pellets

Injection Molding

PREPROCESSING

Special Characteristics

Heat aging stabilized

Durethan® AKV30XTS3 901510
PA66-GF30

Envalior

Residual moisture content: 0.03 - 0.12%
Drying temperature dry air dryer: 80 °C

Drying time dry air dryer 2 - 6 h

PROCESSING

Melt temperature (Tmin - Tmax): 270 - 290 °C
admissible residence time at Tmax <5 min
Mold temperature: 80 - 120 °C