

Ultramid® A3X2G7

PA66-GF35 FR(52)

BASF

Glass fibre fibre reinforced injection moulding grade with improved flame retardance. Flame retardant based on red phosphorus; giving outstanding electrical properties and very high stiffness and strength.

The products can also be offered as BMBcert™ and/or Cycled™. Due to the Massbalance approach the product properties do not change.

Rheological properties	dry / cond	Unit	Test Standard
ISO Data			
Melt volume-flow rate, MVR	25 / *	cm³/10min	ISO 1133
Temperature	275 / *	°C	-
Load	5 / *	kg	-
Molding shrinkage, parallel	0.3 / *	%	ISO 294-4, 2577
Molding shrinkage, normal	1.1 / *	%	ISO 294-4, 2577

Mechanical Properties	dry / cond	Unit	Test Standard
ISO Data			
Tensile Modulus	11000 / 8500	MPa	ISO 527
Stress at Break	160 / 120	MPa	ISO 527
Strain at Break	3 / 6	%	ISO 527
Tensile Creep Modulus, 1000h	* / 4250	MPa	ISO 899-1
Impact Strength (Charpy), +23°C	70 / 70	kJ/m²	ISO 179/1eU
Impact Strength (Charpy), -30°C	65 / -	kJ/m²	ISO 179/1eU
Notched Impact Strength (Charpy), +23°C	14 / 18	kJ/m²	ISO 179/1eA
Notched Impact Strength (Charpy), -30°C	10 / -	kJ/m²	ISO 179/1eA

Thermal Properties	dry / cond	Unit	Test Standard
ISO Data			
Melting Temperature (10°C/min)	260 / *	°C	ISO 11357-1/-3
Temp. of deflection under load (1.80 MPa)	240 / *	°C	ISO 75-1/-2
Temp. of deflection under load (0.45 MPa)	250 / *	°C	ISO 75-1/-2
Coeff. of Linear Therm. Expansion, parallel	20 / *	E-6/K	ISO 11359-1/-2
Coeff. of Linear Therm. Expansion, normal	95 / *	E-6/K	ISO 11359-1/-2
Burning Behav. at 1.5 mm Nom. Thickn.	V-0 / *	class	UL 94
Thickness tested	1.6 / *	mm	-
UL recognition	yes / *	-	-
Burning Behav. at thickness h	V-0 / *	class	UL 94
Thickness tested	0.8 / *	mm	-
UL recognition	yes / *	-	-
Burning Behav. 5V at Thickness h	5VA / *	class	IEC 60695-11-20
Thickness tested	1.5 / *	mm	-
Yellow Card available	yes / *	-	-
Oxygen index	27 / *	%	ISO 4589-1/-2

Electrical Properties	dry / cond	Unit	Test Standard
ISO Data			
Relative permittivity, 1MHz	3.6 / 5	-	IEC 62631-2-1
Dissipation Factor, 1MHz	200 / 2000	E-4	IEC 62631-2-1
Volume Resistivity	1E13 / 1E10	Ohm*m	IEC 62631-3-1
Surface Resistivity	* / 1E13	Ohm	IEC 62631-3-2
Electric Strength	33 / 30	kV/mm	IEC 60243-1
Comparative tracking index	- / 600	-	IEC 60112

Other Properties	dry / cond	Unit	Test Standard
ISO Data			
Water Absorption	4.7 / *	%	Sim. to ISO 62
Humidity absorption	1.2 / *	%	Sim. to ISO 62
Density	1450 / -	kg/m³	ISO 1183

Material Specific Properties	dry / cond	Unit	Test Standard
ISO Data			
Viscosity number	140 / *	cm³/g	ISO 307, 1157, 1628

Ultramid® A3X2G7

PA66-GF35 FR(52)

BASF


Rheological calculation properties	Value	Unit	Test Standard
ISO Data			
Ejection temperature	195	°C	-

Test specimen production	Value	Unit	Test Standard
ISO Data			
Injection Molding, melt temperature	290	°C	ISO 294
Injection Molding, mold temperature	80	°C	ISO 294
Injection Molding, injection velocity	200	mm/s	ISO 294


Processing Recommendation Injection Molding	Value	Unit	Test Standard
Pre-drying - Temperature	80 - 100	°C	-
Pre-drying - Time	4	h	-
Processing humidity	≤0.15	%	-
Melt temperature	280 - 300	°C	-
Mold temperature	80 - 90	°C	-

Diagrams

Viscosity-shear rate

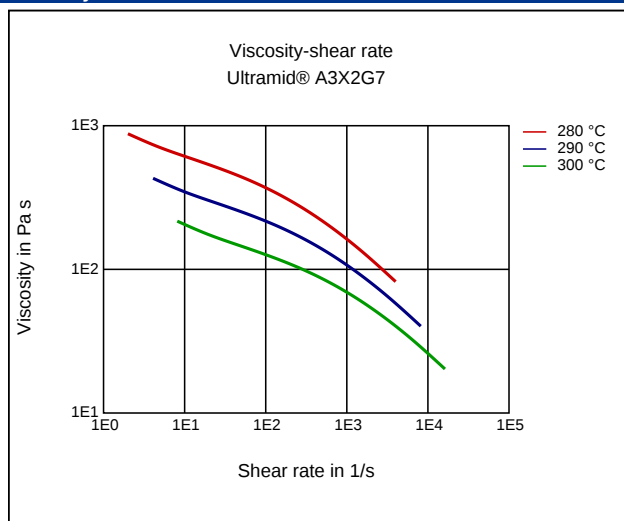


Shearstress-shear rate

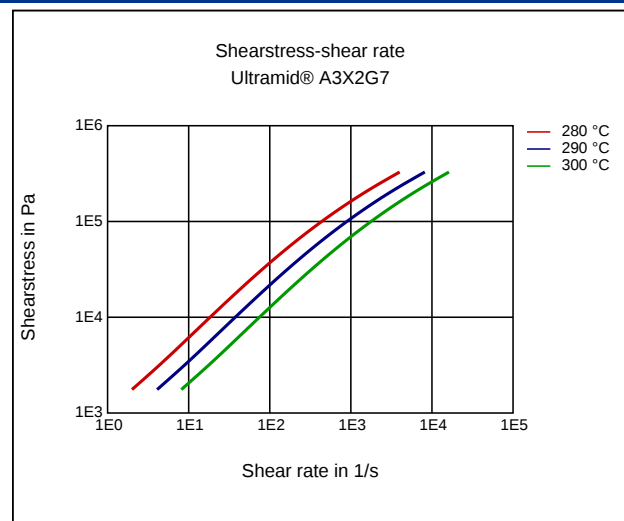


Ultramid® A3X2G7
PA66-GF35 FR(52)

BASF


Dynamic Shear modulus-temperature

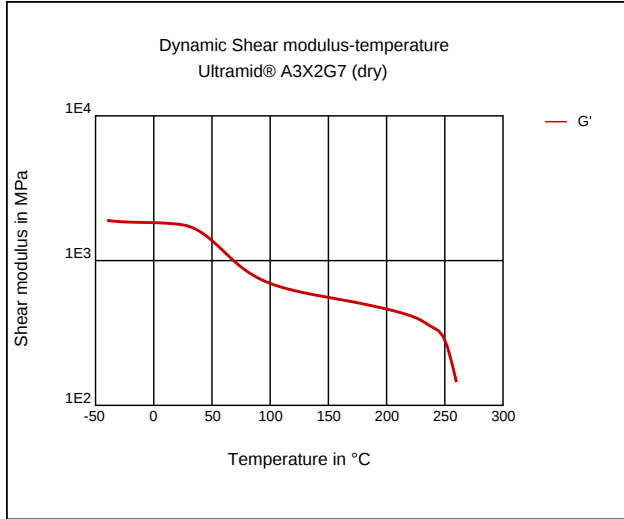


Stress-strain

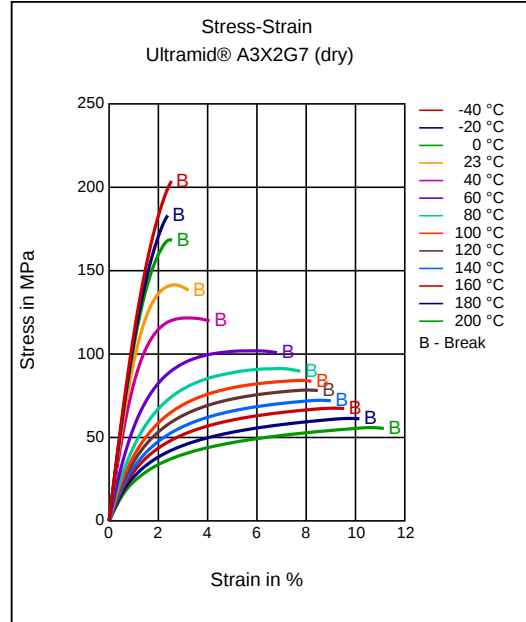

Stress-strain

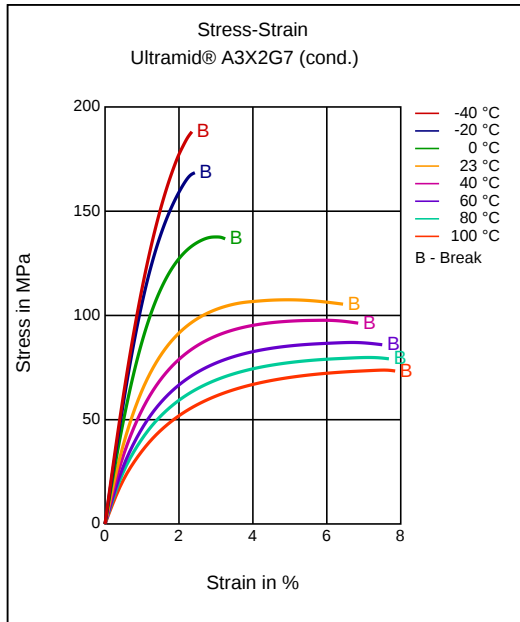


Secant modulus-strain

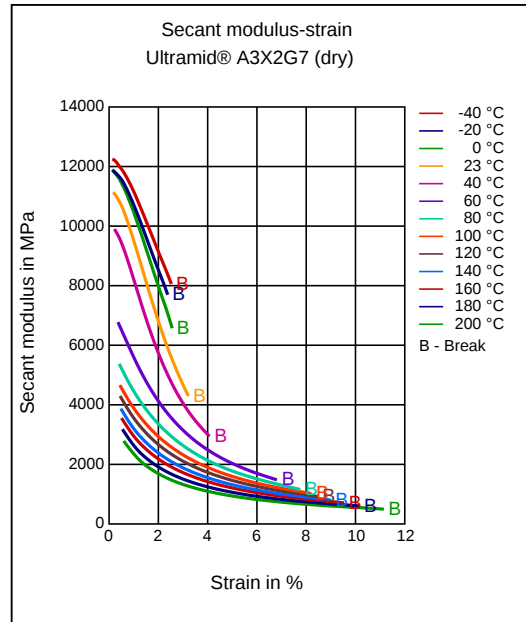


Ultramid® A3X2G7
PA66-GF35 FR(52)

BASF


Secant modulus-strain

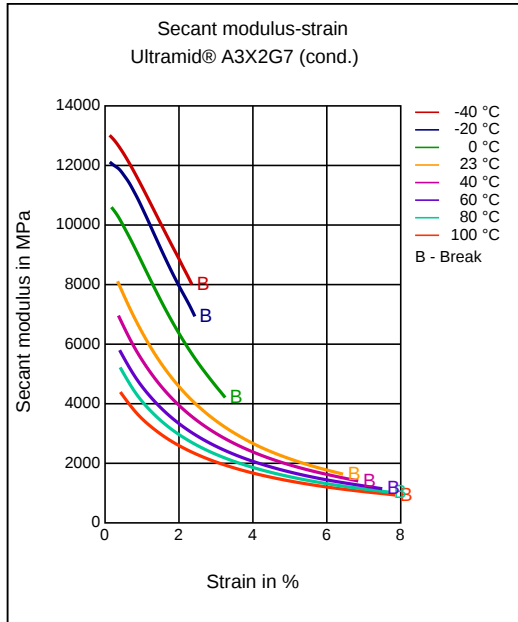


Stress-strain (isochronous) 23 °C

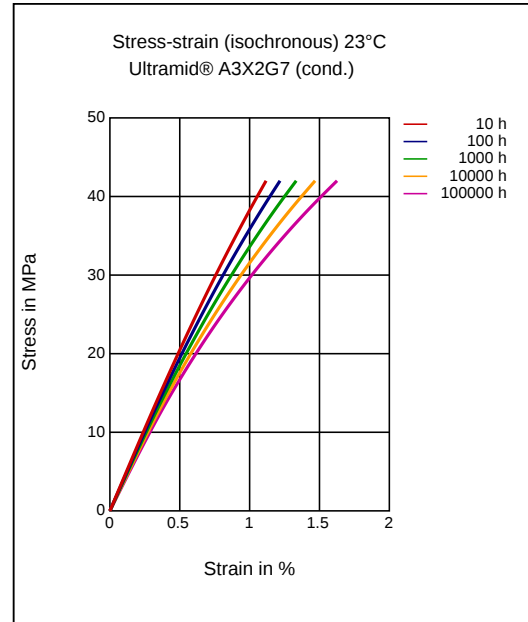

Creep modulus-time 23 °C

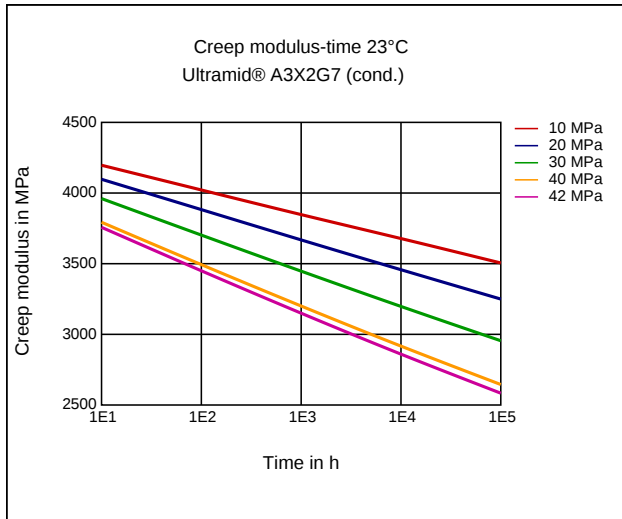


Stress-strain (isochronous) 90 °C

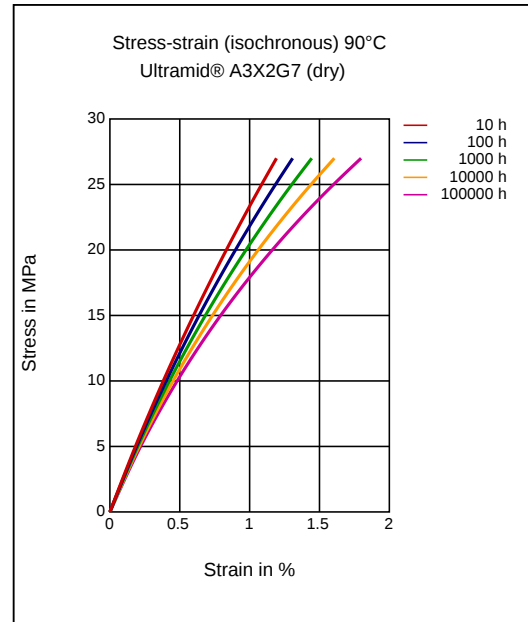


Ultramid® A3X2G7
PA66-GF35 FR(52)

BASF


Creep modulus-time 90 °C

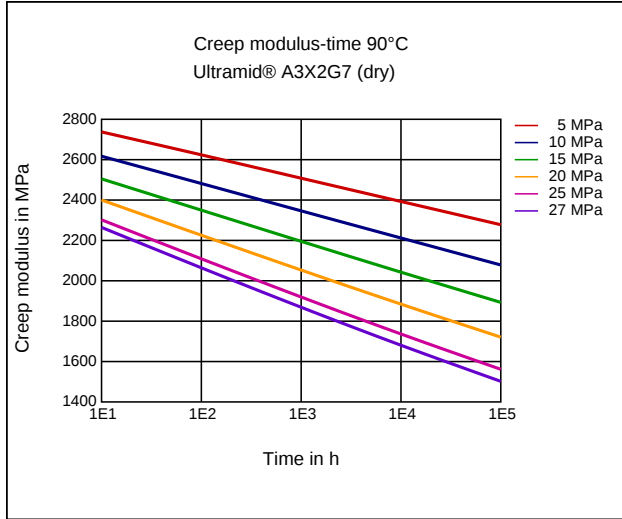


Stress-strain (isochronous) 120 °C

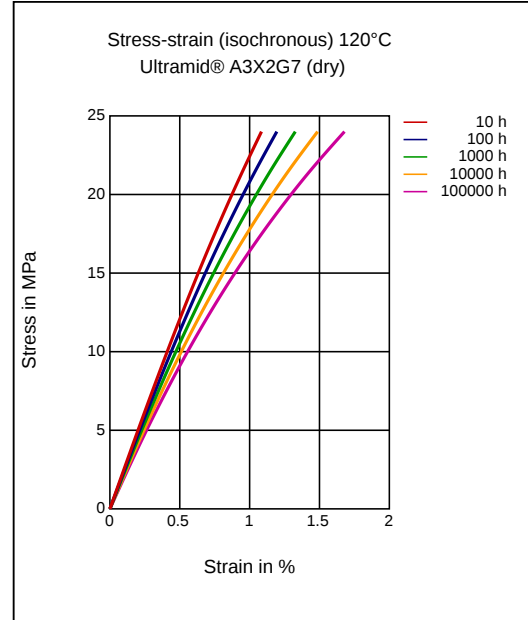

Creep modulus-time 120 °C

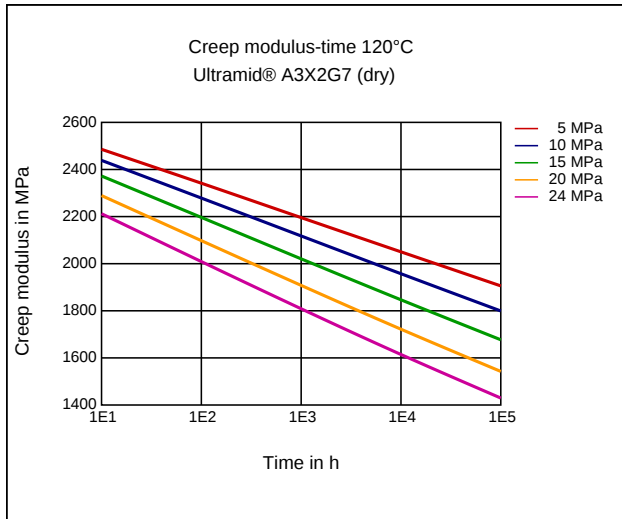

Specific volume-temperature (pvT)

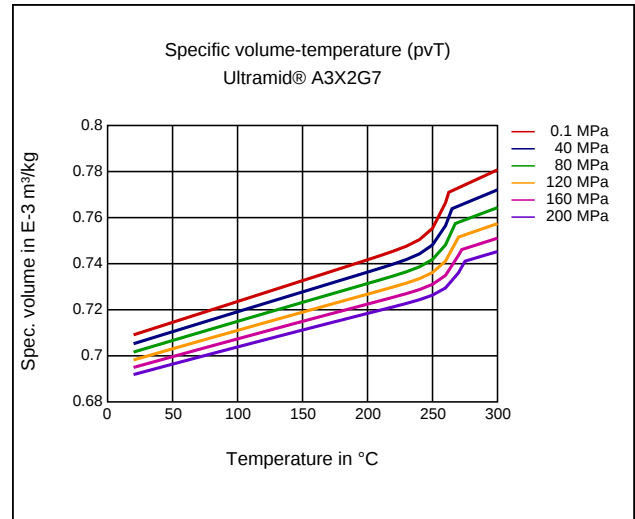


Ultramid® A3X2G7


PA66-GF35 FR(52)

BASF


Tensile Modulus-Temperature

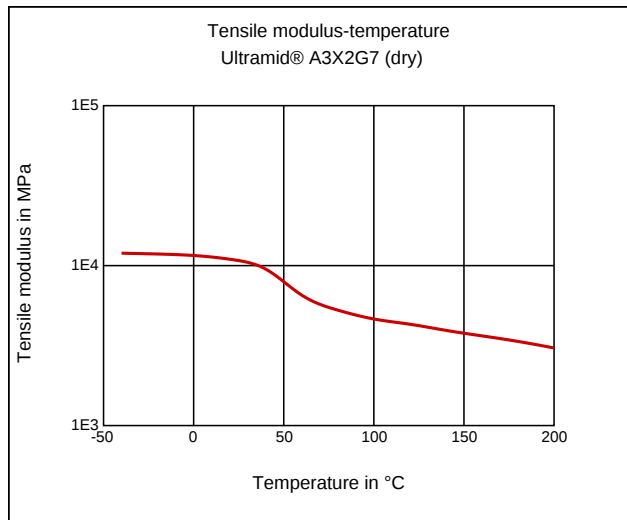

Tensile Modulus-Temperature

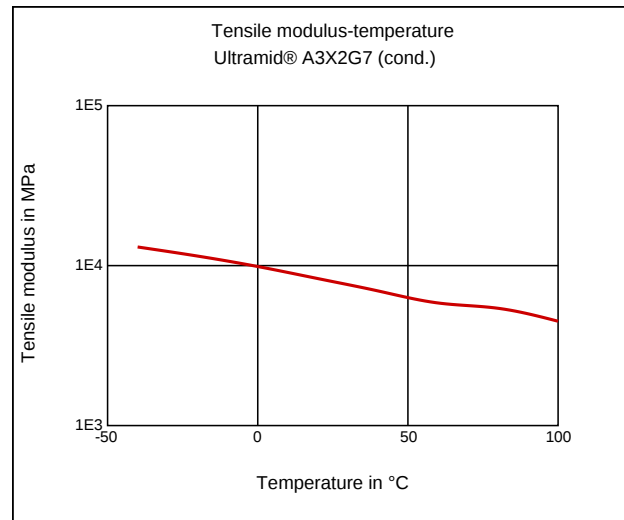

Coeff. of linear thermal expansion, normal

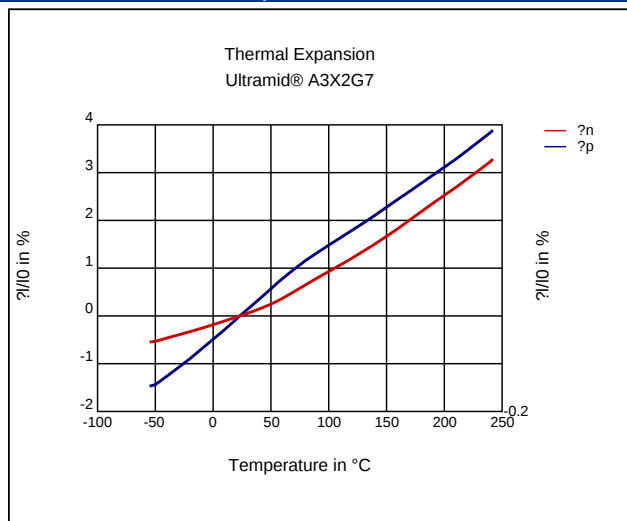

Characteristics

Processing

Injection Molding

Delivery form

Pellets

Additives

Release agent

Special Characteristics

Flame retardant, Halogen-free, Heat aging stabilized

Injection Molding

PREPROCESSING

Pre/Post-processing, max. allowed water content: .15 %

Pre/Post-processing, Pre-drying, Temperature: 80 - 100 °C

Pre/Post-processing, Pre-drying, Time: 4 h

PROCESSING

injection molding, Melt temperature, range: 280 - 300 °C

injection molding, Melt temperature, recommended: 290 °C

injection molding, Mold temperature, range: 80 - 90 °C

injection molding, Mold temperature, recommended: 80 °C

Ultramid® A3X2G7

PA66-GF35 FR(52)

BASF

injection molding, Dwell time, thermoplastics: 10 min

Chemical Media Resistance

Acids

- ✓ Acetic Acid (5% by mass) (23°C)