

Pocan® B1501 000000

PBT

Envalior

Injection Molding, Unreinforced, Extrusion, Food Contact Quality

ISO 1043 PBT

Rheological properties	Value	Unit	Test Standard
ISO Data			
Melt volume-flow rate, MVR	16	cm ³ /10min	ISO 1133
Temperature	250	°C	-
Load	2.16	kg	-
Molding shrinkage, parallel	1.8	%	ISO 294-4, 2577
Molding shrinkage, normal	1.8	%	ISO 294-4, 2577

Mechanical Properties	Value	Unit	Test Standard
ISO Data			
Tensile Modulus	2600	MPa	ISO 527
Yield stress	60	MPa	ISO 527
Yield strain	4	%	ISO 527
Tensile Creep Modulus, 1h	2200	MPa	ISO 899-1
Tensile Creep Modulus, 1000h	1300	MPa	ISO 899-1
Impact Strength (Charpy), +23°C	no break	kJ/m ²	ISO 179/1eU
Impact Strength (Charpy), -30°C	195	kJ/m ²	ISO 179/1eU
Notched Impact Strength (Charpy), +23°C	10	kJ/m ²	ISO 179/1eA
Notched Impact Strength (Charpy), -30°C	10	kJ/m ²	ISO 179/1eA
Puncture - maximum force, +23°C	3560	N	ISO 6603-2
Puncture energy, +23°C	43	J	ISO 6603-2
Flexural Modulus (23°C)	2600	MPa	ISO 178
Notched Impact Strength (Izod), 23°C	10	kJ/m ²	ISO 180/1A
Notched Impact Strength (Izod)	10	kJ/m ²	ISO 180/1A
Temperature	-30	°C	-
Impact Strength (Izod), 23°C	no break	kJ/m ²	ISO 180/1U
Ball Indentation Hardness	120	MPa	ISO 2039-1

Thermal Properties	Value	Unit	Test Standard
ISO Data			
Melting Temperature (10°C/min)	225	°C	ISO 11357-1/-3
Temp. of deflection under load (1.80 MPa)	55	°C	ISO 75-1/-2
Temp. of deflection under load (0.45 MPa)	150	°C	ISO 75-1/-2
Coeff. of Linear Therm. Expansion, parallel	110	E-6/K	ISO 11359-1/-2
Coeff. of Linear Therm. Expansion, normal	110	E-6/K	ISO 11359-1/-2
Burning Behav. at 1.5 mm Nom. Thickn.	HB	class	UL 94
Thickness tested	1.5	mm	-
Oxygen index	24	%	ISO 4589-1/-2

Electrical Properties	Value	Unit	Test Standard
ISO Data			
Relative permittivity, 100Hz	3.4	-	IEC 62631-2-1
Relative permittivity, 1MHz	3.2	-	IEC 62631-2-1
Dissipation Factor, 100Hz	15	E-4	IEC 62631-2-1
Dissipation Factor, 1MHz	190	E-4	IEC 62631-2-1
Surface Resistivity	>1E15	Ohm	IEC 62631-3-2
Electric Strength	27	kV/mm	IEC 60243-1
Comparative tracking index	600	-	IEC 60112

Other Properties	Value	Unit	Test Standard
ISO Data			
Water Absorption	0.5	%	Sim. to ISO 62
Humidity absorption	0.2	%	Sim. to ISO 62
Density	1310	kg/m ³	ISO 1183
Bulk density	800	kg/m ³	-

Pocan® B1501 000000

PBT

Envalior


Material Specific Properties	Value	Unit	Test Standard
ISO Data			
Viscosity number	140	cm ³ /g	ISO 307, 1157, 1628

Test specimen production	Value	Unit	Test Standard
ISO Data			
Injection Molding, melt temperature	250	°C	ISO 294
Injection Molding, mold temperature	80	°C	ISO 294


Processing Recommendation Injection Molding	Value	Unit	Test Standard
Pre-drying - Temperature	120	°C	-
Pre-drying - Time	4 - 8	h	-
Processing humidity	≤0.02	%	-
Melt temperature	250 - 260	°C	-
Mold temperature	80 - 100	°C	-

Diagrams


Viscosity-shear rate

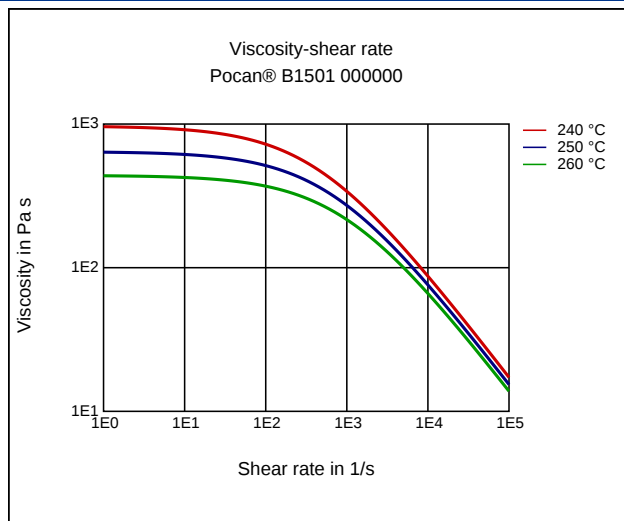

Shearstress-shear rate

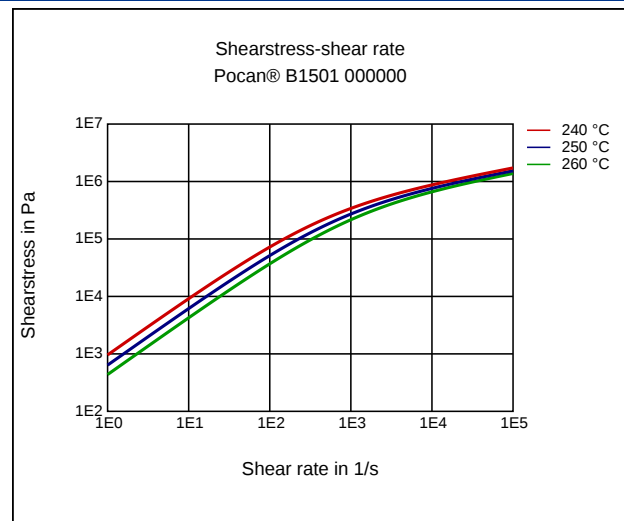

Specific volume-temperature (pvT)

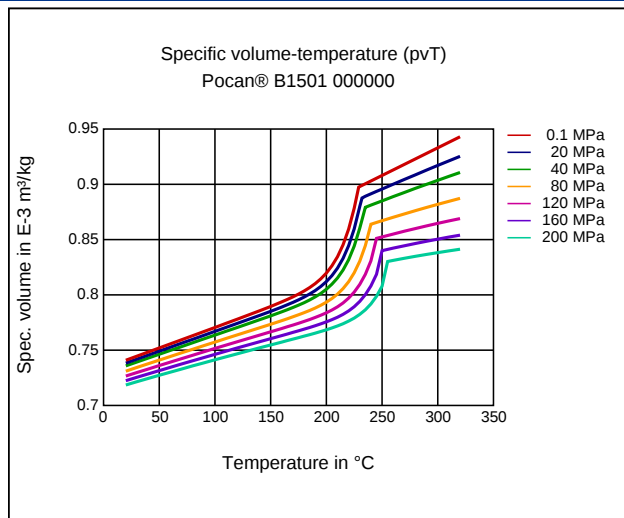

Pocan® B1501 000000

PBT

Envalior

Characteristics

Processing

Injection Molding, Other Extrusion

Additives

Release agent

Delivery form

Pellets

Certifications

Food approval

Injection Molding

PREPROCESSING

Residual moisture content: 0.00 - 0.02 %

Drying temperature circulating air dryer: 120 °C

Drying time circulating air dryer: 4 - 8 h

PROCESSING

Melt temperature (Tmin - Tmax): 250 - 260 °C

Mold temperature: 80 - 100 °C