

Ultradur® B 4520 High Speed PBT

BASF

Easy flowing injection molding grade for connectors and other technical parts.

Abbreviated designation according to ISO 1043-1: PBT

Rheological properties	Value	Unit	Test Standard
ISO Data			
Melt volume-flow rate, MVR	50	cm³/10min	ISO 1133
Temperature	250	°C	-
Load	2.16	kg	-

Mechanical Properties	Value	Unit	Test Standard
ISO Data			
Tensile Modulus	2200	MPa	ISO 527
Yield stress	53	MPa	ISO 527
Yield strain	3.5	%	ISO 527
Nominal strain at break	>50	%	ISO 527
Impact Strength (Charpy), +23°C	190	kJ/m²	ISO 179/1eU
Notched Impact Strength (Charpy), +23°C	4	kJ/m²	ISO 179/1eA

Thermal Properties	Value	Unit	Test Standard
ISO Data			
Melting Temperature (10°C/min)	223	°C	ISO 11357-1/-3
Temp. of deflection under load (1.80 MPa)	55	°C	ISO 75-1/-2
Temp. of deflection under load (0.45 MPa)	130	°C	ISO 75-1/-2
Burning Behav. at 1.5 mm Nom. Thickn.	HB	class	UL 94
Thickness tested	1.5	mm	-
UL recognition	yes	-	-
Burning Behav. at thickness h	HB	class	UL 94
Thickness tested	0.4	mm	-

Electrical Properties	Value	Unit	Test Standard
ISO Data			
Electric Strength	36	kV/mm	IEC 60243-1

Other Properties	Value	Unit	Test Standard
ISO Data			
Water Absorption	0.5	%	Sim. to ISO 62
Humidity absorption	0.25	%	Sim. to ISO 62
Density	1300	kg/m³	ISO 1183

Material Specific Properties	Value	Unit	Test Standard
ISO Data			
Viscosity number	115	cm³/g	ISO 307, 1157, 1628

Rheological calculation properties	Value	Unit	Test Standard
ISO Data			
Density of melt	1060	kg/m³	-

Test specimen production	Value	Unit	Test Standard
ISO Data			
Injection Molding, melt temperature	240	°C	ISO 294
Injection Molding, mold temperature	60	°C	ISO 294
Injection Molding, injection velocity	200	mm/s	ISO 294


Processing Recommendation Injection Molding	Value	Unit	Test Standard
Pre-drying - Temperature	80 - 120	°C	-
Pre-drying - Time	4	h	-
Processing humidity	≤0.04	%	-
Melt temperature	250 - 275	°C	-
Mold temperature	40 - 70	°C	-

Ultradur® B 4520 High Speed PBT


BASF

Diagrams


Dynamic Shear modulus-temperature

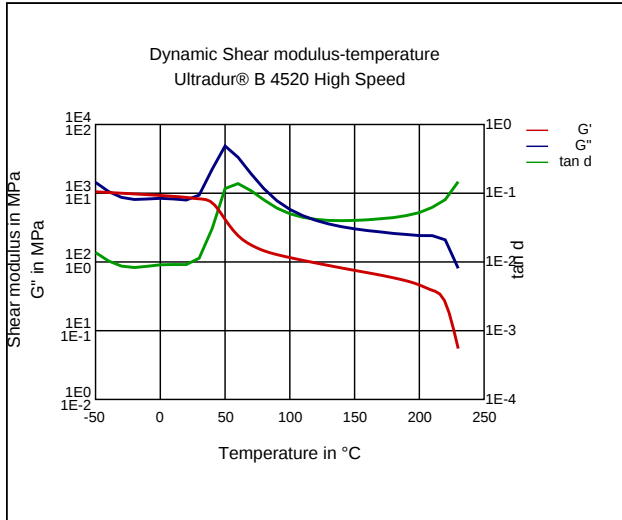


Stress-strain

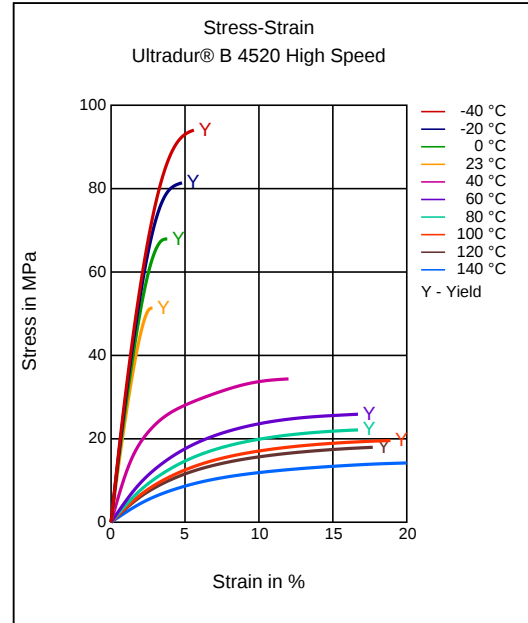

Secant modulus-strain

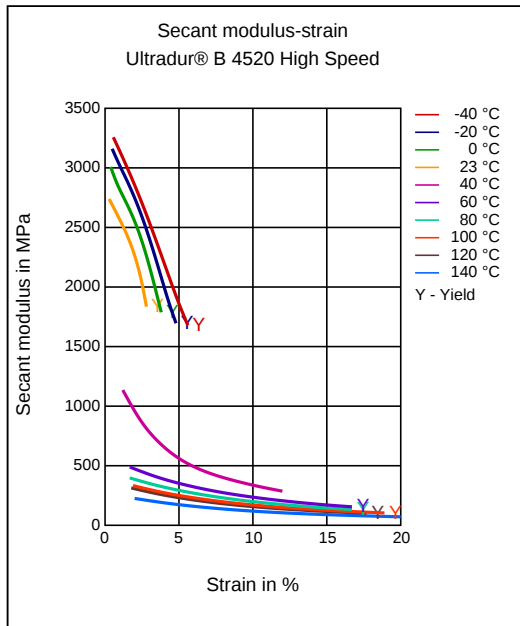

Specific volume-temperature (pvT)

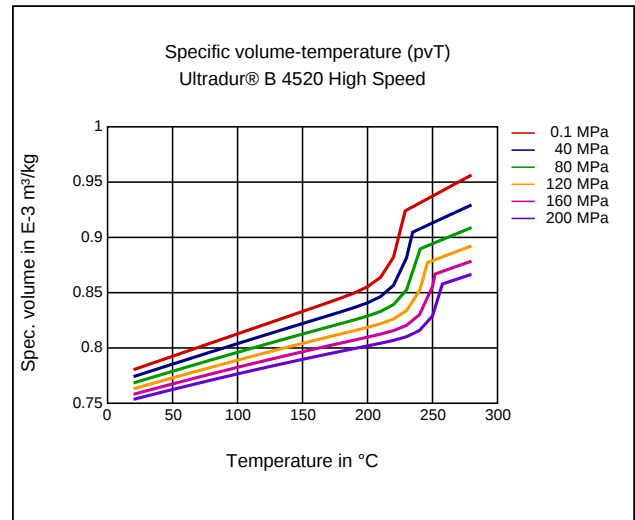


Ultradur® B 4520 High Speed

PBT

BASF

Tensile Modulus-Temperature

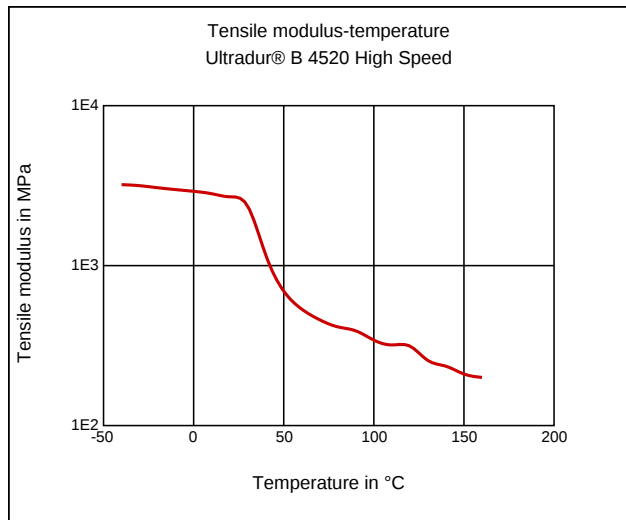

Characteristics

Processing

Injection Molding

Additives

Lubricants

Delivery form

Pellets

Special Characteristics

Light stabilized or stable to light, UV stablized, Heat aging stabilized

Injection Molding

PREPROCESSING

Pre/Post-processing, max. allowed water content: .04 %

Pre/Post-processing, Pre-drying, Temperature: 80 - 120 °C

Pre/Post-processing, Pre-drying, Time: 4 h

PROCESSING

injection molding, Melt temperature, range: 250 - 275 °C

injection molding, Melt temperature, recommended: 260 °C

injection molding, Mold temperature, range: 40 - 70 °C

injection molding, Mold temperature, recommended: 60 °C

Chemical Media Resistance

Acids

- ✓ Acetic Acid (5% by mass) (23°C)