

Ultrason® E 2010 G6 UN

PESU-GF30

BASF

Medium viscosity injection moulding grade with high rigidity and strength, 30 % glass fiber reinforced.

Abbreviated designation according to ISO 1043: PESU-GF

Processing/Physical Characteristics	Value	Unit	Test Standard
ASTM Data			
Mold Shrinkage, MD	0.004	mm/mm	ASTM D 955
Density, 73°F	1600	kg/m³	ASTM D 792

Rheological properties	dry / cond	Unit	Test Standard
ISO Data			
Melt volume-flow rate, MVR	25 / *	cm³/10min	ISO 1133
Temperature	360 / *	°C	-
Load	10 / *	kg	-
Molding shrinkage, parallel	0.3 / *	%	ISO 294-4, 2577
Molding shrinkage, normal	0.6 / *	%	ISO 294-4, 2577

Mechanical Properties	dry / cond	Unit	Test Standard
ISO Data			
Tensile Modulus	- / 9800	MPa	ISO 527
Stress at Break	- / 155	MPa	ISO 527
Strain at Break	- / 2.3	%	ISO 527
Tensile Creep Modulus, 1h	* / 9000	MPa	ISO 899-1
Impact Strength (Charpy), +23°C	- / 60	kJ/m²	ISO 179/1eU
Impact Strength (Charpy), -30°C	- / 65	kJ/m²	ISO 179/1eU
Notched Impact Strength (Charpy), +23°C	- / 10	kJ/m²	ISO 179/1eA
Notched Impact Strength (Charpy), -30°C	- / 9.5	kJ/m²	ISO 179/1eA
ASTM Data			
Tensile Strength at Break	140 / -	MPa	ASTM D 638
Elongation at Break	1.9 / -	%	ASTM D 638
Flexural Modulus	9722 / -	MPa	ASTM D 790
Notched Impact Strength (Izod), 1/8 in	10 / -	J/m	ASTM D 256

Thermal Properties	dry / cond	Unit	Test Standard
ISO Data			
Glass Transition Temperature (10°C/min)	225 / *	°C	ISO 11357-1/-2
Temp. of deflection under load (1.80 MPa)	222 / *	°C	ISO 75-1/-2
Temp. of deflection under load (0.45 MPa)	224 / *	°C	ISO 75-1/-2
Vicat softening temperature, 50°C/h 50N	217 / *	°C	ISO 306
Coeff. of Linear Therm. Expansion, parallel	15 / *	E-6/K	ISO 11359-1/-2
Coeff. of Linear Therm. Expansion, normal	45 / *	E-6/K	ISO 11359-1/-2
Burning Behav. at 1.5 mm Nom. Thickn.	V-0 / *	class	UL 94
Thickness tested	1.5 / *	mm	-
UL recognition	yes / *	-	-
Burning Behav. at thickness h	V-0 / *	class	UL 94
Thickness tested	3.0 / *	mm	-
UL recognition	yes / *	-	-
Oxygen index	47.3 / *	%	ISO 4589-1/-2
ASTM Data			
Coefficient of Thermal Expansion, TD	40	E-6/K	ASTM D 696
DTUL @ 66 psi	215	°C	ASTM D 648
DTUL @ 264 psi	212	°C	ASTM D 648

Electrical Properties	dry / cond	Unit	Test Standard
ISO Data			
Relative permittivity, 100Hz	- / 4.3	-	IEC 62631-2-1
Relative permittivity, 1MHz	- / 4.3	-	IEC 62631-2-1
Dissipation Factor, 100Hz	- / 20	E-4	IEC 62631-2-1
Dissipation Factor, 1MHz	- / 100	E-4	IEC 62631-2-1
Volume Resistivity	- / >1E13	Ohm*m	IEC 62631-3-1
Surface Resistivity	* / >1E15	Ohm	IEC 62631-3-2
Electric Strength	- / 37	kV/mm	IEC 60243-1
Comparative tracking index	- / 125	-	IEC 60112

Ultrason® E 2010 G6 UN
PESU-GF30

BASF

Other Properties	dry / cond	Unit	Test Standard
ISO Data			
Water Absorption	1.6 / *	%	Sim. to ISO 62
Humidity absorption	0.6 / *	%	Sim. to ISO 62
Density	1590 / -	kg/m³	ISO 1183

Material Specific Properties	dry / cond	Unit	Test Standard
ISO Data			
Viscosity number	56 / *	cm³/g	ISO 307, 1157, 1628

Rheological calculation properties	Value	Unit	Test Standard
ISO Data			
Density of melt	1410	kg/m³	-
Thermal Conductivity of Melt	0.24	W/(m K)	-
Spec. heat capacity of melt	1740	J/(kg K)	-
Eff. thermal diffusivity	9.78E-8	m²/s	-
Ejection temperature	205	°C	-

Test specimen production	Value	Unit	Test Standard
ISO Data			
Injection Molding, melt temperature	370	°C	ISO 294
Injection Molding, mold temperature	170	°C	ISO 294
Injection Molding, injection velocity	200	mm/s	ISO 294
Injection Molding, pressure at hold	80	MPa	ISO 294


Processing Recommendation Injection Molding	Value	Unit	Test Standard
Pre-drying - Temperature	140	°C	-
Pre-drying - Time	4	h	-
Processing humidity	≤0.02	%	-
Melt temperature	350 - 390	°C	-
Mold temperature	150 - 190	°C	-

Ultrason® E 2010 G6 UN
PESU-GF30


BASF

Diagrams


Viscosity-shear rate

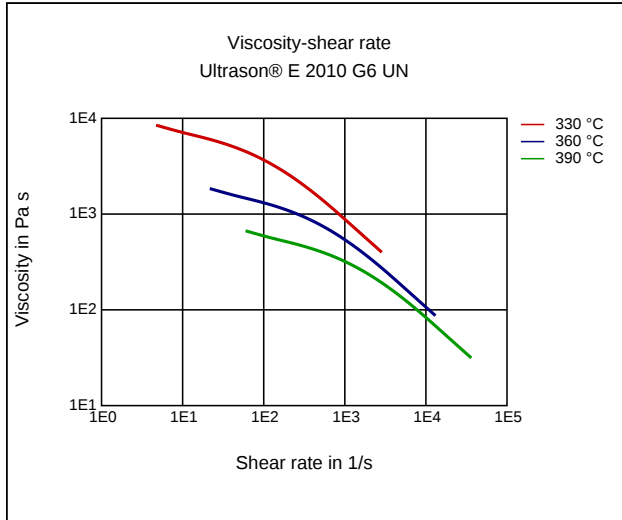


Shearstress-shear rate

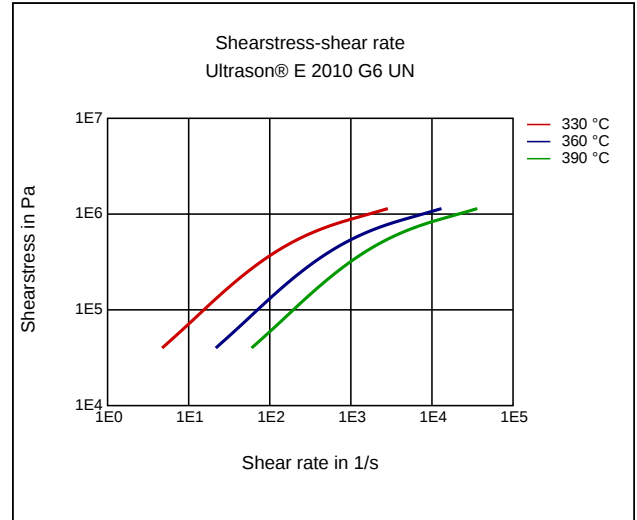

Dynamic Shear modulus-temperature

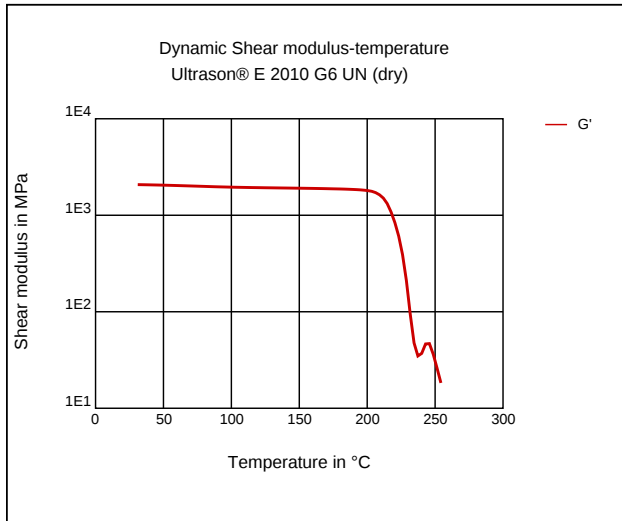


Stress-strain

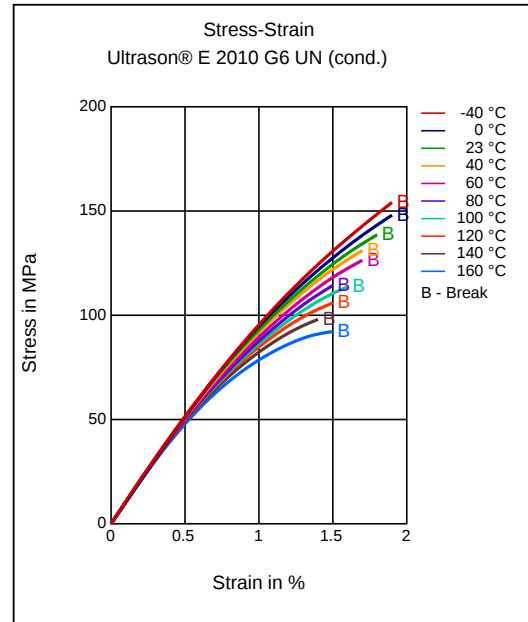


Ultrason® E 2010 G6 UN
PESU-GF30

BASF


Secant modulus-strain

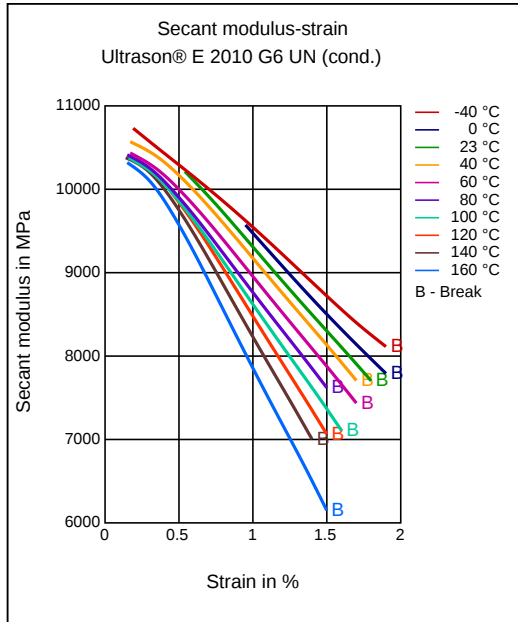


Stress-strain (isochronous) 23 °C

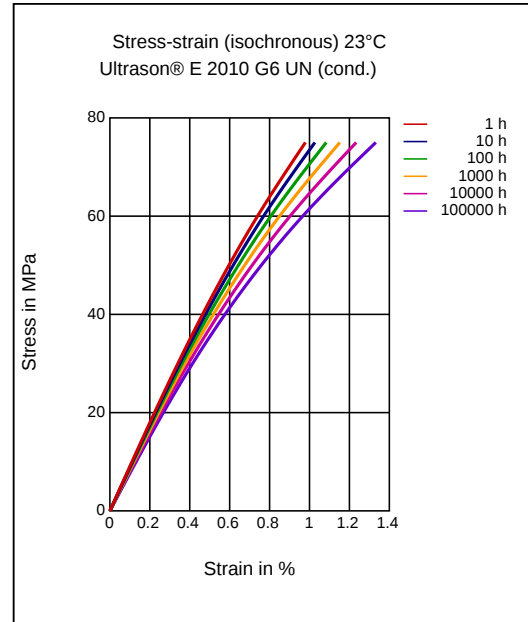

Creep modulus-time 23 °C

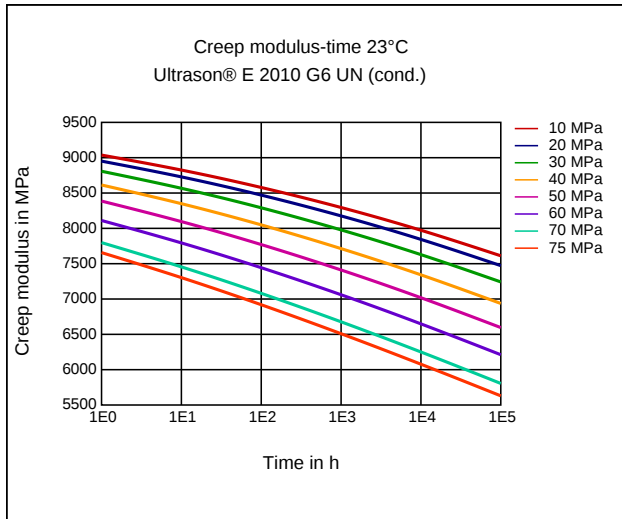

Stress-strain (isochronous) 180 °C

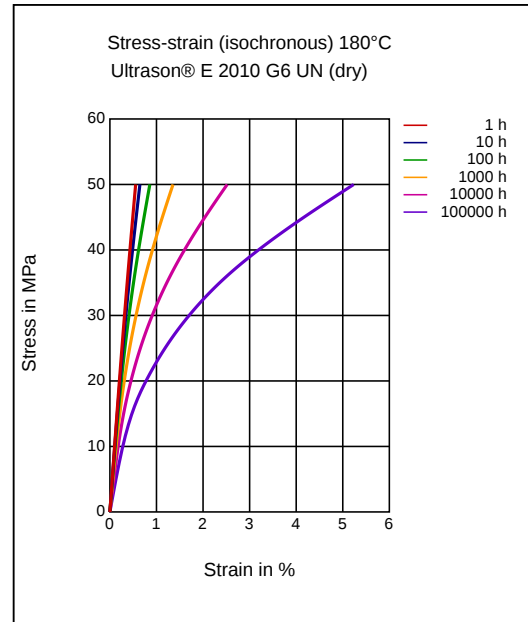


Ultrason® E 2010 G6 UN


PESU-GF30

BASF


Creep modulus-time 180 °C

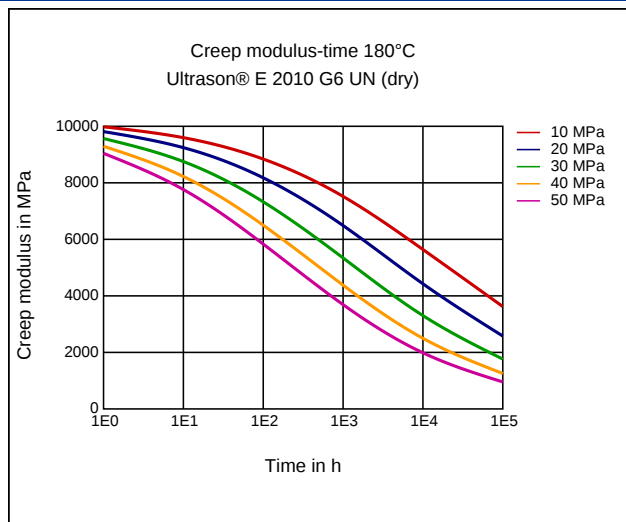

Specific volume-temperature (pvT)

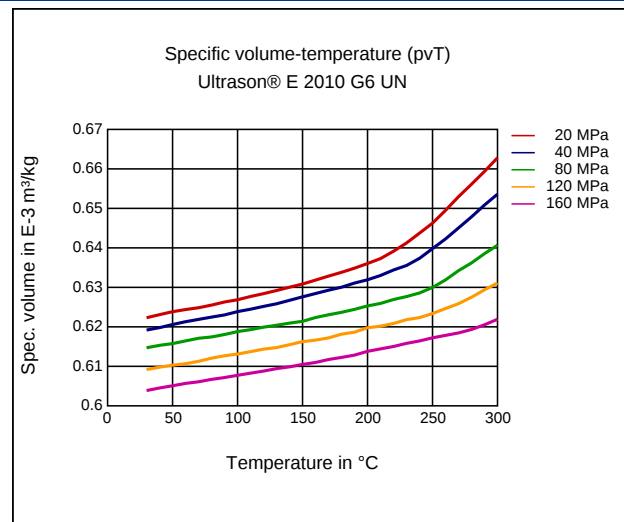

Tensile Modulus-Temperature

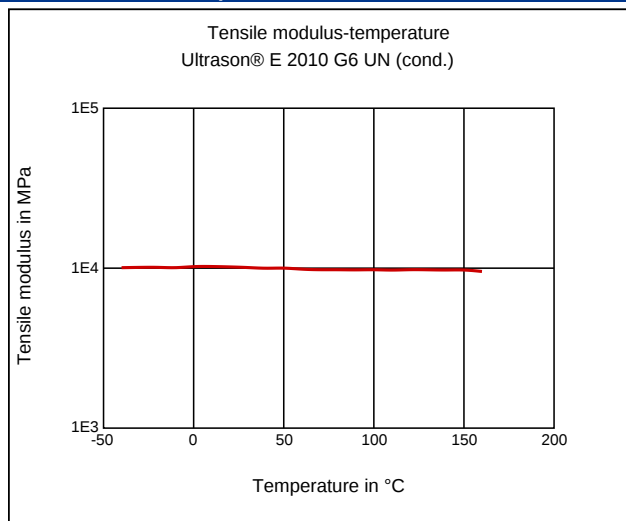

Characteristics

Processing

Injection Molding, Profile Extrusion, Sheet Extrusion

Delivery form

Pellets, Natural Color

Special Characteristics

Platable

Injection Molding

PREPROCESSING

Pre/Post-processing, max. allowed water content: .02 %

Pre/Post-processing, Pre-drying, Temperature: 140 °C

Pre/Post-processing, Pre-drying, Time: 4 h

PROCESSING

injection molding, Melt temperature, range: 350 - 390 °C

injection molding, Melt temperature, recommended: 370 °C

injection molding, Mold temperature, range: 150 - 190 °C

injection molding, Mold temperature, recommended: 170 °C

Ultrason® E 2010 G6 UN
PESU-GF30

BASF

injection molding, Dwell time, thermoplastics: 10 min

Pretreatment

Drying temperature: 130 - 150 °C

Drying time: minimum 4h

recommended dryer: vaccum or dry air dryer

maximum moisture: 0,02 - 0,05%

Ultrason® can be injection molded by any type of machinery on the market, provided that the plasticizing unit and the mold temperature control system have been configured appropriately. The machinery manufacturer must be consulted if any doubts exist on the ability of various parts to withstand the high temperatures required (e.g. barrel, barrel head, bolted connections, etc.)

Long residence time in combination with high temperatures should be avoided e.g. by pump out material at regular intervals.
During extended interruptions, the barrel temperature should be lowered to about 250-280 °C.

It has been found out that heating to the requested processing temperature and shutting down or lowering the temperature is best carried out in two steps.

First, the barrel temperatures are set at the lower processing temperature range for the particular thermoplastic (340 - 350 °C). As soon as these temperatures have reached a steady state, the material in the barrel is pumped out. Second, the barrel temperature can be set to the required processing temperature or the heaters can be shut down.