

Ultrason® S 2010 G6 UN

PSU-GF30

BASF

Medium viscosity injection moulding grade with high rigidity and strength, 30 % glass fiber reinforced

Abbreviated designation according to ISO 1043: PSU-GF30

Processing/Physical Characteristics	Value	Unit	Test Standard
ASTM Data			
Mold Shrinkage, MD	0.003	mm/mm	ASTM D 955
Density, 73°F	1490	kg/m³	ASTM D 792

Rheological properties	dry / cond	Unit	Test Standard
ISO Data			
Melt volume-flow rate, MVR	35 / *	cm³/10min	ISO 1133
Temperature	360 / *	°C	-
Load	10 / *	kg	-
Molding shrinkage, parallel	0.3 / *	%	ISO 294-4, 2577
Molding shrinkage, normal	0.5 / *	%	ISO 294-4, 2577

Mechanical Properties	dry / cond	Unit	Test Standard
ISO Data			
Tensile Modulus	- / 9000	MPa	ISO 527
Stress at Break	- / 130	MPa	ISO 527
Strain at Break	- / 3	%	ISO 527
Tensile Creep Modulus, 1h	* / 8600	MPa	ISO 899-1
Impact Strength (Charpy), +23°C	- / 45	kJ/m²	ISO 179/1eU
Impact Strength (Charpy), -30°C	- / 50	kJ/m²	ISO 179/1eU
Notched Impact Strength (Charpy), +23°C	- / 9	kJ/m²	ISO 179/1eA
Notched Impact Strength (Charpy), -30°C	- / 9	kJ/m²	ISO 179/1eA
ASTM Data			
Tensile Strength at Break	126 / -	MPa	ASTM D 638
Elongation at Break	1.8 / -	%	ASTM D 638
Flexural Modulus	10200 / -	MPa	ASTM D 790
Notched Impact Strength (Izod), 1/8 in	10 / -	J/m	ASTM D 256

Thermal Properties	dry / cond	Unit	Test Standard
ISO Data			
Glass Transition Temperature (10°C/min)	187 / *	°C	ISO 11357-1/-2
Temp. of deflection under load (1.80 MPa)	184 / *	°C	ISO 75-1/-2
Temp. of deflection under load (0.45 MPa)	187 / *	°C	ISO 75-1/-2
Vicat softening temperature, 50°C/h 50N	190 / *	°C	ISO 306
Coeff. of Linear Therm. Expansion, parallel	20 / *	E-6/K	ISO 11359-1/-2
Burning Behav. at 1.5 mm Nom. Thickn.	V-1 / *	class	UL 94
Thickness tested	1.6 / *	mm	-
UL recognition	yes / *	-	-
Burning Behav. at thickness h	V-0 / *	class	UL 94
Thickness tested	3.0 / *	mm	-
UL recognition	yes / *	-	-
Oxygen index	37.4 / *	%	ISO 4589-1/-2
ASTM Data			
DTUL @ 66 psi	186	°C	ASTM D 648
DTUL @ 264 psi	183	°C	ASTM D 648

Electrical Properties	dry / cond	Unit	Test Standard
ISO Data			
Relative permittivity, 100Hz	- / 3.7	-	IEC 62631-2-1
Relative permittivity, 1MHz	- / 3.7	-	IEC 62631-2-1
Dissipation Factor, 100Hz	- / 10	E-4	IEC 62631-2-1
Dissipation Factor, 1MHz	- / 60	E-4	IEC 62631-2-1
Volume Resistivity	- / >1E13	Ohm*m	IEC 62631-3-1
Surface Resistivity	* / >1E15	Ohm	IEC 62631-3-2
Electric Strength	- / 45	kV/mm	IEC 60243-1
Comparative tracking index	- / 125	-	IEC 60112

Ultrason® S 2010 G6 UN

PSU-GF30

BASF

Other Properties	dry / cond	Unit	Test Standard
ISO Data			
Water Absorption	0.6 / *	%	Sim. to ISO 62
Humidity absorption	0.2 / *	%	Sim. to ISO 62
Density	1460 / -	kg/m³	ISO 1183

Material Specific Properties	dry / cond	Unit	Test Standard
ISO Data			
Viscosity number	63 / *	cm³/g	ISO 307, 1157, 1628


Rheological calculation properties	Value	Unit	Test Standard
ISO Data			
Ejection temperature	182	°C	-

Test specimen production	Value	Unit	Test Standard
ISO Data			
Injection Molding, melt temperature	360	°C	ISO 294
Injection Molding, mold temperature	150	°C	ISO 294
Injection Molding, injection velocity	200	mm/s	ISO 294
Injection Molding, pressure at hold	80	MPa	ISO 294


Processing Recommendation Injection Molding	Value	Unit	Test Standard
Pre-drying - Temperature	140	°C	-
Pre-drying - Time	4	h	-
Processing humidity	≤0.02	%	-
Melt temperature	350 - 390	°C	-
Mold temperature	130 - 180	°C	-

Diagrams

Viscosity-shear rate

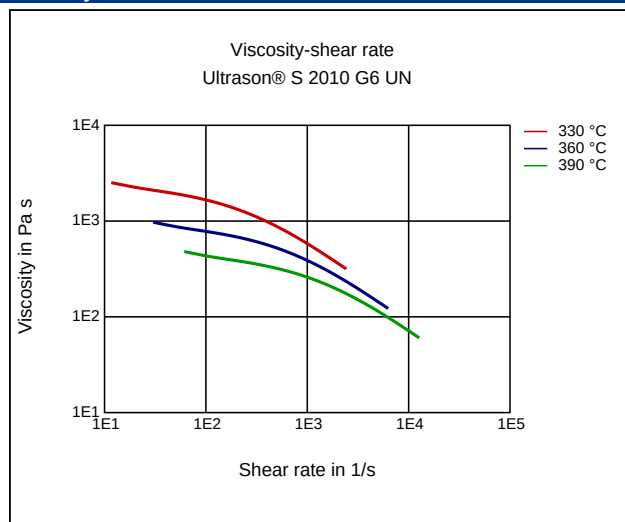


Shearstress-shear rate

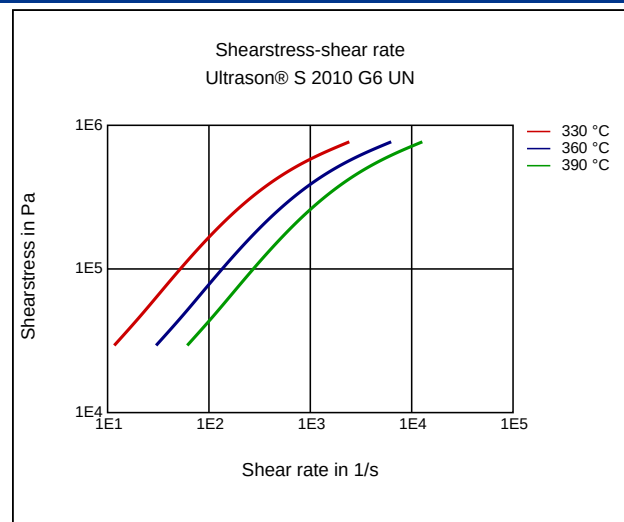


Ultrason® S 2010 G6 UN
PSU-GF30

BASF


Dynamic Shear modulus-temperature

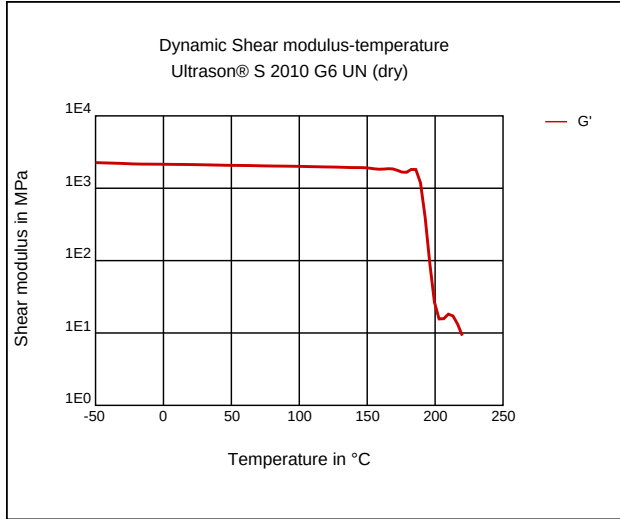


Stress-strain

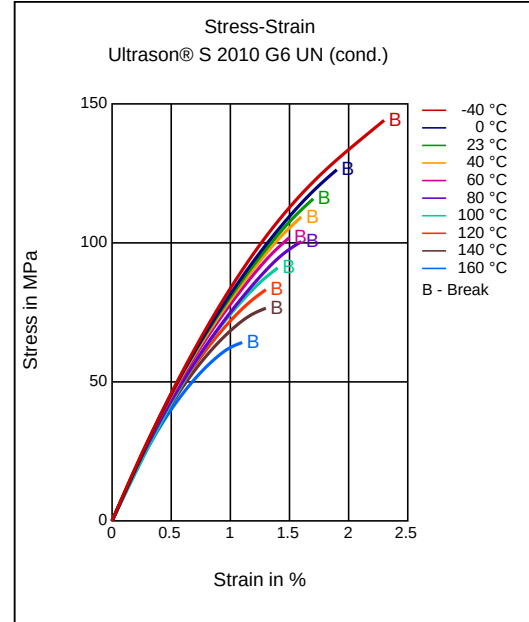

Secant modulus-strain

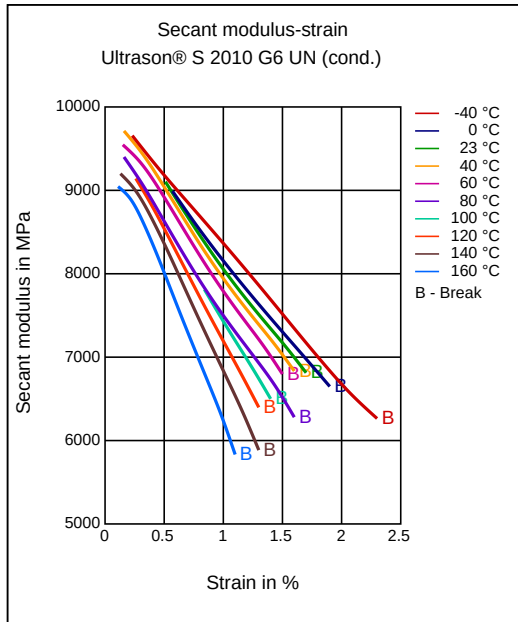


Stress-strain (isochronous) 23 °C

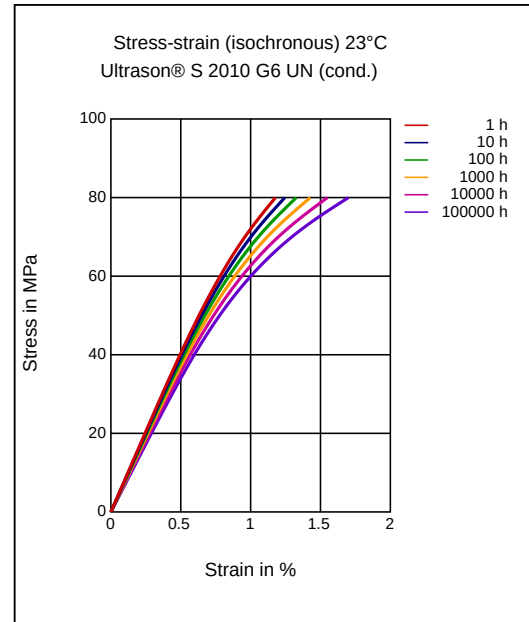


Ultrason® S 2010 G6 UN
PSU-GF30

BASF


Creep modulus-time 23°C

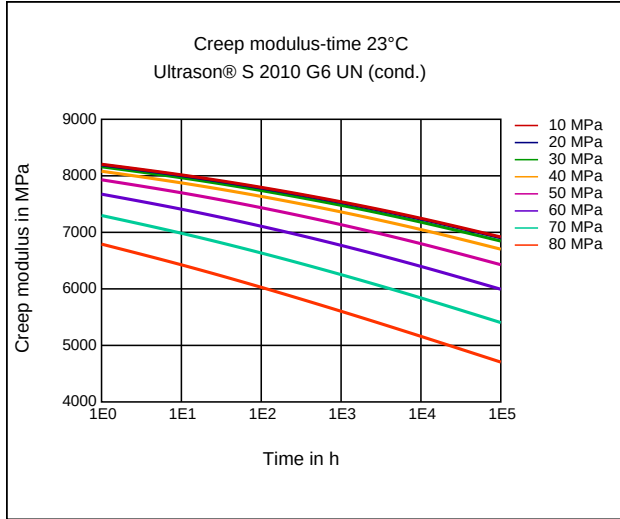


Stress-strain (isochronous) 140°C

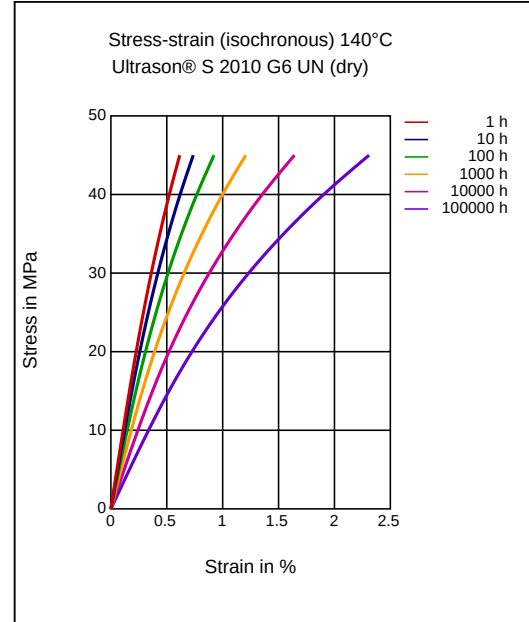

Creep modulus-time 140°C

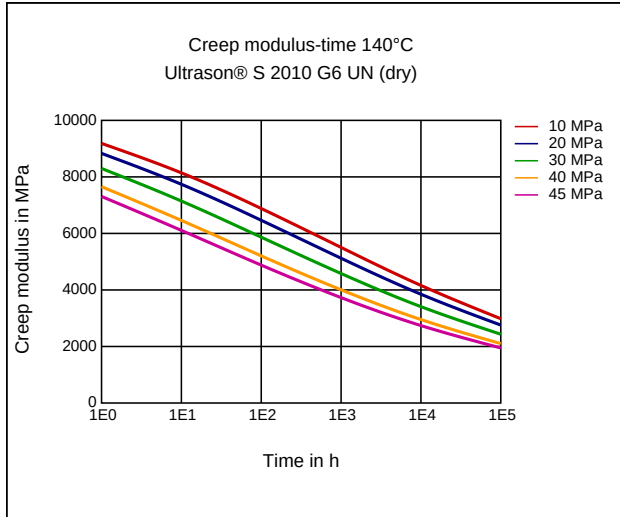


Specific volume-temperature (pvT)

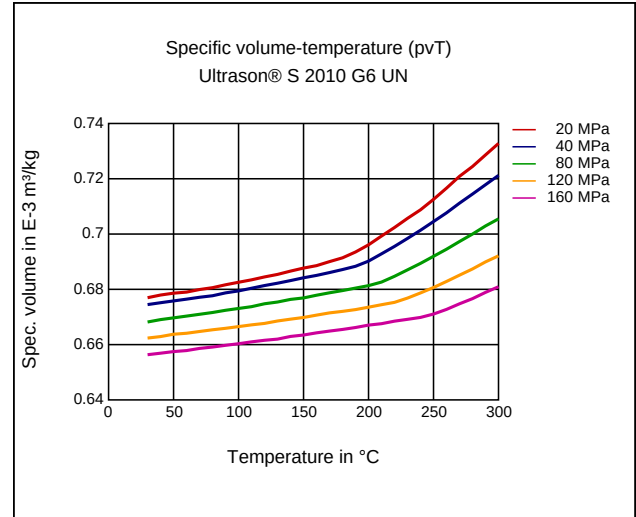

Ultrason® S 2010 G6 UN PSU-GF30

BASF

Tensile Modulus-Temperature

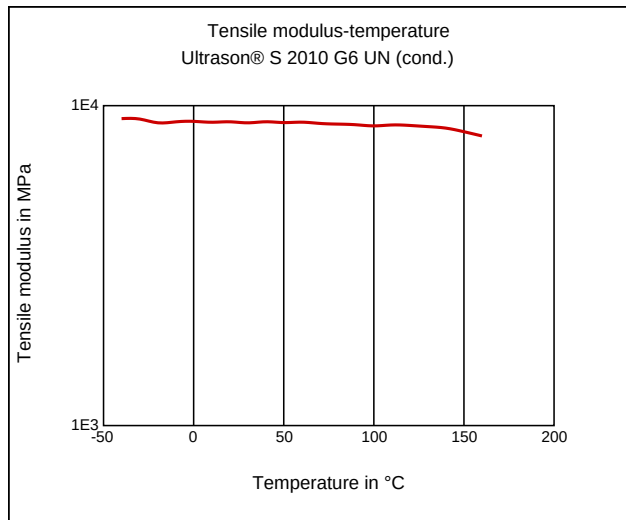

Characteristics

Processing

Injection Molding, Profile Extrusion, Sheet Extrusion

Special Characteristics

Platable

Delivery form

Pellets, Natural Color

Injection Molding

PREPROCESSING

Pre/Post-processing, max. allowed water content: .02 %

Pre/Post-processing, Pre-drying, Temperature: 140 °C

Pre/Post-processing, Pre-drying, Time: 4 h

PROCESSING

injection molding, Melt temperature, range: 350 - 390 °C

injection molding, Melt temperature, recommended: 360 °C

injection molding, Mold temperature, range: 130 - 180 °C

injection molding, Mold temperature, recommended: 150 °C

injection molding, Dwell time, thermoplastics: 10 min

Pretreatment

Drying temperature: 130 - 150 °C

Drying time: minimum 4h

recommended dryer: vacuum or dry air dryer

maximum moisture: 0,02 - 0,05%

Ultrason® can be injection molded by any type of machinery on the market, provided that the plasticizing unit and the mold temperature control system have been configured appropriately. The machinery manufacturer must be consulted if any doubts exist on the ability of various parts to withstand the high temperatures required (e.g. barrel, barrel head, bolted connections, etc.)

Long residence time in combination with high temperatures should be avoided e.g. by pump out material at regular intervals. During extended interruptions, the barrel temperature should be lowered to about 250-280 °C.

It has been found out that heating to the requested processing temperature and shutting down or lowering the temperature is best carried out in two steps.

First, the barrel temperatures are set at the lower processing temperature range for the particular thermoplastic (340 - 350 °C). As soon as these temperatures have reached a steady state, the material in the barrel is pumped out. Second, the barrel temperature can be set to the required processing temperature or the heaters can be shut down.