

RADILON A BMV150HHR 3800 BK

DESCRIPTION

PA66 15% glass fibre reinforced, high viscosity blow moulding grade. Highly heat stabilized, excellent thermal resistance. Black colour.

Suitable for hollow parts, such as tubes and containers. Especially developed for automotive hot side turbo air ducts when temperature can reach 210 °C. Also suitable for cooling circuit pipes.

ISO 1043: PA66-GF15

REGIONAL AVAILABILITY: North America, Europe, Asia Pacific, South and Central America, Near East/Africa

MATERIAL HANDLING AND PROCESSING

The material is delivered in moisture-proof packaging ready for processing. Maximum recommended water content for best processing is 0.15%. Typical conditions with a desiccant drier: temperature 80 °C, dew point -20 °C or below, time 2-4 h or more. Special care must be taken to avoid moisture absorption and contamination with other polymers when adding regrind material. Colour variation and mechanical properties reduction may occur and should always be carefully monitored.

Injection Molding Processing Parameters

Melt Temperature
280 - 300°C

Mold Temperature
80 - 90°C

Injection Speed
medium-high

Extrusion Temperature

260 - 280°C (barrel) 265-280°C (accumulator)

PRODUCT SAFETY AND APPROVALS

For safety instruction please refer to Material Safety Data Sheet
ROHS compliant 2011/65/EU and following amendments



RADILON A BMV150HHR 3800 BK

PROPERTY	STANDARD	UNIT	VALUE	
			DAM*	Cond**
PHYSICAL PROPERTIES				
Density	ISO 1183	kg/m ³	1180	
Melt Flow Rate	ISO 1133	g/10min		10
MECHANICAL PROPERTIES				
Tensile Modulus	ISO 527-2/1A	MPa	4600	
Stress at Break	ISO 527-2/1A	MPa	90	
Strain at Break	ISO 527-2/1A	%	4.5	
Flexural Modulus	ISO 178	MPa	4000	
Flexural Strength	ISO 178	MPa	135	
Charpy Impact Strength	ISO 179/1eU	kJ/m ²	70	
Charpy Notched Impact Strength	ISO 179/1eA	kJ/m ²	20	
THERMAL PROPERTIES				
Melting Temperature	ISO 11357-1/-3	°C	250	
Heat Deflection Temperature	ISO 75/2Af	°C	210	
FLAMMABILITY PROPERTIES				
Flammability	UL 94	class	HB	
Automotive Interior Flammability	ISO 3795	mm/min	0	
ELECTRICAL PROPERTIES				
Volume Resistivity	IEC 62631-3-1	Ohm*m	1E13	1E11
Surface Resistivity	IEC 62631-3-2	Ohm	1E12	1E10

*: DAM = Dry As Moulded state according to ISO 16396-2, **: Cond = Conditioned state similar to ISO 1110


1: Temperature [°C] / Load [kg]



RADILON A BMV150HHR 3800 BK

DIAGRAMS

Stress-strain (dry)

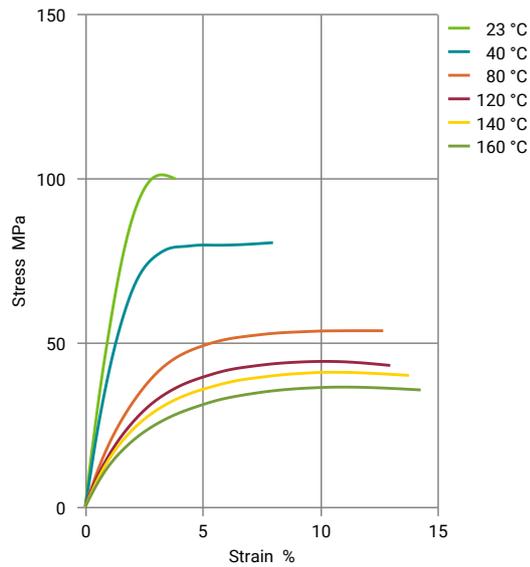

Secant modulus-strain (dry)

