

RADILON A RV300RKC 306 BK

DESCRIPTION

PA66 30% glass fibre reinforced injection moulding grade. Heat stabilized. Black colour.

Suitable for parts requiring high stiffness and good mechanical resistance. Good resistance to hydrolysis. Product specifically intended for applications in civil and industrial water management sector. Suitable and approved for drinking water and foodstuff contact.

ISO 1043: PA66-GF30

REGIONAL AVAILABILITY: North America, Europe, Asia Pacific, South and Central America, Near East/Africa

MATERIAL HANDLING AND PROCESSING

The material is delivered in moisture-proof packaging ready for processing. Maximum recommended water content for best processing is 0.15%. Typical conditions with a desiccant drier: temperature 80 ° C, dew point -20 ° C or below, time 2-4 h or more. Special care must be taken to avoid moisture absorption and contamination with other polymers when adding regrind material. Colour variation and mechanical properties reduction may occur and should always be carefully monitored.

Injection Molding Processing Parameters

Melt Temperature
280 - 300°C

Mold Temperature
80 - 100°C

Injection Speed
medium-high

PRODUCT SAFETY AND APPROVALS

For safety instruction please refer to Material Safety Data Sheet

ROHS compliant 2011/65/EU and following amendments

Underwriters Laboratories Inc. certified materia www.ul.com

Suitable for materials and articles intended to come into contact directly or indirectly with food in compliance with EU 10/2011 and FDA Title 21 CFR Chapter 1, part 177.1500

Suitable and approved for drinking water contact.

Please get in contact with our Customer Service for drinking water contact approvals and further information.



RADILON A RV300RKC 306 BK

PROPERTY	STANDARD		UNIT	VALUE	
				DAM*	Cond**
PHYSICAL PROPERTIES					
Density		ISO 1183	kg/m³	1360	
Moulding shrinkage - Parallel / Normal	300/90/60 [1]	ISO 294-4	%	0.3 / 1.0	
Water Absorption, immersion at 23°C	2mm	ISO 62	%	6.2	
Moisture Absorption 23°C - 50%RH	2mm	ISO 62	%	1.6	
MECHANICAL PROPERTIES					
Tensile Modulus	1mm/min	ISO 527-2/1A	MPa	9500	7500
Stress at Break	5mm/min	ISO 527-2/1A	MPa	170	130
Strain at Break	5mm/min	ISO 527-2/1A	%	3.3	5
Flexural Modulus	2mm/min	ISO 178	MPa	8800	6500
Flexural Strength	2mm/min	ISO 178	MPa	270	205
Charpy Impact Strength	+23°C	ISO 179/1eU	kJ/m²	70	85
Charpy Impact Strength	-30°C	ISO 179/1eU	kJ/m²	60	
Charpy Notched Impact Strength	+23°C	ISO 179/1eA	kJ/m²	10	15
Charpy Notched Impact Strength	-30°C	ISO 179/1eA	kJ/m²	9	
THERMAL PROPERTIES					
Melting Temperature	10°C/min	ISO 11357-1/-3	°C	260	
Heat Deflection Temperature	1.80 MPa	ISO 75/2Af	°C	245	
Heat Deflection Temperature	0.45 MPa	ISO 75/2Bf	°C	255	
Vicat Softening Temperature	50°C/h 50N	ISO 306	°C	250	
FLAMMABILITY PROPERTIES					
Flammability	0.8mm	UL 94	class	HB	
Glow Wire Flammability Index	2mm	IEC 60695-2-12	°C	700	
Automotive Interior Flammability	3mm	ISO 3795	mm/min	0	
ELECTRICAL PROPERTIES					
Volume Resistivity	500V	IEC 62631-3-1	Ohm*m	1E13	1E11
Surface Resistivity	500V	IEC 62631-3-2	Ohm	1E12	1E10
Comparative Tracking Index	Sol.A	IEC 60112	V	500	

*: DAM = Dry As Moulded state according to ISO 16396-2, **: Cond = Conditioned state similar to ISO 1110


1: Melt Temperature [°C] / Mold Temperature [°C] / Cavity Pressure [MPa]




RADILON A RV300RKC 306 BK

DIAGRAMS


Viscosity-shear rate

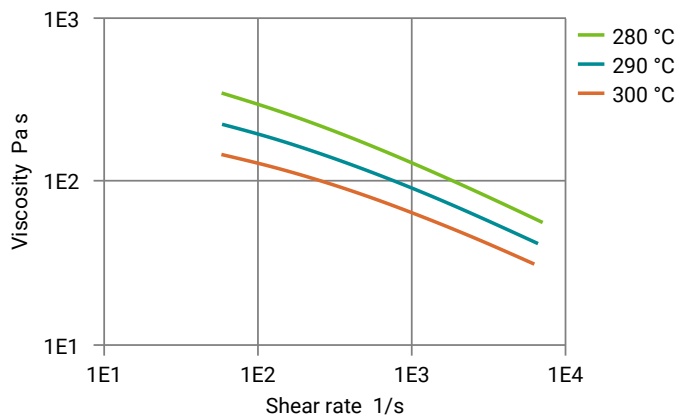


Shearstress-shear rate

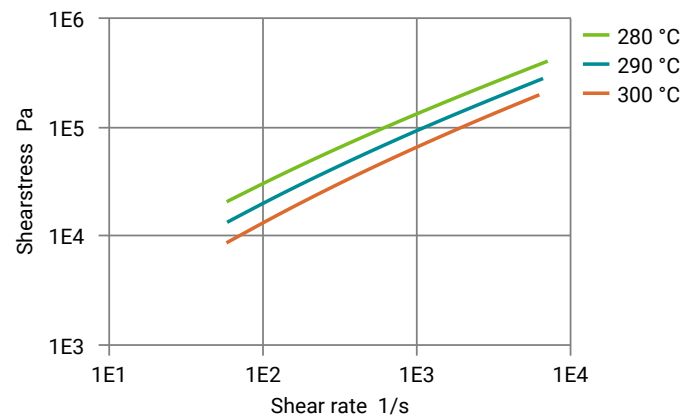

Stress-strain (cond.)

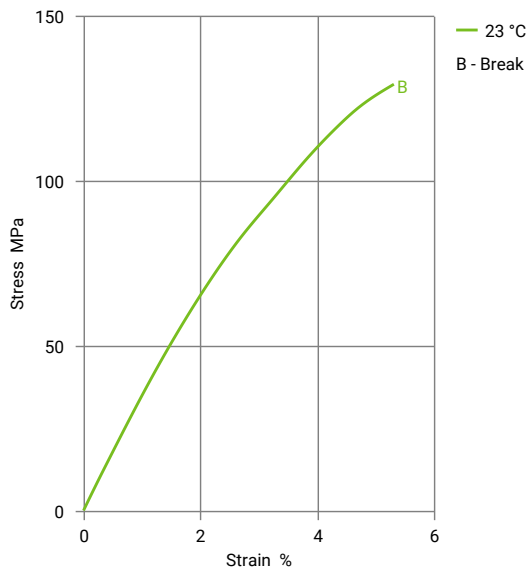


Stress-strain (dry)

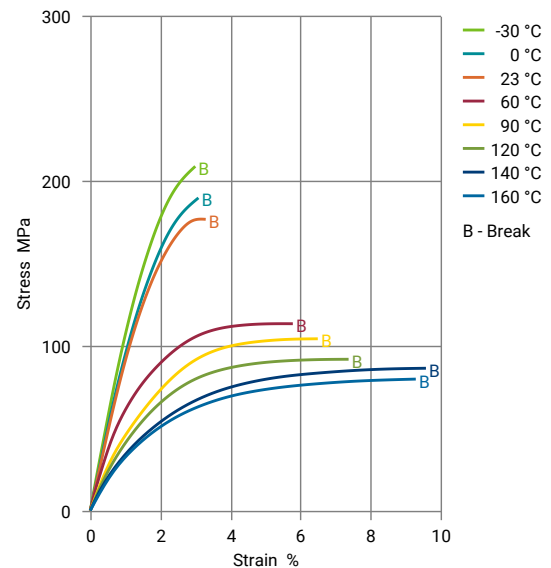


RADILON A RV300RKC 306 BK

Secant modulus-strain (cond.)

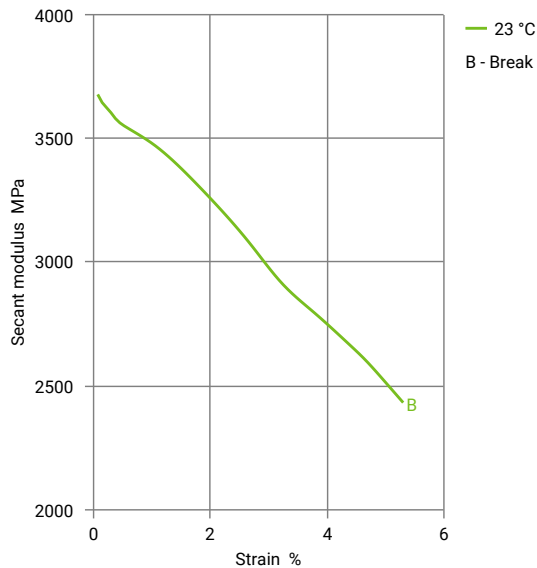

Secant modulus-strain (dry)

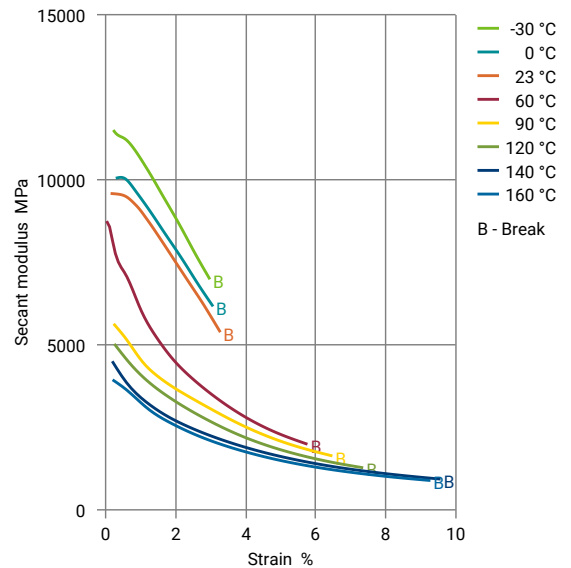

Specific volume-temperature (pvT)

