

RADILON S RV300W 333 BK

DESCRIPTION

PA6 30% glass fibre reinforced injection moulding grade. Heat stabilized. Black colour.

Suitable for parts requiring high stiffness, good mechanical resistance and excellent heat ageing properties retention.

ISO 1043: PA6-GF30

REGIONAL AVAILABILITY: North America, Europe, Asia Pacific, South and Central America, Near East/Africa

MATERIAL HANDLING AND PROCESSING

The material is delivered in moisture-proof packaging ready for processing. Maximum recommended water content for best processing is 0.15%. Typical conditions with a desiccant drier: temperature 80 ° C, dew point -20 ° C or below, time 2-4 h or more. Special care must be taken to avoid moisture absorption and contamination with other polymers when adding regrind material. Colour variation and mechanical properties reduction may occur and should always be carefully monitored.

Injection Molding Processing Parameters

Melt Temperature
240 - 280°C

Mold Temperature
80 - 90°C

Injection Speed
medium-high

PRODUCT SAFETY AND APPROVALS

For safety instruction please refer to Material Safety Data Sheet
ROHS compliant 2011/65/EU and following amendments



RADILON S RV300W 333 BK

PROPERTY	STANDARD	UNIT	VALUE	
			DAM*	Cond**
PHYSICAL PROPERTIES				
Density		kg/m ³	1350	
Moulding shrinkage - Parallel / Normal	280/90/60 ^[1]	%	0.3 / 0.8	
Water Absorption, immersion at 23°C	2mm	%	7.5	
Moisture Absorption 23°C - 50%RH	2mm	%	2	
MECHANICAL PROPERTIES				
Tensile Modulus	1mm/min	MPa	9400	6200
Stress at Break	5mm/min	MPa	165	105
Strain at Break	5mm/min	%	3.2	6
Flexural Modulus	2mm/min	MPa	8800	
Flexural Strength	2mm/min	MPa	255	
Charpy Impact Strength	+23°C	kJ/m ²	85	100
Charpy Impact Strength	-30°C	kJ/m ²	70	
Charpy Notched Impact Strength	+23°C	kJ/m ²	13	20
Charpy Notched Impact Strength	-30°C	kJ/m ²	9	
THERMAL PROPERTIES				
Melting Temperature	10°C/min	°C	220	
Heat Deflection Temperature	1.80 MPa	°C	200	
Heat Deflection Temperature	0.45 MPa	°C	215	
Vicat Softening Temperature	50°C/h 50N	°C	210	
Coeff. of Linear Therm. Expansion	parallel, 23°C-55°C	E-6/K	25	
Coeff. of Linear Therm. Expansion	normal, 23°C-55°C	E-6/K	95	
FLAMMABILITY PROPERTIES				
Flammability	0.8mm	class	HB	
Glow Wire Flammability Index	2mm	°C	650	
Automotive Interior Flammability	3mm	mm/min	0	
ELECTRICAL PROPERTIES				
Volume Resistivity	500V	Ohm*m	1E13	1E11
Surface Resistivity	500V	Ohm	1E12	1E10
Comparative Tracking Index	Sol.A	V	500	

*: DAM = Dry As Moulded state according to ISO 16396-2, **: Cond = Conditioned state similar to ISO 1110


1: Melt Temperature [°C] / Mold Temperature [°C] / Cavity Pressure [MPa]




RADILON S RV300W 333 BK

DIAGRAMS


Viscosity-shear rate

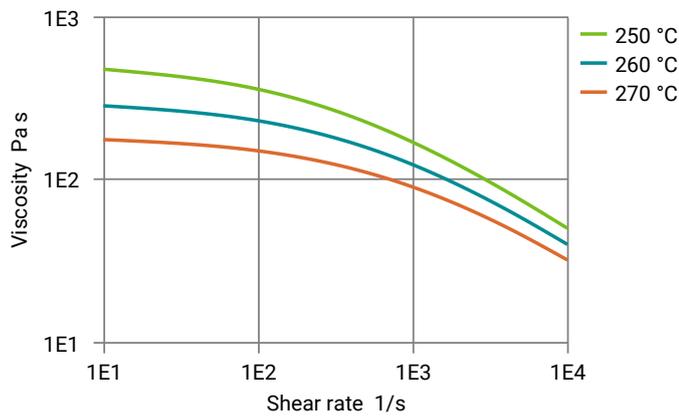


Shearstress-shear rate

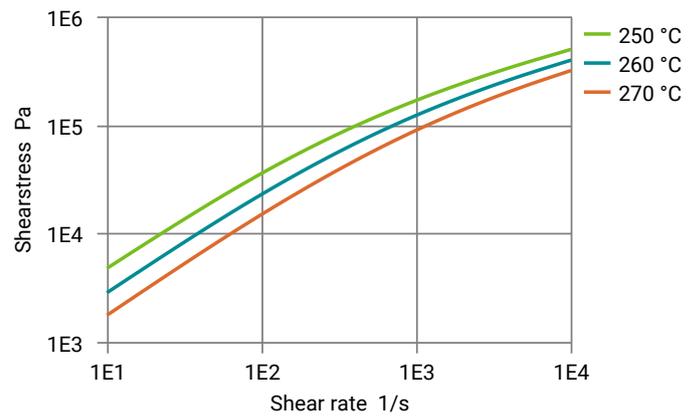

Dynamic Shear modulus-temperature (dry)

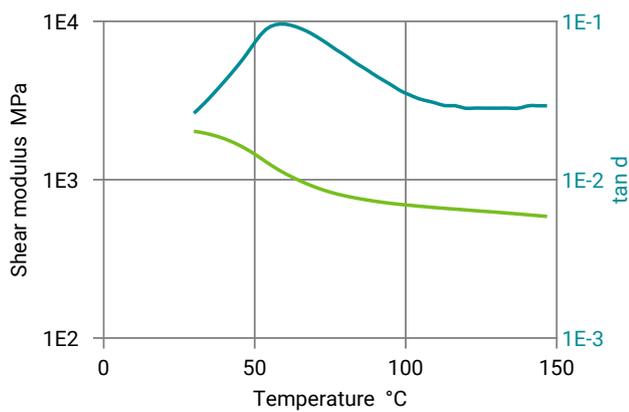


Stress-strain (cond.)

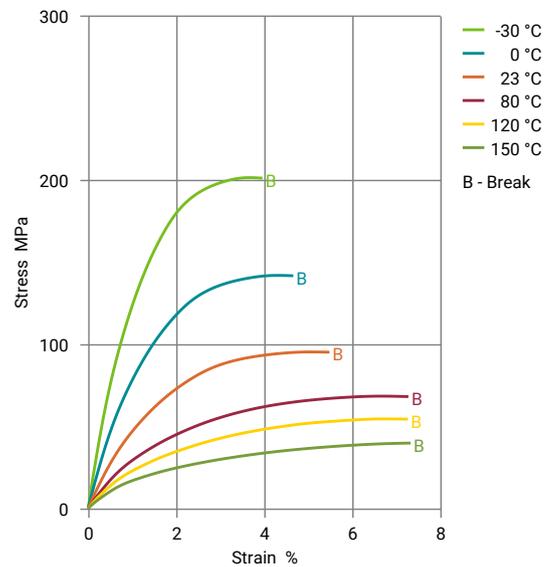


RADILON S RV300W 333 BK


Stress-strain (dry)

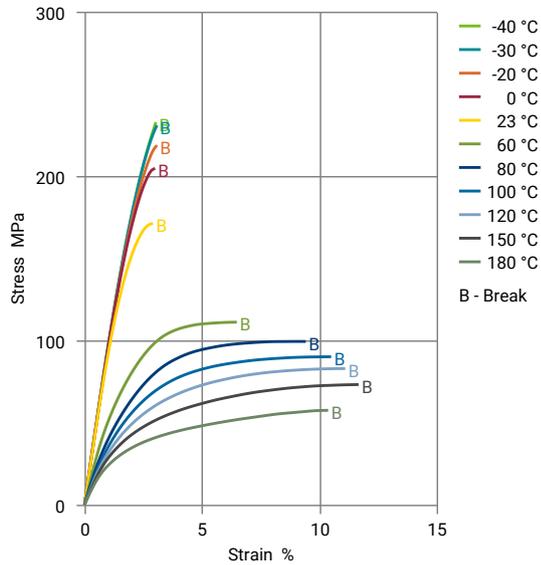


Secant modulus-strain (cond.)

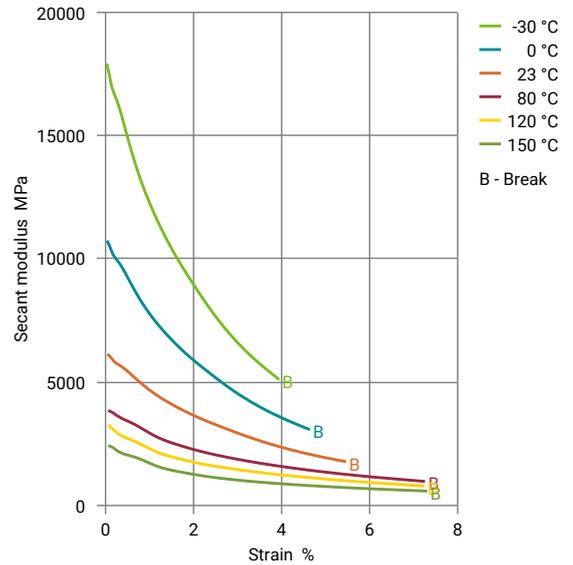

Secant modulus-strain (dry)

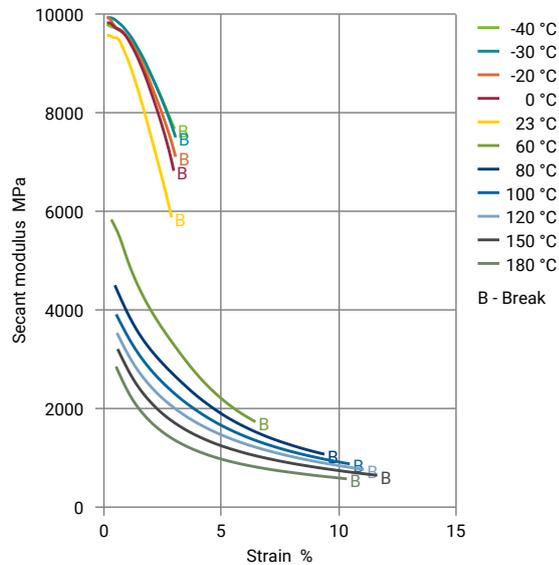


Specific volume-temperature (pvT)

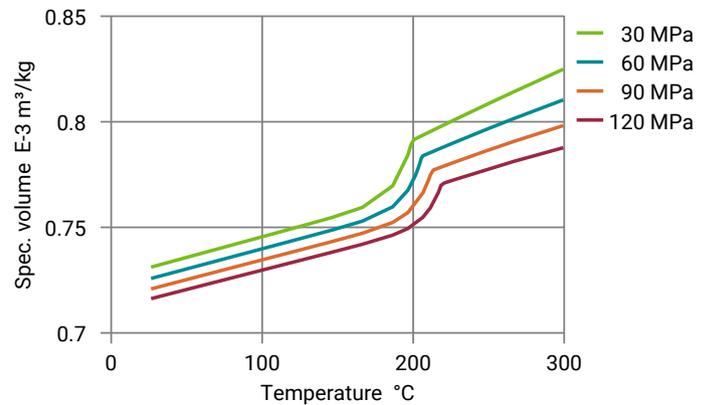


RADILON S RV300W 333 BK


Tensile modulus-temperature (cond.)

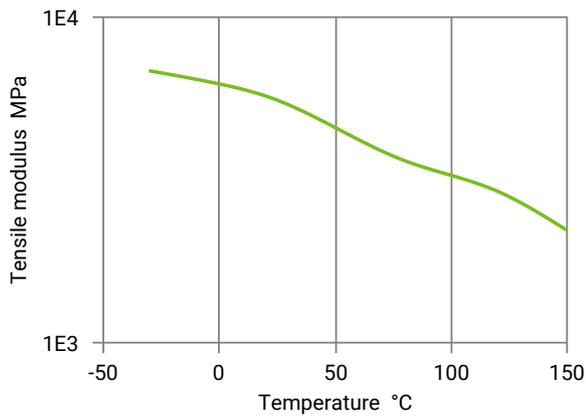


Tensile modulus-temperature (dry)

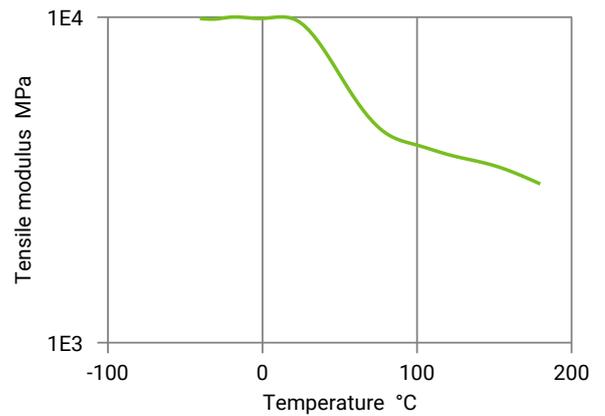

Thermal expansion

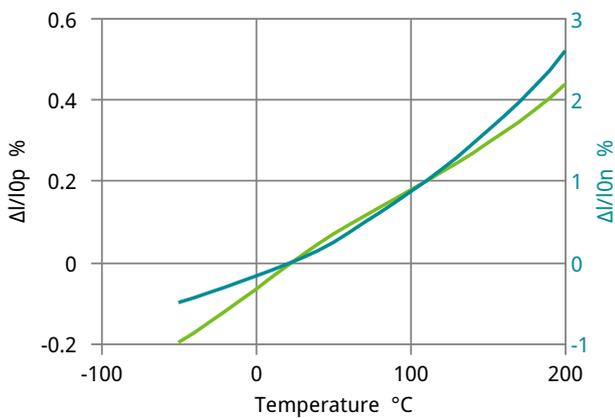


LTHA-Stress at Break 4mm (dry)

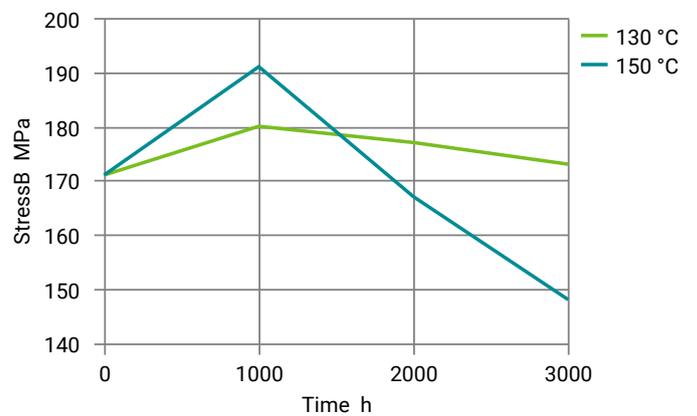


RADILON S RV300W 333 BK

LTHA-Strain at Break 4mm (dry)

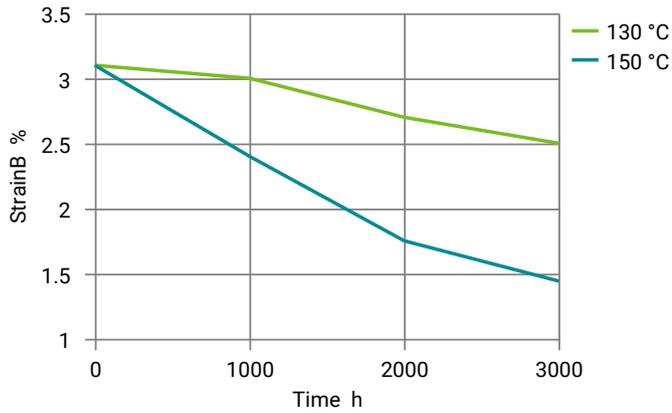

LTHA-Charpy Impact Strength (23°C) 4mm (dry)

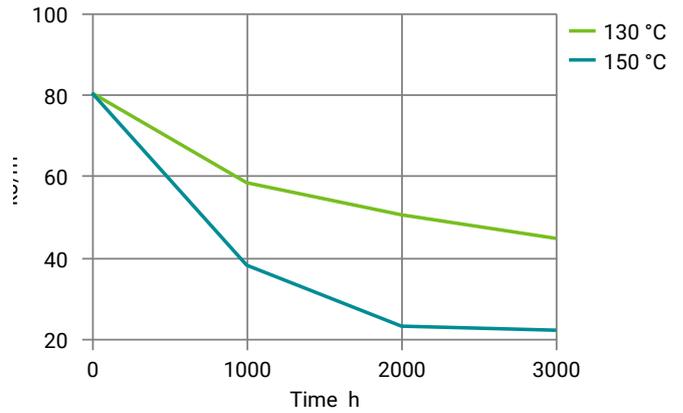

LTHA-Charpy Notched Impact Strength (23°C) 4mm (dry)

