


Technyl® A 20 V35

PA66-GF35 FR

Solvay Engineering Plastics


Product Texts

Polyamide 6.6, 35 % glass fibre reinforced
 flame retardant with red phosphorus, halogen free UL 94 V0 rated at 0.8 mm wall thickness


Mechanical properties	dry / cond	Unit	Test Standard
ISO Data			
Tensile Modulus	12000 / 10000	MPa	ISO 527-1/-2
Stress at break	170 / -	MPa	ISO 527-1/-2
Strain at break	2 / -	%	ISO 527-1/-2
Charpy impact strength (+23°C)	65 / -	kJ/m ²	ISO 179/1eU
Charpy notched impact strength (+23°C)	10 / -	kJ/m ²	ISO 179/1eA
Thermal properties			
ISO Data			
Melting temperature (10°C/min)	263 / *	°C	ISO 11357-1/-3
Temp. of deflection under load (1.80 MPa)	255 / *	°C	ISO 75-1/-2
Temp. of deflection under load (0.45 MPa)	255 / *	°C	ISO 75-1/-2
Coeff. of linear therm. expansion, parallel	25 / *	E-6/K	ISO 11359-1/-2
Burning behav. at thickness h	V-0 / *	class	IEC 60695-11-10
Thickness tested	1.6 / *	mm	IEC 60695-11-10
Oxygen index	30.5 / *	%	ISO 4589-1/-2
Electrical properties			
ISO Data			
Relative permittivity, 1MHz	3.4 / 5	-	IEC 60250
Dissipation factor, 1MHz	200 / -	E-4	IEC 60250
Volume resistivity	1E13 / 1E11	Ohm*m	IEC 60093
Surface resistivity	* / 1E12	Ohm	IEC 60093
Electric strength	25 / 25	kV/mm	IEC 60243-1
Comparative tracking index	375 / -	-	IEC 60112
Other properties			
ISO Data			
Water absorption	4.5 / *	%	Sim. to ISO 62
Humidity absorption	1.4 / *	%	Sim. to ISO 62
Density	1460 / -	kg/m ³	ISO 1183
Test specimen production			
ISO Data			
Injection Molding, melt temperature	220	°C	ISO 294
Injection Molding, mold temperature	23	°C	ISO 10724

Diagrams


Viscosity-shear rate

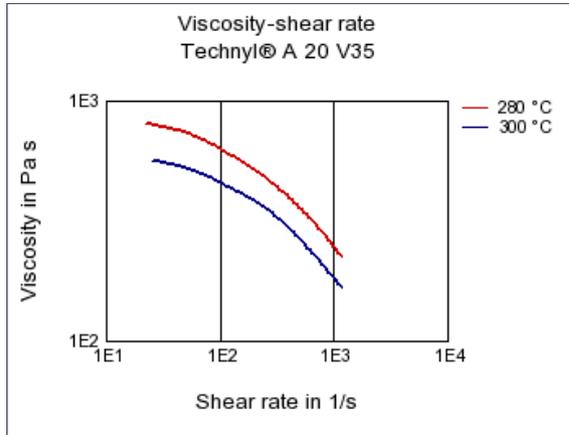

Shearstress-shear rate

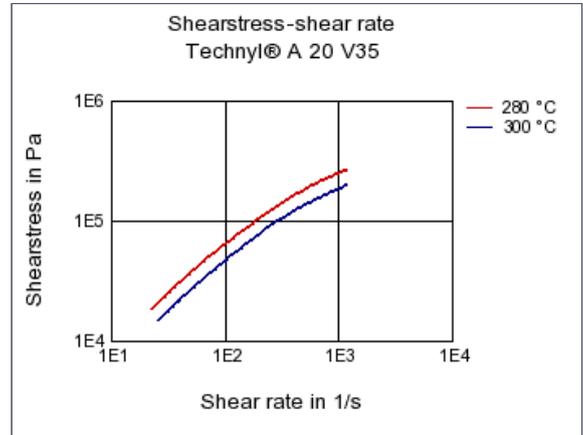

Stress-strain

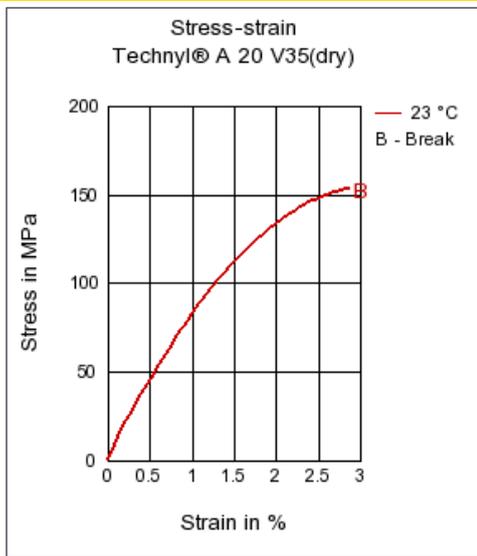

Characteristics

Processing

Injection Molding

Special Characteristics

Flame retardant, Heat stabilized or stable to heat

Other text information

Injection Molding

Recommended moulding conditions :

Barrel temperatures :

- feed zone 270 - 275°C

- compression zone 275 - 280°C

- front zone 280 - 285°C

Mould: 60 at 80°C

Chemical Media Resistance

Acids

- 😊 Acetic Acid (5% by mass) (23°C)
- 😊 Citric Acid solution (10% by mass) (23°C)
- 😊 Lactic Acid (10% by mass) (23°C)
- 🚫 Hydrochloric Acid (36% by mass) (23°C)
- 🚫 Nitric Acid (40% by mass) (23°C)

-  Sulfuric Acid (38% by mass) (23°C)
-  Sulfuric Acid (5% by mass) (23°C)
-  Chromic Acid solution (40% by mass) (23°C)

Bases

-  Sodium Hydroxide solution (35% by mass) (23°C)
-  Sodium Hydroxide solution (1% by mass) (23°C)
-  Ammonium Hydroxide solution (10% by mass) (23°C)

Alcohols

-  Isopropyl alcohol (23°C)
-  Methanol (23°C)
-  Ethanol (23°C)

Hydrocarbons

-  n-Hexane (23°C)
-  Toluene (23°C)
-  iso-Octane (23°C)

Ketones

-  Acetone (23°C)

Ethers

-  Diethyl ether (23°C)

Mineral oils

-  SAE 10W40 multigrade motor oil (23°C)

Standard Fuels

-  Standard fuel with alcohol (pref. ISO 1817 Liquid 4) (23°C)

Salt solutions

-  Zinc Chloride solution (50% by mass) (23°C)

Other

-  Ethylene Glycol (50% by mass) in water (108°C)
-  50% Oleic acid + 50% Olive Oil (23°C)
-  Water (23°C)
-  Deionized water (90°C)