

## PLEXIGLAS® 8N

Röhm GmbH  
PMMA

### **Processing**

Injection molding

### **Delivery Form**

Pellets

### **Additives**

Release agent

### **Special Characteristics**

Light stabilized or stable to light, U.V. stabilized or stable to weather, Heat stabilized or stable to heat, Transparent

### **Features**

Amorphous

### **Applications**

Automotive

## Product Text

### **Product Information**

#### **Productprofil:**

PLEXIGLAS® 8N is an amorphous thermoplastic molding compound (PMMA).

Typical properties of PLEXIGLAS® molding compounds are:

- good flow
- high mechanical strength, surface hardness and abrasion resistance
- high light transmission
- very good weather resistance
- free colorability due to crystal clarity

Special properties of PLEXIGLAS® 8N are:

- optimum mechanical properties
- maximum heat deflection temperature
- good flow / melt viscosity
- AMECA listing.

#### **Application:**

Used for injection molding optical and technical items.

# PLEXIGLAS® 8N

Röhm GmbH

## **Example:**

optical waveguides, luminaire covers, automotive lighting, instrument cluster covers, optical lenses, displays, etc.

## **Processing:**

PLEXIGLAS® 8N can be processed on injection molding machines with 3-zone general purpose screws for engineering thermoplastics.

## **Physical Form / Packaging:**

PLEXIGLAS® molding compounds are supplied as pellets of uniform size, packaged in 25kg polyethylene bags or in 500kg boxes with PE lining; other packaging on request.

Processing/Physical Characteristics	Value	Unit	Standard
Melt volume-flow rate, MVR	3	cm <sup>3</sup> /10min	ISO 1133
Temperature	230	°C	
Load	3.8	kg	
Density of melt	1062	kg/m <sup>3</sup>	
Thermal conductivity of melt	0.181	W/(m K)	
Spec. heat capacity of melt	2438	J/(kg K)	
Eff. thermal diffusivity	6.991E-8	m <sup>2</sup> /s	
Ejection temperature	90	°C	
Mechanical Properties	Value	Unit	Standard
Tensile modulus	3300	MPa	ISO 527
Stress at break	77	MPa	ISO 527
Strain at break	5.5	%	ISO 527
Poisson's ratio	0.35		ISO 527
Tensile creep modulus, 1h	2800	MPa	ISO 899-1
Tensile creep modulus, 1000h	2200	MPa	ISO 899-1
Charpy impact strength, +23°C	20	kJ/m <sup>2</sup>	ISO 179/1eU
Thermal Properties	Value	Unit	Standard
Glass transition temperature, 10°C/min	117	°C	ISO 11357-1/-2
Temp. of deflection under load, 1.80 MPa	98	°C	ISO 75-1/-2
Temp. of deflection under load, 0.45 MPa	103	°C	ISO 75-1/-2
Vicat softening temperature, B	108	°C	ISO 306
Coeff. of linear therm. expansion, parallel	80	E-6/K	ISO 11359-1/-2
Burning behav. at 1.5 mm nom. thickn.	HB	class	IEC 60695-11-10
Thickness tested	1.57	mm	
Yellow card available	yes		

# PLEXIGLAS® 8N

Röhm GmbH


Thermal Properties	Value	Unit	Standard
Oxygen index	17.2	%	ISO 4589-1/-2
Electrical Properties	Value	Unit	Standard
Relative permittivity, 100Hz	3.6		IEC 62631-2-1
Relative permittivity, 1MHz	2.7		IEC 62631-2-1
Dissipation factor, 100Hz	500	E-4	IEC 62631-2-1
Dissipation factor, 1MHz	200	E-4	IEC 62631-2-1
Volume resistivity	>1E13	Ohm*m	IEC 62631-3-1
Surface resistivity	1E13	Ohm	IEC 62631-3-2
Comparative tracking index	600		IEC 60112
Optical Properties	Value	Unit	Standard
Luminous transmittance	92	%	ISO 13468-1, -2
Other Properties	Value	Unit	Standard
Water absorption	2	%	Sim. to ISO 62
Humidity absorption	0.6	%	Sim. to ISO 62
Density	1190	kg/m <sup>3</sup>	ISO 1183
Material Specific Properties	Value	Unit	Standard
Viscosity number	53	cm <sup>3</sup> /g	ISO 307, 1157, 1628
Test Specimen Production	Value	Unit	Standard
Processing conditions acc. ISO	8257		ISO ....-2
Injection molding, melt temperature	248	°C	ISO 294
Injection molding, mold temperature	68	°C	ISO 294
Injection molding, injection velocity	195	mm/s	ISO 294

## Diagrams


# PLEXIGLAS® 8N

Röhm GmbH


Stress-strain

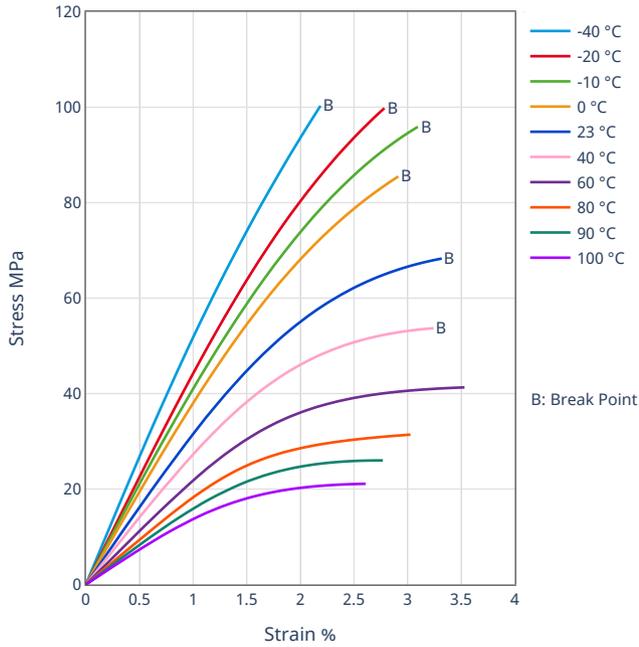


True stress-true strain

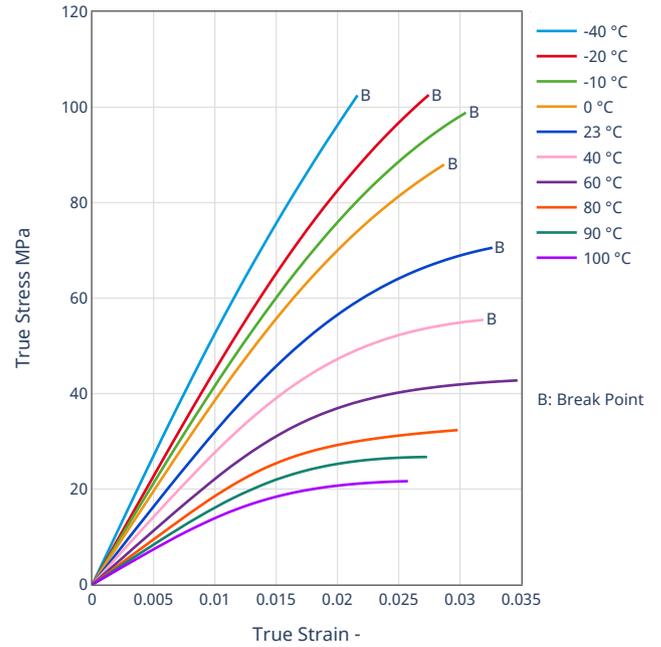

Secant modulus-strain

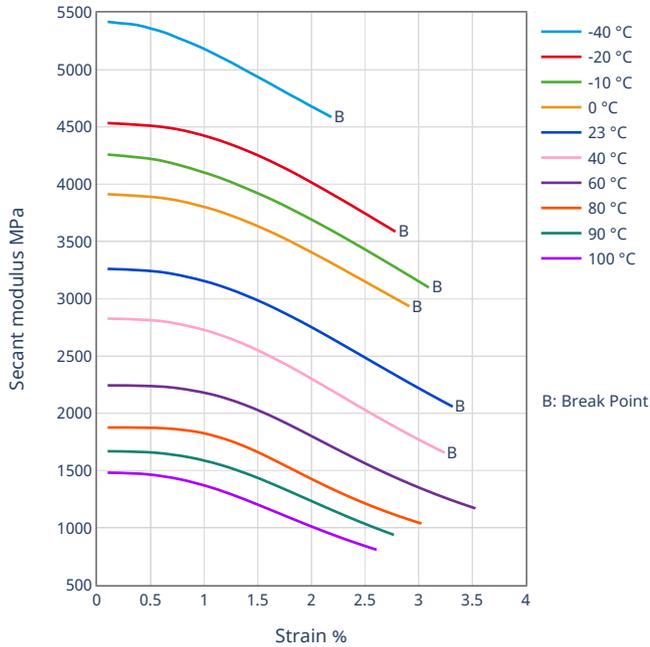


Viscosity-shear rate

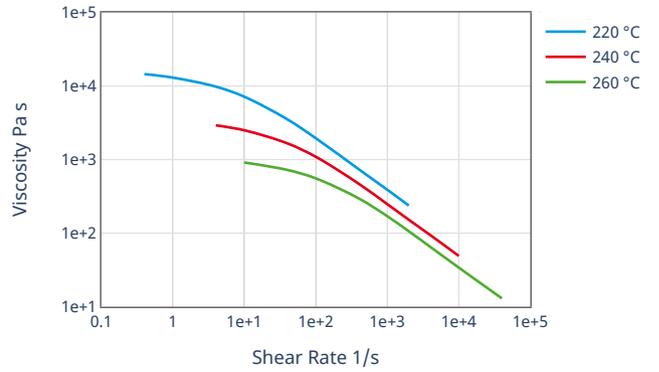


# PLEXIGLAS® 8N

Röhm GmbH


### Shearstress-shear rate

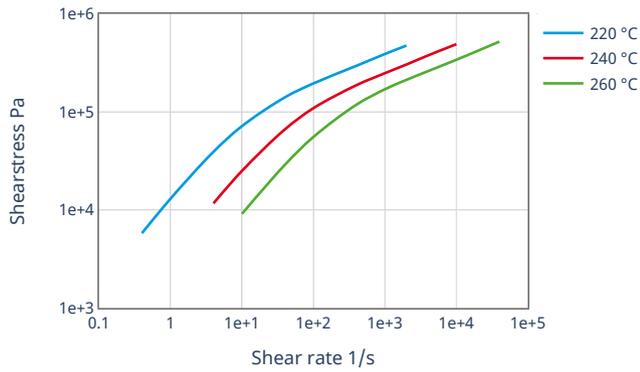


### Spec. volume-Temperature (pVT) ->Generic PMMA

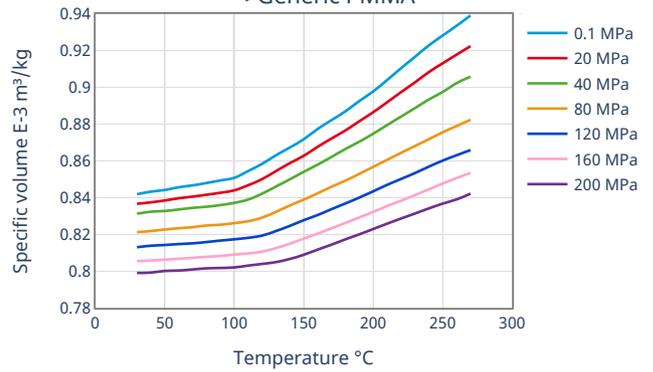

### Dynamic shear modulus-temperature

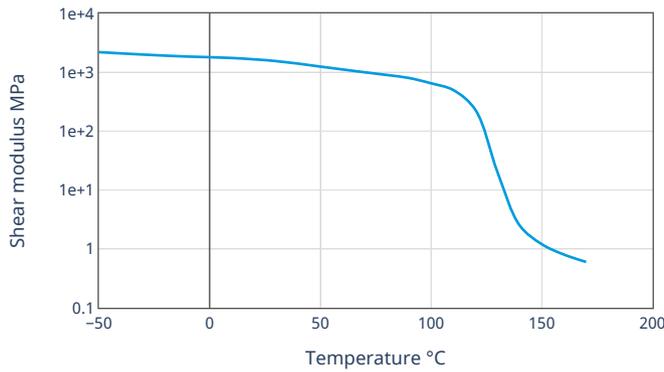


### Stress-strain (isochronous) 23°C

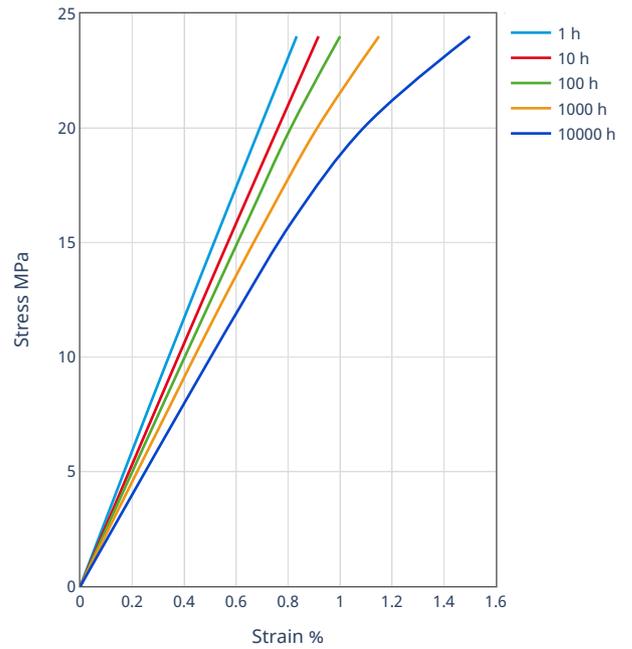


# PLEXIGLAS® 8N

Röhm GmbH


Creep modulus-time 23°C

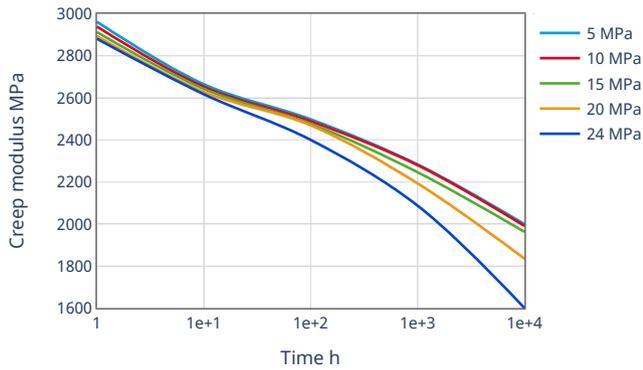

Creep curve 23°C

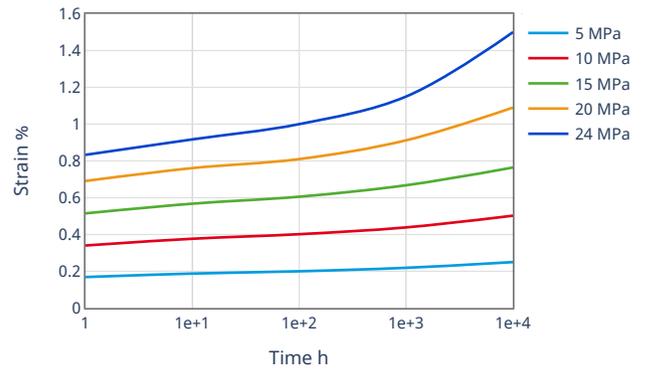

Tensile modulus-temperature

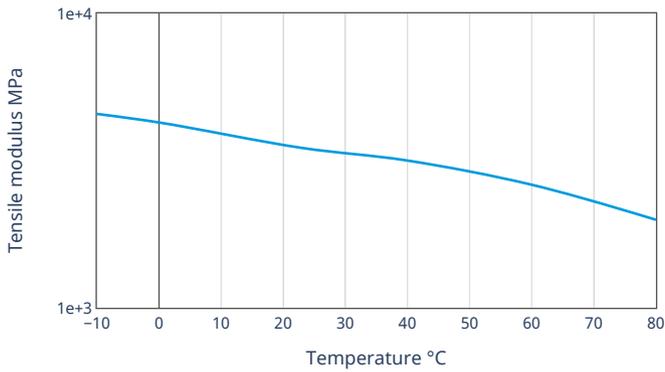

## Processing Information

### Injection molding

#### PREPROCESSING

Predrying temperature: max. 98 °C

Predrying time in a desiccant-type drier: 2 - 3 h

#### PROCESSING

Melt temperature: 220 - 260°C

Mold temperature: 60 - 90°C